



# UNIVERSITÀ DI PARMA

## ARCHIVIO DELLA RICERCA

University of Parma Research Repository

Asphalt-based cold patches for repairing road potholes - An overview

This is the peer reviewed version of the following article:

*Original*

Asphalt-based cold patches for repairing road potholes - An overview / Hafezzadeh, Raheb; Autelitano, Federico; Giuliani, Felice. - In: CONSTRUCTION AND BUILDING MATERIALS. - ISSN 0950-0618. - 306:(2021), pp. 124870.1-124870.19. [10.1016/j.conbuildmat.2021.124870]

*Availability:*

This version is available at: 11381/2902412 since: 2021-11-05T17:58:23Z

*Publisher:*

Elsevier

*Published*

DOI:10.1016/j.conbuildmat.2021.124870

*Terms of use:*

Anyone can freely access the full text of works made available as "Open Access". Works made available

*Publisher copyright*

note finali coverpage

(Article begins on next page)

02 May 2026

# Asphalt-Based Cold Patches for Repairing Road Potholes- An Overview

Cold Mix Patching Materials (CMPMs) are usually used instead of Hot Mix Asphalt (HMA) to repair potholes and localized distresses. Although these materials provide immediate serviceability, they have a relatively short life. However, worldwide interest in these solutions, which started as fragmented industrial initiatives, is growing. This article provides a critical comparison between several aspects regarding using CMPMs and HMA in repairing potholes. Specifically, repair techniques, productivity and costs were investigated in detail. Plus, the impact of the main crucial factors, i.e., workability, bonding, water susceptibility, stability, and storageability, on the performance of CMPMs was investigated through an overview.

**Keywords:** Cold mix asphalt, Pothole, Patch materials, Serviceability, Pavement maintenance

## 1. Introduction

Road asphalt pavements suffer from various deteriorations during their life-cycle, which requires technical and economic resources for repair and maintenance. One of the most common forms of this distress is potholes [1]. Repairing potholes costs millions of euros annually and imposes a budget constraint on the maintenance organizations. In many cases, especially for local authorities, funding for maintaining road surfaces is the most important matter. Potholes often appear towards the end of the winter season, after prolonged periods of rain or during thawing periods, as a result of defects in the preventive maintenance of wearing courses (sealing) favored by sub-bases with poor bearing capacity or poor drainage. They can influence road users' operations and traffic safety and increase the number of crashes with resulting injuries and even fatalities [2-7]. A report by the ministry of road transport and highways of India shows more than 1% of the accidents and deaths in 2018 and 2019 have occurred due to potholes [8]. Besides, the durability and life span of the pavement are affected by the occurrence and subsequent spread of potholes. This is especially true during the winter months, when potholes grow rapidly, making it extremely difficult to repair countless breakdowns in adverse weather [7, 9], and also when there are no adequate strategies and budgets for a preventive maintenance program. The repair operations in warmer weather conditions are usually applied by conventional Hot Mix Asphalt (HMA) that has a low initial cost but desired performance [10, 11]. However, the availability and application of HMA in wintertime are strongly affected by low temperatures, which induce its thermal dissipation

1 34 during hauling to the jobsite. Besides, the repair materials come into contact with stagnant  
2 35 water and the closure of the traffic should not last for a long time. Thus, road maintenance  
3 36 agencies are propelled to use appropriate temporary repair methods to restore the serviceability  
4 37 of the pavement in a short time [12-14].

5 38 In recent years, Cold Mix Patching Materials (CMPMs) have become popular for temporary  
6 39 repairs due to their ease of handling, affordability, few required labor and equipment, and long  
7 40 storage time. Plus, they have lower environmental impacts. However, at the time of writing  
8 41 this paper, there was no precise information about the percentage of unused bagged CMPMs.  
9 42 Also, the environmental implications in terms of increases in special waste and management  
10 43 of packaging waste are not known [15-18]. These mixtures have a short application time and  
11 44 are potentially suitable for repairing potholes in different climates. Plus, as they can be  
12 45 produced in various quantities and stored for several months in sealed containers or stockpiled  
13 46 around the road, repairing scattered distresses that require small quantities of materials can be  
14 47 facilitated with them [16, 19]. However, despite all of the mentioned advantages, CMPMs have  
15 48 the lowest quality of all the patching materials. Repaired potholes during adverse weather  
16 49 conditions, especially in wet winter and spring, withstand only a few freeze-thaw cycles and  
17 50 are sometimes physically removed even by the first traffic actions. They usually have a short  
18 51 lifetime and need frequent treatment operations [6, 19]. Additionally, CMPMs deal with  
19 52 different types of deficiencies, such as poor workability, less durability, rutting, poor skid  
20 53 resistance, adhesion and cohesion problems during the stockpile and under in-service  
21 54 conditions [15, 20]. Since there are no standards for designing and evaluating CMPMs, the  
22 55 state of practice experiences a heterogeneity of product types, and various CMPMs with  
23 56 different test methods have been employed by researchers to design the CMPMs and  
24 57 investigate their performance.

25 58 Thus, after a detailed description of pothole formation mechanisms and their general  
26 59 maintenance and rehabilitation techniques, the paper focused on the development of CMPMs  
27 60 over the past years in comparison to conventional hot patch mixtures with specific attention to  
28 61 their components, curing, and performance evaluation.

## 2. Pothole description

### 2.1. Definition, formation mechanism, and severity levels

29 64 Although several definitions have been proposed to identify a pothole, it can be simply  
30 65 described as “a bowl-shaped hole of various sizes in the pavement surface” [21] or in greater  
31 66

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
67 detail as “a localized deterioration of road pavement resulting from a loss of material or  
68 depression in the pavement surface” [1]. Potholes are caused by a combination of physical,  
69 mechanical, and environmental stresses. Specifically, water infiltration and traffic loads play  
70 the main roles in the initiation and growth of potholes. Continuous traffic, especially in adverse  
71 weather conditions, leads to cracks in the pavement, which are the prerequisite for pothole  
72 formation [22-24]. The cracks in the pavement facilitate water seepage into the road structure.  
73 Then, the occurrence of freezing and thawing cycles due to water ingress leads to loss of  
74 support in the road layers, and consequently, more serious damage is caused [25-27]. Despite  
75 water permeability and traffic, other factors, such as poor mix design or inadequate  
76 construction methods [28], defective geometric design of the road [12], material failure,  
77 raveling, stripping, bleeding and shoving of the pavement [27, 29], lack of information and  
78 defective workmanship, excavation and reinstatements by utility companies [30], inappropriate  
79 pavement repair and winter maintenance practices, especially snow removal [31, 32], reduction  
80 in lifespan of the road structure, fatigue and interconnected alligator cracks, etc., simplify the  
81 formation of potholes and various damages [33-35].

27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65  
82 Road management classifies potholes and their severity levels based on their dimensions,  
83 surface area, and depth [28]. These parameters are further influenced by other factors, such as  
84 climate conditions, speed and intensity of traffic, vehicle type, and the presence of pedestrians  
85 and bicycles [5]. According to the U.S. Federal Highway Administration (FHWA), holes with  
86 a minimum width of 150 mm and a depth of 2.5 mm, 2.5-5.0 mm, and greater than 5.0 mm are  
87 considered low, moderate, and high-severe potholes, respectively [21, 23]. The ERA-NET  
88 ROAD pothole project has established a depth of at least 30 mm and a diameter of 100 mm up  
89 to 1 m for typical potholes depending on road specific conditions. Potholes with a depth of  
90 more than 40 mm are instead regarded as severe [5] and must be repaired in less than 24 hours  
91 [26]. Based on Norwegian standards, any damage wider than 100 mm for a vehicle lane and  
92 30 mm for a bicycle lane must be repaired within a week [34]. A conducted study by the  
93 Strategic Highway Research Program (SHRP) in the U.S. classifies 0.93 square meters and 150  
94 mm as the maximum surface size and the maximum depth of a pothole [7]. The maximum  
95 recommended depth by UK Haringey Council standards is 50, 60, and 25 mm for major roads,  
96 unclassified roads, and places that may be dangerous for pedestrians or cyclists, respectively  
97 [28]. Also, based on the answers to a questionnaire by approximately 80 local authorities in  
98 2014 in the UK, 67% of respondents considered 25–40 mm, 12% selected 40–50 mm, and 14%  
99 considered a depth of greater than 60 mm as a typical pothole depth [21]. Furthermore, as

follows (Table 1), the Swiss Road Maintenance and Management Association classifies potholes based on the severity of the distress [26].

Table 1. Potholes' classification based on the severity of the distress [26]

Damage condition	Severity	Depth (mm)	Diameter (mm)
Starting to form single potholes	Low	-	< 100
Single potholes	Medium	< 40	100-300
Slightly connected potholes	High	≥ 40	≥ 300

The severity of the potholes is ranked slightly differently by Shahin [36]. According to Table 2, for potholes with an average diameter of up to 762 mm, both the depth and the diameter are considered to classify the pothole severity. If the diameter is higher than 762 mm, the pothole area is determined and divided by 0.47 square meters. If the result is higher than 25.4, the severity is considered high, otherwise medium [36]. If the distance between the potholes is less than 200 mm, they should be measured together and considered one big pothole [3].

Table 1. Classification of potholes based on depth and diameter according to Shahin [36]

Maximum Depth (mm)	Average Diameter (mm)		
	102-203	203-457	457-762
12.7 – 25.4	Low	Low	Medium
25.4 – 50.8	Low	Medium	High
> 50.8	Medium	Medium	High

## 2.2. Maintenance and rehabilitation

Road pavements deteriorate under various vehicle traffic and weather conditions. Thus, they need to be rehabilitated to restore serviceability [37]. This rehabilitation technique generally adopted for potholes is called patching (Fig. 1), which is the process of filling potholes in the road pavement with a suitable material to control further deterioration of the pavement and restore the users' safety and comfort [6].

Pothole patching covers a wide range of methods, from temporary procedures in emergency situations to permanent (or semi-permanent) interventions performed during corrective and routine maintenance operations [38]. It is the most obvious and sensible sign of road maintenance to the public and road users [39]. As stated by O'Flaherty [29], patch operations should be performed in good weather before potholes spread throughout the pavement,

worsening its condition. Nevertheless, before patching, the cause of the failure must be determined [40].

Prompt repair can limit expenditures and prolong the service life of a pavement. However, this maintenance and rehabilitation strategy is costly and time-consuming, especially in the cold and wet winter months. Therefore, potholes need urgent attention by road maintenance authorities to cut down on further pavement deterioration, vehicle damage, and user costs [20].



Figure 1. Patching a pothole with CPM

Despite improvements in mix design and the development of enhanced materials, pavement failures still happen. However, when the distresses are close and occur in relatively isolated locations or on low-traffic roads, the most common maintenance technique used to repair and restore the serviceability is patching [41, 42]. In good patching practices, material quality, repair method, and compaction level are the most important parameters [43, 44]. Nevertheless, the decision to patch is influenced by various factors, such as [38]:

- The temporal frequency of routine maintenance of pavement resurfacing or overlay
- Traffic level
- The hierarchy of the road and the possibility of setting up a temporary construction worksite
- The availability of the equipment, materials, and labor
- Public negative view

Additionally, running time, the climate condition, size of the pothole, properties of the host pavement, and the overall expenditure can affect the patching operations [26].

### 2.2.1. Repair Procedures

Pothole repair operations include several temporary and semi-permanent to permanent approaches, which are as follows [44, 45].

- Temporary repairs

- 149 ○ Throw-and-dump or throw-and-go: The cold mixture is just shoveled into the  
150 pothole without any heavy compaction and removing the water and debris. The  
151 patch is compacted by normal traffic.
- 152 ○ Throw-and-roll: The cold patch is placed into the unprepared pothole and  
153 compacted using a hand tamper and the truck tires.
- 154 ○ Edge seal method: The repair method is similar to throw-and-roll, but after  
155 compaction, the perimeter of the repaired section is covered with a tack coat  
156 and sand. Then, it is left for about one day to dry.
- 157 ○ Spray-injection: The mixture of aggregate and heated asphalt emulsion is  
158 sprayed into a prepared pothole, then the patch is covered with aggregates to  
159 prevent tracking by vehicles.
- 160 ■ Semi-permanent repair: In this partial-depth repair, the edges of the prepared pothole  
161 are vertically cut with a saw and filled with a cold mixture or, in some cases, with HMA.  
162 Then the patch is compacted with a roller.
- 163 ■ Permanent or full-depth repair: This approach is used to repair structural damage and  
164 may involve the rehabilitation of the subbase and base layers.
  - 165 ○ Infrared: The new asphalt is blended with the existing -Infrared Heated-  
166 Pavement material and compacted.
  - 167 ○ Microwave: The hole and its surroundings are pre-heated, and after cleaning  
168 loose debris, the pothole is overfilled with patch material and heated and  
169 compacted.

170  
171 It is recommended that road maintenance agencies should consider permanent repairs as their  
172 first choice and use temporary methods only for emergencies to provide safety quickly [35].  
173 Studies show that although the semi-permanent method provides more durability in repairing  
174 failures, the high cost of equipment, labor, and higher required effort to patch, reduces its  
175 productivity compared to temporary methods like throw-and-roll and edge seal [7]. Spray  
176 injection also requires high equipment costs while, depending on the labor skills, its  
177 productivity is high. Plus, the materials used in spray injection have a lower price. The throw-  
178 and-roll procedure does not require special equipment, but hand tools to fill the hole. This  
179 method can be an alternative to semi-permanent that ensures satisfactory repair using high-  
180 quality materials [38, 46]. A study by Wilson [47] in 1993 stated that spray injection offers  
181 more durable patches than the aforementioned procedures, and in terms of tons/person-day  
182 (Table 3), it is the most productive technique [47, 48]. The results of another study showed that

the productivity of throw-and-roll and spray injection approaches is 4 and 2 times better than the infrared method in terms of tons/day. Moreover, the investigation of winter pothole patching methods by Nazzal et al. [7] showed (Table 3) that by considering the required time for repairing potholes, throw-and-roll, spray-injection, edge seal, and semi-permanent techniques have the highest productivity, respectively. However, the most recent market data shows that there is considerable interest in the convenience of single-use packaged products for throw-and-roll, albeit higher unit prices offset by greater ease of handling and speed of use. The general characteristics of the patching procedures are shown in Table 4.

Table 3. Average productivity values for different repair techniques

Repair technique	Average productivity (tons/hour)	Labor (person)	Average productivity (tons/person-day) [47]	Average required patching time (min) [7]
Spray injection	1.7	2	3.4	2.8
Throw-and-roll	1.6	2	3.2	2.6
Edge seal	1.4	2	2.8	3.2
Semi-permanent	0.3	4	1.2	13.3

Table 4. General features of pothole patching procedures

	Benefits	Drawbacks or limitations	longevity	Ref.
Throw-and-go	<ul style="list-style-type: none"> <li>relatively short time</li> <li>using few workers</li> <li>simple application</li> <li>can be used for temporary patching under adverse conditions</li> </ul>	<ul style="list-style-type: none"> <li>shortest service life</li> </ul>	<ul style="list-style-type: none"> <li>a few days to few weeks</li> </ul>	[7, 33, 49, 50]
Throw-and-roll	<ul style="list-style-type: none"> <li>easy and fast</li> <li>does not require specialized equipment</li> <li>crew is less frequently exposed to traffic</li> <li>can be used for temporary patching under adverse conditions</li> <li>high productivity rate</li> </ul>	<ul style="list-style-type: none"> <li>labor intensive and repairs can easily fail if the repair is not done correctly</li> </ul>	<ul style="list-style-type: none"> <li>3-12 months</li> <li>All-season</li> </ul>	[7, 42, 48, 51]

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

<p style="text-align: center;"><b>Spray Injection</b></p>	<ul style="list-style-type: none"> <li>• fast repair</li> <li>• require fewer people and no compaction</li> <li>• ability to repair potholes in adverse weather</li> <li>• produce a neater and smoother repair</li> <li>• less labor intensive and safe</li> <li>• requires the least expensive materials</li> <li>• does not need to be further compaction</li> </ul>	<ul style="list-style-type: none"> <li>• higher cost of patching for low quantities</li> <li>• requires specialized equipment</li> <li>• need to clean up debris</li> <li>• operator is typically exposed to errant traffic</li> <li>• parked vehicles may become coated with overspray</li> <li>• formation of a cold joint</li> <li>• requires well trained and experienced operators</li> <li>• higher equipment costs</li> </ul>	<ul style="list-style-type: none"> <li>• up to 2 years at summer</li> </ul> <p>≥3 years</p>	<p style="text-align: center;">[7, 24, 52, 53]</p>
<p style="text-align: center;"><b>Edge seal</b></p>	<ul style="list-style-type: none"> <li>• better connection between the asphalt pavement and new materials</li> <li>• keeps water out</li> </ul>	<ul style="list-style-type: none"> <li>• requires a long recovery time between patching and opening the roadway to traffic</li> </ul>	<ul style="list-style-type: none"> <li>• &gt;1 year All-Season</li> </ul>	<p style="text-align: center;">[7]</p>
<p style="text-align: center;"><b>Semi-Permanent</b></p>	<ul style="list-style-type: none"> <li>• more cost-effective</li> <li>• results in the long life</li> <li>• improving the underlying and surrounding support</li> </ul>	<ul style="list-style-type: none"> <li>• requires more workers and equipment</li> <li>• less effective in winter conditions</li> <li>• has higher labor and equipment costs and lower productivity</li> <li>• involves more preparation and compaction and not feasible under adverse conditions</li> <li>• More patch time is required</li> </ul>	<ul style="list-style-type: none"> <li>• up to 2 years All-Season</li> </ul>	<p style="text-align: center;">[7, 33, 37, 44, 54]</p>

Permanent	<ul style="list-style-type: none"> <li>• results in the longest life</li> <li>• improving the underlying and surrounding support</li> </ul>	<ul style="list-style-type: none"> <li>• requires more workers and equipment</li> <li>• not applicable in winter</li> </ul>	<ul style="list-style-type: none"> <li>• 3-6 years</li> <li>• With proper preparation up to 15 years</li> </ul>	[7, 15, 24, 42, 47]
Infrared	<ul style="list-style-type: none"> <li>• less crew time in traffic</li> <li>• eliminating or reducing the amount of new asphalt mix, using waste material</li> <li>• provide higher bonding between patch and old pavement</li> </ul>	<ul style="list-style-type: none"> <li>• requires long patching time; 10-20 min</li> </ul>	<ul style="list-style-type: none"> <li>• <math>\geq 13</math> years for crack filling</li> </ul>	[7, 54-56]
microwave	<ul style="list-style-type: none"> <li>• using RAP and RAS</li> <li>• strong interface bonding</li> </ul>	<ul style="list-style-type: none"> <li>• requires long heating time</li> </ul>		[57, 58]

### 2.2.2. Patching materials

The materials that can be used to repair potholes are numerous. However, they are classified into the following **main** categories [5, 42]:

- Hot-mixed asphalt materials
- Cold-mixed asphalt materials
- Cement-based materials

**Asphalt-based materials (hot and cold)** can be used for both asphalt and concrete pavements, whereas cement-based materials are commonly used for permanent patches on rigid pavements. Additionally, there are other types of repair materials such as synthetic binders, epoxies, polymeric materials, and resins that are not used commonly, especially throughout Europe [5, 42].

Hot-mixed asphalt mixtures are applied hot or cold in the repair operations. The mixture can be produced with well-graded heated aggregates and a hot **asphalt** binder at high temperatures and used **immediately** after being produced. Moreover, they are produced in an HMA plant with heated aggregates and liquid **asphalt-base** binders at a lower temperature than used in the previous procedure. Then, the cold product is stored for later use.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

212 Cold-mixed asphalt mixtures are not heated during their production. The liquid asphalt-base  
213 binder and aggregates are mixed in a plant or on a jobsite and stockpiled or used cold in  
214 pavement treatments. Compared to the HMA mixtures, they have low quality and poor  
215 performance [6, 59]. In general, these kinds of products, also known as CMPMs, are classified  
216 according to the following categories [26, 40]:

- 217     ▪ The cold mix is produced by a local asphalt plant: The available materials are used to  
218         produce the cold mixture without considering the binder-aggregate compatibility test.
- 219     ▪ The cold mix is produced based on the specifications that have been set by the agency:  
220         The binder-aggregate acceptability and acceptance criteria by the maintenance agency  
221         are considered before buying the material.
- 222     ▪ Proprietary cold mix: These materials, which include specially formulated binders, after  
223         passing some acceptance tests, can be produced in bulk and stockpiled or can be kept  
224         in buckets or bags (25-40 kg) to be handled easily on the job site.

225  
226 Hot and cold asphalt-base materials are the most extensively used for all road maintenance  
227 operations. They have a relatively low cost, satisfactory stability, good quality, and easy  
228 application. Hot prepared and applied materials provide a more durable and effective solution  
229 for repairing potholes [26]. According to previous studies, HMA materials, due to their high  
230 initial stability, low permanent deformation, effective bonding to the old pavement, and easy  
231 compactibility, perform better than CMPMs and give the best repair [2, 60]. The New Jersey  
232 Department of Transportation (NJDOT) used three different types of CMPMs and one type of  
233 HMA to repair potholes. The results showed that HMA has far better performance than the  
234 other mixtures [61]. Other studies by Dong et al. [41] and Marasteanu et al. [15] indicated  
235 similar results. The performance of patching materials involving hot mix, cold mix, cold mix  
236 with fibers, and fiber mix heated in a Porta-patcher in filling shallow potholes was evaluated  
237 in a study by Feighan et al. in 1986. Their service lives and repair procedures were analyzed  
238 and compared on roads with poor, fair, and good conditions. The results indicated that hot mix  
239 asphalt has excellent performance in comparison to the other mixes. Plus, CMA was less  
240 effective [42]. Moreover, apart from their less workability in adverse climate, dependency on  
241 equipment, and being less environmentally-friendly, owing to their higher durability, they are  
242 the priority of road maintenance agencies in patching operations [62, 63]. The outcomes of a  
243 survey in 2014 in the UK (Fig. 2) included responses of approximately 80 local authorities to  
244 questionnaires, and showed that 31% of the agencies prefer to use HMA for pothole repair, and  
245 69% of them use both cold and hot materials [25]. In another survey included responses from

49 states in the USA, 20 local agencies in eight U.S. states, and 33 highway agencies at the local and national levels in the UK and Ireland; the results (Fig. 3) indicated that HMA is the most widely used material for permanent patches [42].

Despite the durability of these materials in patching potholes, their limited applicability in adverse weather and their long and specific application procedures draw the attention of maintenance agencies to the use of CMPMs. Generally, CMPMs have lower quality and poorer performance than HMAs in the face of several benefits. They are workable in most weather conditions [64, 65], since in the CMPMs, the workability is not achieved through heat but by using solvents [11]. Also, their longevity is significantly affected by the quality of the materials [25]. The CMPM application is quick and takes less time, resulting in a safer repair operation with less traffic disruption, especially in difficult conditions like high-speed roads and intersections such as roundabouts [30].

Therefore, using a high-quality mixture is very important to ensure durability, but not enough [30]. If the mixture is used in unsuitable conditions, it will not work well, and the service life will be short [26]. The following are three main concerns of CMPMs to achieve maximum performance [66, 67]:

- high air-void content or a modest level of densification
- weak initial strength and stability
- long curing time to attain their max performance.
- 

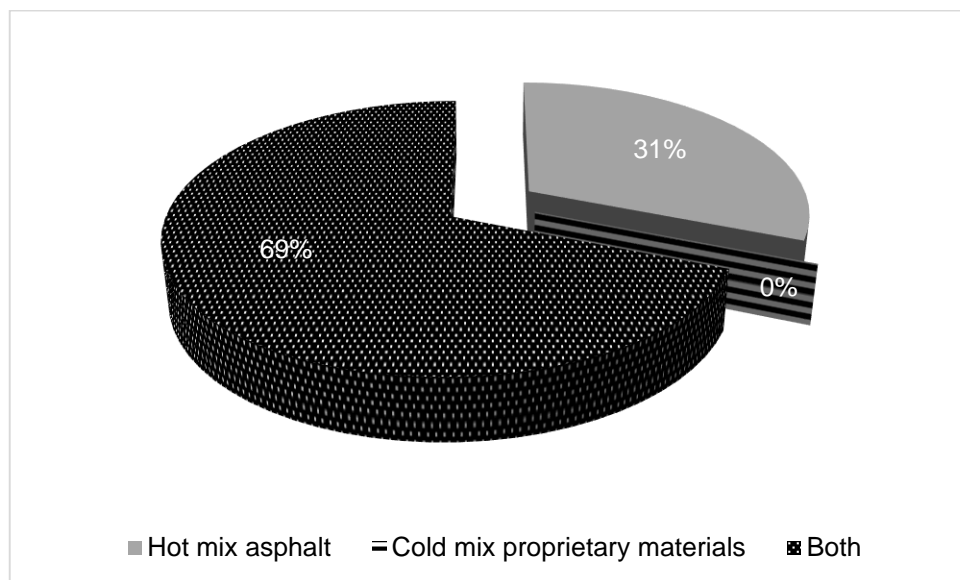


Figure 2. Material used for patch repair based on responses of local authorities [25]

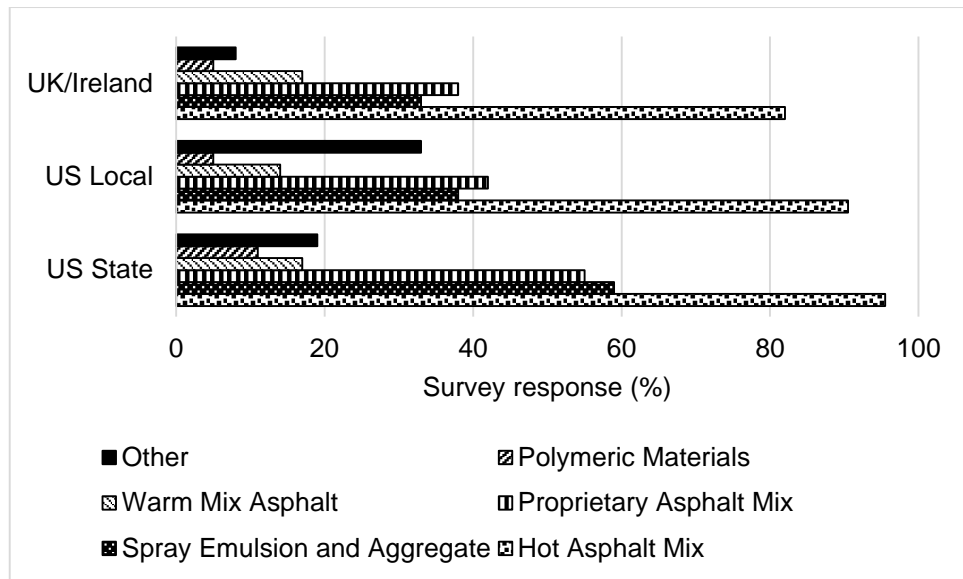


Figure 3. Materials used to repair potholes according to responses of agencies [42]

### 2.2.3. Durability of the repaired potholes

The patch durability usually depends on repair conditions (high or low weather temperature), the quality of the patching material, and the patching method [41]. Therefore, if the patching procedure is done satisfactorily under warm or fair-weather conditions, the repair method can be very efficient and durable [7]. The patching operation in cold winter compared to spring leads to a shorter life, usually a few days to a few months [26]. In fact, the purpose of repairing potholes in winter is only to provide traffic safety by restoring rideability, not a permanent repair. Nevertheless, repaired patches in the spring are expected to last as long as the surrounding pavement [38]. The durability and survival period of winter and summer repaired potholes were assessed through a laboratory study and a questionnaire in six provinces (Alberta, Manitoba, Ontario, Quebec, Saskatchewan, and New Brunswick) in Canada. The results (Table 5) declared that winter patched potholes survive for no more than 12 months. This value for summer patched potholes was more than one year [32, 53].

Table 5. Survival period of repaired patch in six provinces in Canada (months) [32]

Province	Alberta	Manitoba	Ontario	Quebec	Saskatchewan	New Brunswick
Winter	<3	9-12	3-6	6-9	3-6	<3
Summer	>24	>24	12-18	12-18	18-24	>24

Durable patches are not obtained only by applying HMA. The use of high-quality CMPMs also leads to a long patch life. Proprietary cold mixes with a one-year survival period can be considered suitable patches for repairing potholes [41]. The results of the repaired potholes

289 with high-quality CPAMs in China were desirable, but the mixture with high-quality material  
290 was 3-5 times overpriced than HMA [18]. Nevertheless, past experiences show that high-  
291 quality materials give a longer service life even if they cost more. In fact, high-quality materials  
292 offset the cost of frequent repairs that are conducted with poor-quality materials [10].

293 Despite the material and application conditions, the patching methods involving temporary,  
294 semi-permanent, and permanent methods also have an important role in patch longevity. The  
295 expected life of a temporary repaired patch is up to one year. However, if a high-quality  
296 material is used, it can last up to 18 months [28]. The NCHRP report has limited this period to  
297 3 to 6 months [42]. If the patching mixture can be compacted to an equal density as the existing  
298 pavement, the life span will be extended [68].

299 Repaired potholes with throw-and-go have the worst durability and last a few hours to a few  
300 weeks [49, 50]. Owing to the short life, frequent re-patch, and high cost, this repair method is  
301 generally not recommended [42]. The durability of repaired potholes by the throw-and-roll  
302 method is higher than by throw-and-go. If the patching operation is properly done using this  
303 method, it can last up to 12 months for the spring season and 6 months for the winter season  
304 [28, 33]. In the aforementioned study in six Canadian provinces, potholes filled by the throw-  
305 and-roll method in winter did not last more than 3 months. But summer patched potholes had  
306 a lifespan of more than 2 years [32]. In a 14-month field survey in Tennessee, winter-repaired  
307 potholes with the throw-and-roll method showed a shorter life span and failed just after several  
308 weeks [69]. In general, the throw-and-roll method can be a proper substitute for a semi-  
309 permanent repair method if the durability of the product exceeds more than 9 months [32].  
310 Patching by the edge seal method is relatively durable in all seasons and lasts more than one  
311 year. The spray injection method, if it is applied correctly, can act as a permanent patch and  
312 last up to two years, but shows poor performance if exposed to stable wet conditions [28, 42].  
313 In the semi-permanent repairing method, the expected patch life is up to 2 years [33]. The  
314 permanent patching method is the most durable repair method that lasts 3 to 6 years. If a  
315 permanent technique with HMA is applied correctly in a properly prepared pothole, the lifespan  
316 can also last 15 years or more [15, 24, 44].

317 Overall, previous studies categorize the durability of the patching materials as follows [45, 70]:

- 318 - Short-lasting patches: patches with less than one year of longevity.
- 319 - Medium-lasting patches: patches with a 1-3 year lifespan.
- 320 - Long-lasting patches: patches with more than 3 years of survival life.

321 However, the patch longevity **is still** considered to **be** days or months instead of years [71]. In  
 322 fact, owing to one or a combination of the already mentioned factors, the patch fails in a short  
 323 time. Table 6 gives the most important reasons **for** patch failure in more detail [9].

324 Table 6. Failure symptoms and mechanisms of cold patching materials [9]

Symptom	Failure reasons
<b>In stockpile</b>	
<b>Poor workability</b>	High viscosity binder; dirty aggregates or excessive dust; too fine or too coarse gradation
<b>Binder draindown</b>	Low viscosity binder; stored or mixed at high temperatures
<b>Stripping</b>	Aggregates poor coating during mixing; wet or cold aggregate
<b>Lumpy mixture, premature hardening</b>	Higher rate of volatilization and premature curing
<b>Stiffness in low temperature</b>	Binder higher temperature susceptibility, dirty aggregates or excessive dust; too fine or too coarse gradation
<b>During placement</b>	
<b>Poor workability</b>	High viscosity binder; dirty aggregates or excessive dust; too fine or too coarse gradation
<b>Poor stability</b>	High binder content, low viscosity binder, poor aggregate interlock, inadequate voids in aggregate
<b>Hard to compact</b>	Low viscosity binder, higher or lower amount of binder, improper gradation, excessive fine, the shape of the aggregates
<b>In-service</b>	
<b>Shoving, pushing</b>	Poor compaction, low viscosity binder or high amount of binder; Binder moisture and temperature susceptibility; contaminated mixture; long volatilization process; inadequate voids in aggregate; poor aggregate interlock
<b>Rutting</b>	Poor compaction
<b>Raveling</b>	Poor compaction; low viscosity binder; poor mixture cohesion; poor aggregate interlock; aggregate binder absorption; moisture susceptibility; dirty aggregates or excessive dust; too fine or too coarse gradation
<b>Freeze-Thaw deterioration</b>	Poor mixture cohesion; too pervious mixture, moisture susceptibility
<b>Poor skid resistance</b>	Higher binder content; rounded aggregate; too dense gradation
<b>Shrinkage or debonding</b>	Poor pothole preparation; mixture poor stickiness

325  
 326 Most of the symptoms and problems listed in the table, such as binder content, poor-graded  
 327 aggregates, and improper repair by the non-specialist crew, were also discussed by Kandhal  
 328 and Mellott [72]. However, depending on different circumstances, the impact of these factors  
 329 on patch failure can be different. The response of approximately 80 local authorities across the  
 330 UK to a questionnaire about the main causes of patch failure showed (Fig. 4) that water  
 331 infiltration and poor-quality mixtures have the highest and lowest impact on patch failure,  
 332 respectively [25].

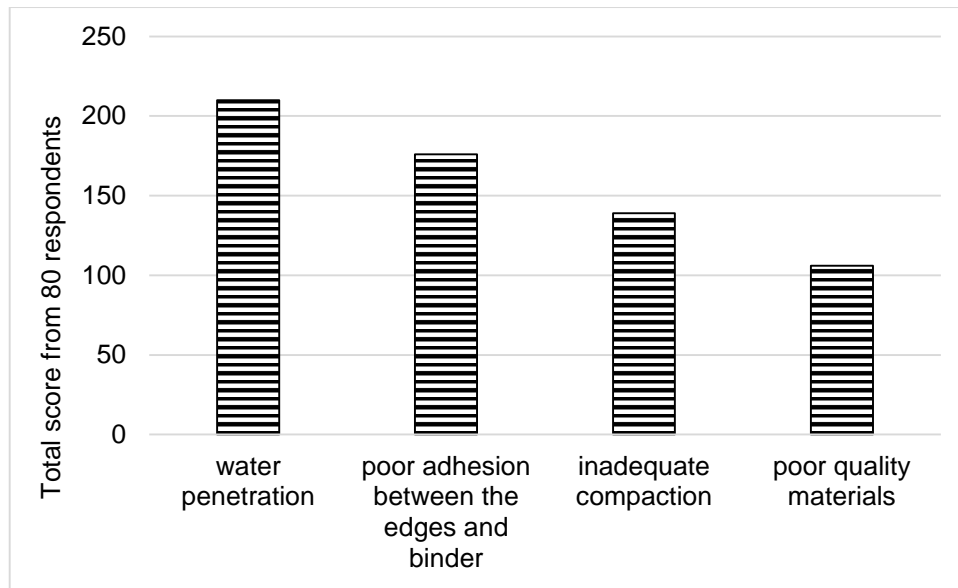


Figure 4. The main factor in failing of potholes in UK (least likely reason=1, most likely reason=4; the score is the sum of all weighted rank counts) [25]


### 2.3. Cost analysis

Since patching practice is an extensive and large-scale repair activity, road agencies have to spend millions of dollars annually [6, 71]. Pothole patching major costs involve materials, labor, and equipment. However, lane closure and user-delay costs, vehicle damage costs, and insurance costs are also involved with pothole maintenance expenditure and cannot be ignored [2].

According to a study in 2010, the cost of accidents and vehicle damage exactly due to potholes over a rainy season in the UK was more than £10 billion (\$13.8 billion), which is four times more than the total yearly road budget of South Africa [40]. In another research, the Local Government Association (LGA) estimated the money needed to repair damaged cars due to potholes in the UK was £1 billion (\$1.38 billion) in 2014. Besides, the results of conducted research by the international research data and analytics group (YouGov) showed that businesses in England and Wales face an annual incremental loss of £5 billion (\$6.9 billion) due to poor road conditions, which is higher than the road maintenance budget [25]. Therefore, the repair lifespan in determining the benefit-cost ratio (BCR) is essential, and durable patches, especially patches with more than one year of survival life, can significantly reduce the overall costs as they do not need to be patched frequently [62]. Previous studies indicate that by preventing the replacement of unsuccessful patches, cost-effectiveness improves tremendously [42]. Therefore, preventative maintenance programs have an important impact on the longevity of the patches and, in the long term, can be less expensive than routine patch operations [28].

357 According to a study by ALARM in 2012 [30], a preventive maintenance plan can be at least  
 358 20 times cheaper than reactive maintenance. However, due to a lack of budget, planned  
 359 maintenance operations are usually less considered. Based on responses of approximately 80  
 360 local authorities to a questionnaire across the United Kingdom, 25% of the yearly budget  
 361 allocated for pothole repair is spent on “planned maintenance”, 59% on “reactive maintenance”  
 362 and the remaining 16% is spent on routine operations [25].


363 Usually, in repair operations, the highest cost is devoted to crew and equipment. Through  
 364 research in 2013, Dong et al. [69] claimed in patching practices, 50 to 60% of total patching  
 365 costs account for workforce charges. Plus, the equipment accounts for a significant portion of  
 366 the total cost. However, the devoted costs in temporary approaches with CMA are a bit  
 367 different. The materials and equipment costs can be notable based on the employed method for  
 368 repairing potholes, as Lukas Hammel showed in his research (Fig. 5) [73]. As a result, skilled  
 369 labor and standard equipment with patching materials can reduce or increase the patching costs  
 370 [60].

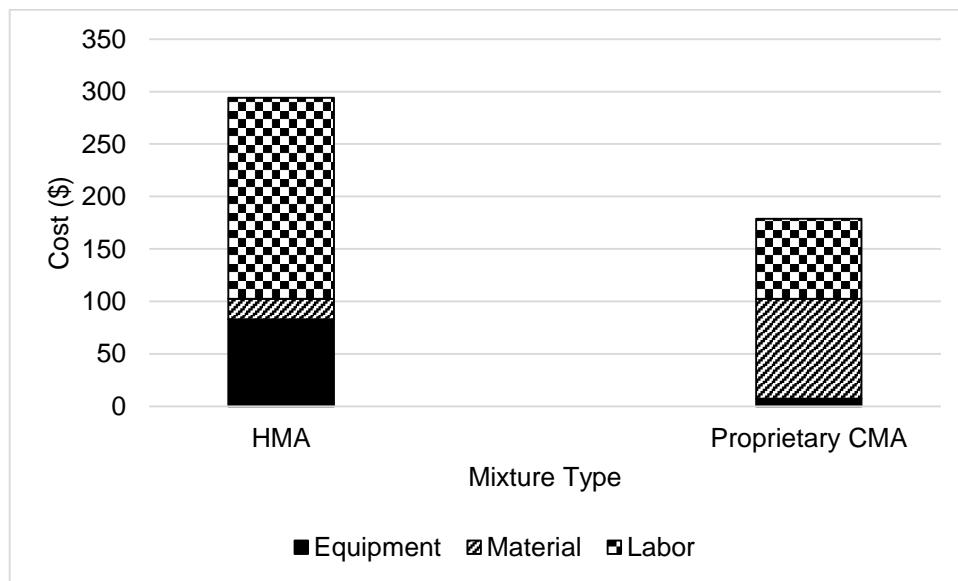

372  
 373 Figure 5. The comparison between devoted costs in 2015 for HMA and a proprietary CMA. (The  
 374 original cumulative costs were expressed in Euros) [73]

375 In most cases, the cost of materials is just a small portion of the total patching costs [37, 41].  
 376 Studies have shown that this value is 15 to 25 percent of the total operation costs [74]. If the  
 377 repair process is done properly, it also accounts for less than 10-20 percent of the total cost  
 378 [49]. According to studies, CMPMs contribute 20% of the overall repair cost, while this value  
 379 for hot mix asphalt is 2-5% [60]. Despite the low cost, the materials have a significant impact  
 380 on the patch and the total cost. Usually, CMPMs with poor performance lead to increased labor,

381 equipment, traffic control, and user delay costs. Therefore, utilizing high-quality materials is  
 382 recommended to increase longevity, prevent re-patching operations, and reduce overall costs  
 383 [47, 49, 51]. In fact, the cost of high-quality materials and a proper repair method is  
 384 significantly less than the cost of frequent patching operations [9]. Through research in 1988,  
 385 Anderson et al. [9, 74] calculated the annualized expenditure per repair for various patching  
 386 materials costing from \$30/ton to \$120/ton (Fig. 6). By considering the critical condition, if the  
 387 most expensive mixture (\$120/ton) lasts until the second year, the cost required to repair the  
 388 damage will be less than the cost needed to patch the pothole with cheap material (\$30/ton)  
 389 after just one year. Therefore, using expensive materials with high longevity leads to a notable  
 390 cost saving in the long run [49].

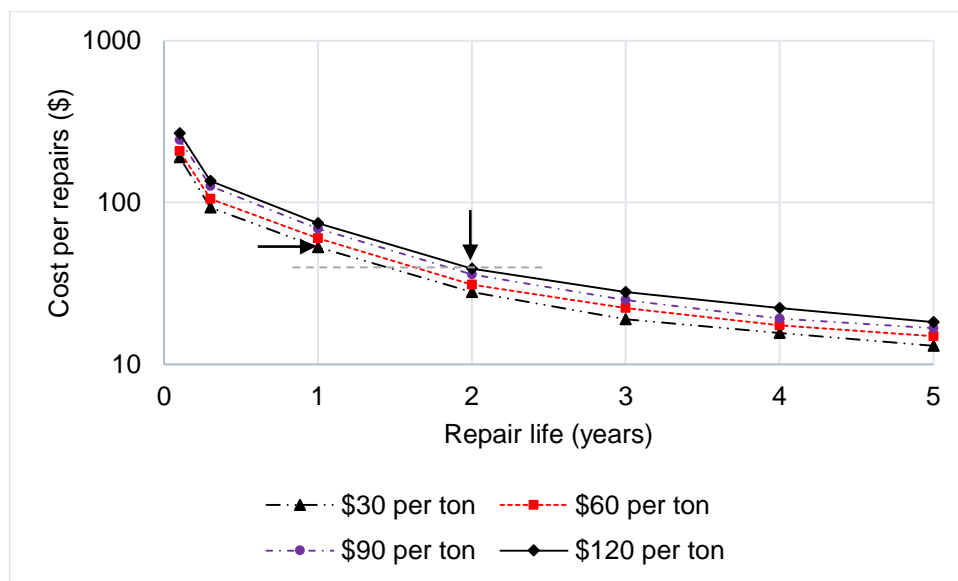

391  
392 Figure 6. Equivalent uniform annualized cost in 1998 for standard repair procedure [74]

393 However, the results of a research project at the University of Minnesota showed that for short-  
 394 term purposes, cheaper materials and temporary methods are more cost-effective, and long-  
 395 lasting patching methods offer high effectiveness in the long term. Additionally, if user costs  
 396 are taken into account in the analysis, the benefits are even greater [15].

397 It is noticeable that high-quality materials alone cannot guarantee the durability of the patch. If  
 398 used in poor condition with inappropriate technique, it will not perform well and not last long  
 399 enough. As stated in a two-year European study called POTHOLE, unprepared pothole practice  
 400 with cold mixtures costs the most compared to other patching repair strategies. Among the  
 401 repair methods, a standard procedure including cutting, cleaning, filling, and compacting the  
 402 patch is the most cost-effective repair method [15]. The throw-and-go method, as a common  
 403 repair method without any hole preparation, is not considered a cost-effective method

1 404 compared to other strategies. According to Thomas and Anderson's study [49], this patching  
2 405 procedure is roughly three times more expensive than a standard patching method.

3 406 Following the results of a questionnaire survey in 2011, in Tennessee, the semi-permanent  
4 407 method is the most cost-effective technique in the long run, despite the increased cost of labor,  
5 408 equipment, and operation time. Plus, the throw-and-roll treatment method used in spring is  
6 409 cost-effective, while the winter season's throw-and-roll procedure is the least cost-effective.  
7 410 The semi-permanent technique is considered to be more cost-effective than throw-and-roll  
8 411 [33]. The most extensive pothole repair research project (H-106) by the SHRP found that for  
9 412 similar patching materials, the throw-and-roll repair method is as effective as the semi-  
10 413 permanent method. However, when the effective cost is considered based on the patch service  
11 414 and analysis period, the throw-and-roll method would be more cost-effective than the semi-  
12 415 permanent one due to reduced labor and equipment [47]. Under optimal conditions, the labor  
13 416 cost for patching and traffic control can be considered as two and four workers for the throw-  
14 417 and-roll and permanent methods, respectively [37]. Confirming other similar studies, pothole  
15 418 repair using a semi-permanent method costs almost 2.5 times more than the throw-and-roll  
16 419 method [32]. These cost differences between throw-and-roll and semi-permanent methods have  
17 420 been shown in another study by Dong et al. [69] for Tennessee DOT. According to the results,  
18 421 repairing potholes with the various cold mixtures by the throw-and-roll technique requires  
19 422 much less cost for equipment and labor (Fig. 7).

20 423 In another study, Nazzal et al. [7] assessed the performance and lifecycle cost of infrared  
21 424 patching operations and compared them with spray injection and throw-and-roll repair  
22 425 methods. The comparison revealed that if the user costs are overlooked, for short-term repairs  
23 426 (less than 12 months), the throw-and-roll method will be more cost-effective than the infrared  
24 427 method. However, in the long run, especially for winter repairs, the infrared method is more  
25 428 cost-effective than the other methods.

26 429

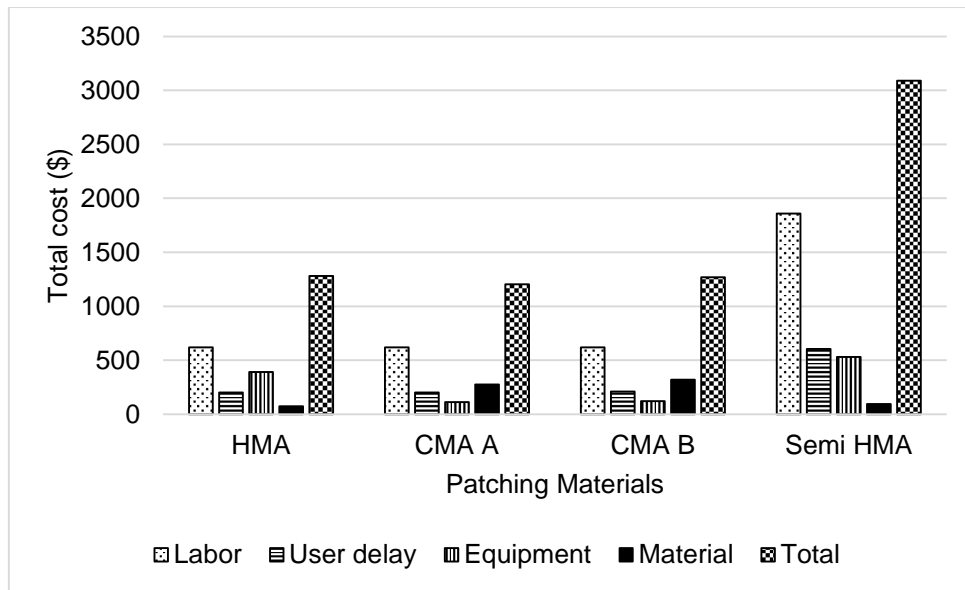


Figure 7. Total patching cost differences between cold mix and hot mix asphalt in 2014 [69]

Wei and Tighe [75] evaluated the durability and cost-effectiveness of repaired potholes through different methods (Table 7). They found that the spray injection patching method is less cost-effective. Although, unlike the hot mix patching procedure that requires purging the leftover unused materials from the vehicle after the end of repair operations, it is possible to store the mixture on the patch spray machine for fast and efficient deployment in small- or large-scale repair practices [76]. Finally, based on the literature, it is noteworthy that cost-effectiveness appears in increased productivity and higher service levels, not essentially in money-saving for the agency [77].

Table 7. Longevity and cost of different patching methods in 2004 [75]

Patch Technique	Life span (years)	Cost (Canadian \$/lane/km)
Spray injection patching	2	3,375
Machine HMA patching	4	1,386
Manual HMA patching	5	1,246
Mill and patch 10%	6	2,450
Mill and patch 20%	7	4,900

### 3. Cold Mix Patching Materials (CMPMs)

CMPMs are usually applied in an emergency situation as a temporary treatment until proper and definite practice is done [20, 78]. These kinds of asphalt-based products are composed of a mix of aggregates with special binders (asphalt emulsion, cutback, proprietary binders), and additives [79]. However, in recent years, the use of waste materials such as Reclaimed Asphalt

447 Pavement (RAP) and Reclaimed Asphalt Shingles (RAS) to modify the binder or as a substitute  
448 for aggregate or mineral filler has received growing interest and attention in the mix design of  
449 CMPMs [80, 81]. Despite the benefits of cold mixtures in maintenance programs, they have  
450 some weaknesses reflected in their poor performance or premature failures. Poor workability  
451 in cold weather, poor stability, especially in deep holes, and moisture susceptibility are primary  
452 problems associated with these mixtures [20, 82]. Besides, since they cannot be compacted at  
453 the same level as the hot mixtures [70, 82], they show high air-void content and porosity of the  
454 mixture (up to 30%) and porosity, which, along with an extended curing time negatively affect  
455 their mechanical properties [67]. Although there are no standards or comprehensive guidelines  
456 for using and evaluating CMPMs [83, 84], a few tests have been recommended by the SHRP  
457 manual as compatibility and acceptance tests to meet the minimum requirements for utilizing  
458 these materials. Compatibility tests involve coating, stripping, and drainage tests, whereas the  
459 acceptance ones include workability and cohesion experiments [62, 78]. It is noticeable that  
460 the mentioned tests do not necessarily guarantee the success of patching mixtures but are  
461 employed to identify materials that may have poor performance in the field [38].

### 3.1. Components

463 The literature has shown the importance and impact of cold mix components on the  
464 performance of repaired patches. The influence of these constituents and how they affect the  
465 mixture are described below.

#### 3.1.1. Binder

468 Cutback, asphalt emulsion, and proprietary binders are used in the cold mix design to meet the  
469 CMPM requirements [67]. Workability and stability, which are two major issues for CMPMs,  
470 can be managed by improving the mix design, both in the type and dosage of ingredients. A  
471 soft binder with low viscosity is needed in the mixture to provide satisfactory workability for  
472 longer storage time and cold weather. However, for better cohesion and stability after  
473 placement of the mixture, high binder viscosity is preferable [78]. Therefore, binder viscosity  
474 should be comparatively low at low temperatures to give desirable workability [85]. Cold  
475 patches containing cutback binders are less sensitive to temperature and can be applied in cold  
476 and rainy weather conditions. Traditional cutback asphalt solvents like gasoline or diesel  
477 decrease the binder viscosity and make the mixture workable with a rather low initial strength.  
478 However, the strength of the patched material increases gradually by solvent evaporation [14,  
479 34]. Despite their advantages, applying cutback-based materials at low temperatures can be

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

difficult and usually **requires** warming-up with the sun before the treatment [40]. The volatilization of the solvents takes up to several months, as well, so that the repaired spots may be damaged during this period [86, 87]. Additionally, cutback-based mixtures emit higher hydrocarbons than an emulsion-based mixture, pollute the atmosphere by contributing to the greenhouse effect, consume non-renewable energy resources, and are flammable, which puts the health of the workforce in danger [63, 88, 89].

**Thus**, the use of current cutbacks has been restricted or even prevented by new European environmental regulations, and using environmentally-friendly alternative solvents is currently emphasized [90]. Compared to cutback, **asphalt** emulsion has relatively fewer environmental issues [37]. However, the relatively short breaking time is the main limitation that propels producers to use slow-setting emulsions in cold asphalt mixtures [13, 26].

**In parallel, environmentally-friendly alternatives to petroleum solvents and proprietary binders are under consideration by producers and researchers** [63]. In a **recent** study by **Wang et al. [91]**, mineral spirit and isoamyl acetate were used as alternative solvents in the cold mixture mix design. The new solvents showed better solubility and higher vaporization rates. Compared to diesel mixtures, using new solvents provided better curing and initial strength, stickiness, rutting resistance, and resistance to water susceptibility, as well. In another study, **Dong et al. [63]** used turpentine as **an** alternative to diesel in cutback **binder**. Although the solubility of solvents was similar, turpentine showed a higher evaporation rate than diesel. Plus, using turpentine in the mixture gave higher initial strength, lower abrasion, and moisture sensitivity. Similar improved performances were achieved by modified cutback with Waterborne Epoxy Resin (WER) in research conducted by **Zhang et al. [92]**. However, the test **results** demonstrated that inappropriate addition of WER may result in poor storability and low-temperature performance. The authors recommended 1.2–1.8 wt% WER as the optimal dosage to improve the cold mix performance. Vegetable oils such as sunflower are also used instead of petroleum solvents to decrease the binder viscosity **at** cold temperatures and make the cold mixture workable. The hardening process of **these** proprietary **binders** occurs by oxidative polymerization in the presence of a catalyst, not by evaporation of the flux oil [88, 90, 93]. **Geng et al. [18]** used Cooking Waste Oil (CWO) as part of **the** diluent in the cold mixture. The research team found that 15% to 35 wt% CWO in a cold mixture containing 21% to 23% diluent yields better adhesion and satisfactory workability. But, the effect of CWO on the strength of the cold mixture was not noticeable.

Besides, there are special CMPMs on the market that their curing and strength evolution occur with water presence through chemical activity, not by evaporation of the solvents. In these

514 water-based cold patches, the strength evolution is faster than in traditional CMPMs, and the  
515 strength development process starts by adding water or even air humidity. Therefore, they must  
516 be kept in totally sealed containers during the storage time and used up to a temperature of 0  
517 °C [73, 86]. Although they provide better patch performance, they are expensive and are not  
518 suitable for large-scale repair operations [17]. The author's laboratory experience with one of  
519 the most popular water-reactive CMPMs on the market indicated that the curing rate of the  
520 material decreases sharply after a few hours of compaction at room temperature, and the  
521 material reaches most of its stability during this time. Plus, the remaining material in the sealed  
522 bucket did not show high sensitivity to humidity and retained its quality even after a few days  
523 of opening the bucket. Eventually, for all CMPMs that foresee an evolution or reaction of the  
524 binder, the packaging and the relative workability of materials are fundamental and decree the  
525 success or failure of treatment. The inefficiency of CMPMs' workability, which is very  
526 frequent following their storage on pallets or shelves, leads to lower demand for materials and  
527 is a severe discrimination factor in commercial competition.

528 **Regardless of the type of binder**, to improve cohesion and adhesion and subsequently the  
529 durability of the patch, a high amount of residual binder is required to achieve a thicker film  
530 on the aggregates; however, binder drain-down during the stockpile should be considered as  
531 well [72]. **The** higher content of the binder leads to bleeding, lower skid resistance, rutting, and  
532 drain-down in the stockpile, **but it** provides a sticky mixture, especially in the winter months.  
533 Nevertheless, an inadequate amount of binder can result in moisture susceptibility, poor  
534 cohesion and adhesion, and subsequently unstable patches, but better workability in cold  
535 **temperatures** [78, 94]. Previous studies indicated that to meet the CMPM requirements, at least  
536 4.5 percent residual binder is needed for aggregates with less than one percent water absorption.  
537 This value changes with the percentage of water absorption, as if the water absorption increased  
538 by 0.5%, the amount of the residual binder should increase by 0.5% as well [72].

### 539 540 3.1.2. Aggregate (**type and grain size distribution**)

541 Aggregates like binders play a crucial role in the performance of cold mixtures. In the CMPM  
542 mix design, various types of virgin and recycled aggregates, such as crushed stone, silty sands,  
543 RAP [95], RAS [80, 81], slag, **and fly ash are** utilized to mix with the binding materials and  
544 form the mixture [11].

545 The most significant required features of aggregates are shape and gradation. Gradation and  
546 aggregate shape significantly impact the workability and stability of the cold patching mixtures  
547 [9]. To achieve better stability, a high degree of aggregate angularity in the mix design is

1 548 required, **even though** angular aggregates do not provide good workability. If one-sized fine-  
2 549 aggregates are predominant in the mixture, the impact of angularity on the workability may be  
3  
4 550 decreased [72]. Although using certain aggregates such as uncrushed gravel, sand, and rounded  
5 551 aggregates can improve the mixture workability, it leads to pavement failure, including rutting  
6  
7 552 and shoving under traffic loads [20, 78]. Despite the shape of the aggregates, their sensitivity  
8  
9 553 to moisture can also result in other problems. Aggregates with higher water absorption cause  
10  
11 554 stripping and drain-down problems during the stockpile and should not be used in the mixture  
12  
13 555 [72]. Therefore, aggregate water absorption should be considered and limited to almost one  
14  
15 556 percent [20, 62]. A maximum of 2% **is fixed** by **the** Ontario Provincial Standard Specification  
16 557 (OPSS) [96].

18 558 Dense-graded and open-graded gradations **are usually** used in cold mixtures to provide  
19  
20 559 satisfactory performance in repaired potholes. Each gradation has its own benefits and  
21  
22 560 drawbacks [34]. A well or dense-graded gradation provides a low air-void and relatively  
23  
24 561 impermeable mixture that yields a stable and durable patch. On the other hand, open-graded  
25  
26 562 gradation gives better workability than dense-graded gradation. Due to their high porosity, they  
27  
28 563 can facilitate volatilization and curing time and are more workable at freezing temperatures.  
29  
30 564 **However**, cold mixtures with a dense gradation have good performance at warm and hot  
31  
32 565 temperatures. Overall, from one region to another, the aggregate proportions can be slightly  
33  
34 566 varied [20, 78] Despite the gradation type, the size of the aggregate in the mix design is  
35  
36 567 important and depends on the depth of the pothole to be repaired [5]. Cold mixtures with fine  
37  
38 568 aggregates are more suitable for filling cracks and repairing shallow potholes as they can be  
39  
40 569 applied thin and prevent raveling on the edges of the hole [28, 41, 62]. However, if the  
41  
42 570 aggregate size is too small compared to the pothole depth, the possibility of displacement or  
43  
44 571 rutting in the patch is high [42]. On the other hand, coarse aggregates are more suitable for  
45  
46 572 filling deep potholes as they result in extra stability and durability [28, 62]. Nevertheless, too  
47  
48 573 large aggregates may lead to insufficient compaction, poor bonding at the pothole edges [42],  
49  
50 574 increased abrasion, and fast deterioration [51]. In the past, the use of 12.5-19 mm coarse  
51  
52 575 aggregates in stockpiled mixtures **had** been promoted to achieve higher durability and stability.  
53  
54 576 Yet, to succeed in applying such a mixture, an ideal patching procedure **involving** saw cuts to  
55  
56 577 create a vertical and clean edge, using a tack coat, and sufficient compaction is needed. While  
57  
58 578 filling potholes is a time-consuming operation and employing an ideal patching method is not  
59  
60 579 usually used, patches with coarse aggregates due to raveling under traffic loads start to  
61  
62 580 premature failure. Otherwise, if fine aggregate mixtures are used that have more flexibility than  
63  
64 581 a coarse aggregate mixture, the patch should be stable at a depth of less than 76 mm [72].

1 582 Mixtures containing finer gradations usually do not provide good workability. However, if they  
2 583 are made mainly of one-sized aggregate mostly kept on the 1.18 mm sieve, the curing and the  
3  
4 584 workability features can be improved. A fine gradation cold mixture consisting of 100%  
5 585 passing 9.5 mm or 4.75 mm sieve can produce a workable and pliable mixture which is  
6  
7 586 characterized by improved durability and flexibility over time [62]. Besides, the use of fine  
8  
9 587 aggregates (maximum particle size of 11 mm) allows cold materials to be applied in thin layers  
10  
11 588 within 25 mm [13, 26]. To achieve maximum workability and stability, the FHWA  
12  
13 589 recommended crushed angular aggregates in sizes ranging from 2.38 mm to 12.7 mm as the  
14  
15 590 optimal aggregate size [9]. Other studies suggest a range of 4 to 10 mm of aggregate as the  
16  
17 591 maximum nominal size of aggregates used in CMPMs [43]. Kandhal and Mellott proposed the  
18  
19 592 gradation reported in Table 8 through their study in 1981 on asphalt stockpile patching mixtures  
20  
21 593 [72]. In another study by FHWA, the recommended gradation for homemade cold patching  
22  
23 594 mixtures is according to Table 8 [78].

24 595 Moreover, dust content affects the repaired patch performance as dirty aggregates may increase  
25  
26 596 moisture damage [78]. In fact, an excessive amount of filler (particles passing through the 0.075  
27  
28 597 mm sieve) makes the mixture brittle, less workable, and less tacky. For this reason, cold patch  
29  
30 598 producers use clean aggregates with low content (usually less than 1%) of dust to improve the  
31  
32 599 cohesive and adhesive characteristics of the patching material. Kandhal and Mellott  
33  
34 600 recommended a maximum dust content of 2% in their research on CMPMs [72]. In the  
35  
36 601 investigation of the 17 proprietary cold mixtures, Franklin and Prowell [1] moderately modified  
37  
38 602 the gradation proposed by Kandhal and Mellott and increased the content of coarse aggregates  
39  
40 603 to improve the stability. The fine particles were increased by up to 3% (Table 8). Also,  
41  
42 604 Minnesota DOT limited the max fine up to 3 percent, and proposed gradation has been  
43  
44 605 indicated in the same table [50].

45 606 A maximum of 1 to 2% of dust has been proposed in a study by Anderson et al. in 1986 [9] to  
46  
47 607 obtain sufficient mixture workability. However, Berlin and Hunt [20] have set higher values  
48  
49 608 for dust content in their study. After 6 months of laboratory evaluation and field survey of  
50  
51 609 several CMPMs, they suggested a value of less than 5 percent for dust particles in the mixture.  
52  
53 610 A similar value (less than 5%) for dust content was also suggested in other studies [15, 62].

614

Table 8. Recommended aggregate gradations for CPAMs

Sieve size (mm)	Percent passing				
	[78]	[1]	[50]	(Specified) [72]	(preferred) [72]
12.5	---	---	100	---	---
9.5	95-100	95-100	95-100	100	100
4.75	40-85	75-95	35-50	40-100	85-100
2.36	15-40	10-40	Max 20	15-40	10-40
1.18	6-25	---	---	---	0-10
0.6	---	---	Max 10	---	---
0.075	1-6	0-3	Max 3	0-2	0-2

615

### 616 3.2. Curing

617 Climate temperature, curing time and curing rate have a remarkable impact on the performance  
618 of the CMPMs. **Biswas et al. [53]** came to this result during their research on cold mixtures in  
619 Canada. The rapid curing rate provides good stability and cohesion, while the slow rate enables  
620 workability. This curing rate is affected by several factors, such as climate conditions (windy,  
621 rainy, temperature, etc.), binder quantity, binder type, binder grade, etc. Therefore, based on  
622 the mixture properties, the curing rate should be considered and controlled, since the **volatile**  
623 evaporation rate of mixtures is different, and prematurely curing leads to unworkability.  
624 Moreover, a longer curing time or higher temperature provides better stability than a shorter  
625 curing time at a lower temperature [78]. The results of research by **Thanaya et al. [66]** indicated  
626 that under full curing conditions, CMPMs and HMA of the same penetration grade binder have  
627 similar stiffness. But, the full curing process is time-consuming. Studies by Chevron Research  
628 Company [90] showed that, depending on weather conditions, it takes 2 to 24 months for the  
629 cold mix asphalt to be fully cured. Usually, materials that are compacted under lower  
630 temperatures or short curing times result in unstable specimens [20]. Moreover, there are  
631 CMPMs on the market that do not reach sufficient stability even after 5 or 6 months. For these  
632 materials, the stability of the **laboratory-made** specimens is low even after high compaction,  
633 and their demolding without long-term curing is almost impossible since they collapse instantly  
634 after demolding. Still, these low-quality materials are bought and utilized by the road agencies  
635 due to their lower price. Therefore, to evaluate the CMPMs, the samples are cured in the oven  
636 to provide sufficient stability for **conducting tests** [97]. **However**, this procedure reflects the  
637 patch condition after several months in service [13], while the patch durability may be shorter

638 than a few months, and the patch deteriorates in a short time after patching. Consequently,  
639 evaluation of the mixture after long-term curing cannot indicate its performance after patch  
640 operation.

641

### 642 **3.3. Performance evaluation**

643 As before mentioned, patch failures are often due to the lack of desirable characteristics. **Thus,**  
644 the evaluation of the mixture properties can help to understand which types of materials  
645 deteriorate in a short time and are not suitable for use in the field. **Workability, water**  
646 **susceptibility and stripping, stability and strength, adhesion and cohesion (bonding**  
647 **characteristics) and storageability are the main factors that can result in poor or good CPM**  
648 **performance.** These properties are engaged **with** each other and the durability of the mixture is  
649 achieved under their overall performance [98, 99]. Since there are abundant materials on the  
650 market claiming to have the best performance, the only way to assess their properties is through  
651 **laboratory** experiments along with a long-term field study [20]. The field performance is  
652 usually carried out through visual evaluations by maintenance engineers. However, the  
653 **laboratory** tests are more quantitative, as explained in the following sections.

654

#### 655 **3.3.1. Workability**

656 Workability is one of the primary properties of cold mixture that **enables** the patching material  
657 to be handled, easily plied, and compacted during the stockpile and placement in the field [78,  
658 100]. Since CPMs are commonly used for temporary repairs, their workability characteristics  
659 are more noteworthy than their **performance** [101]. As claimed by previous studies, the  
660 workability of cold mix can be affected by its main components, including asphalt binder and  
661 aggregates. In fact, using rounded aggregates or uncrushed gravel in the mix design can  
662 improve the mixture workability. An excess amount of filler or mixtures with a maximum  
663 aggregate size bigger than 12.7 mm also negatively affect the mixture workability.  
664 Furthermore, weather temperature during the storage or application time can impact the binder  
665 viscosity and the mixture workability [6, 39, 78]. Usually, a mixture with poor workability  
666 leads to insufficient compaction, reduced stability, and patch failure in a short time. Therefore,  
667 to have a durable patch, factors that improve workability must be considered, as they may  
668 oppose stability [78, 82]. The impact of aggregate and binder on workability and, subsequently,  
669 durability of the patch can be summarized in Table 9 [20].

670

Table 9. Aggregate and binder impact on patch workability and durability [20]

Characteristic	Parameter	Workability	Durability
Binder Viscosity	Low Viscosity	Good	Poor
	High Viscosity	Poor	Good
Aggregate Shape	Angular	Poor	Good
	Rounded	Good	Poor
Aggregate Size	Larger	Poor	Good with ideal condition
	Finer	Good	Good if hole depth is less than 76 mm
Aggregate Gradation	Open	Good	Poor
	Dense	Poor	Good

671

672 To evaluate cold patching materials, **Kandhal and Mellott [1, 72]** used a spatula in their research  
673 in 1981. The test was performed subjectively by dipping the spatula into the mixture, and **the**  
674 results were reported as good, fair, and poor. A cement concrete penetrometer was also used to  
675 obtain quantitative results by the research team and **is** called the PTI method. The greater the  
676 force required to penetrate the tool into the sample, the lower the workability. However, the  
677 results were inconsistent, and the test failed to quantify the workability. The presence of large  
678 aggregate particles or the degree of sample compaction can impact the test, as well. They  
679 suggested maybe using a mixer such as a Vane-Shear device leads to more accurate results.  
680 **During a study in 2019 [34]**, the use of a mixer to quantify the cold mixture workability was  
681 **found to be** satisfactory. The average measured torque in one minute was considered as an  
682 indicator of mixture workability. The greater the torque, the worse the workability. The first  
683 idea of using torque to measure workability **had** already been proposed by Marvillet and  
684 Bought in 1979 to assess HMA workability. They used the torque needed to rotate the paddle  
685 within the HMA sample for this purpose [102].

686 Similar results from the PTI test **were** achieved in a study by **Prowell and Franklin [1]**. During  
687 their study **of** 14 types of proprietary cold mixtures, no strong correlation was found between  
688 laboratory and field results. However, **Berline and Hunt [62]**, in their research in 2001, obtained  
689 a good correlation between the field and lab results. In 1986, **Anderson et al. [9]** used the  
690 PennDOT subjective spatula method to evaluate the mixture workability and found this  
691 procedure undesirable from the point of repeatability, especially inter-laboratory repeatability.  
692 Therefore, by connecting a 9.5 mm by 75 mm extension to the penetrometer foot, they modified  
693 the PTI method and quantified the cold mix workability. A reasonable correlation was obtained  
694 between the results **of** the two methods. In the SHRP H-106 extensive repair project of more  
695 than 1250 potholes, PTI and Blade Resistance test methods were considered to evaluate the

696 mixture workability in the laboratory and field. The Blade Resistance device is similar to the  
697 PTI probe, except the tool uses a blade instead of a bullet-shaped connection in the probe. The  
698 results showed that, due to the greater contact area of the blade with the sample, the values  
699 obtained by the Blade Resistance method are almost five times larger than the values obtained  
700 by the PTI method. Therefore, they found that the PTI method is suitable for stiffer mixtures  
701 owing to its small cross-section. However, the Blade Resistance method is more effective on  
702 soft patching materials. Since the mixture workability is the main issue when it becomes stiff,  
703 the PTI method can provide more meaningful results [47]. The results of the mix workability  
704 were variable by the Blade Resistance test in research conducted by the NJDOT. Therefore,  
705 this test was not recommended for future research [6]. Unlike the results of the NJDOT, the  
706 workability of the 24, 96, and 168-hours cured specimens at 25°C showed a confident linear  
707 correlation with curing time in a study by Liao et al. [83]. However, the required resistance to  
708 penetration of the blade into the mixtures was low compared to the recommended range in  
709 ASTM D6704. To quantify the workability of the patching materials, Estakhri and Button [39,  
710 82] used the same PTI method in 1995. However, they couldn't find noticeable differences in  
711 the workability results of various mixtures. To get more reasonable results, the PTI test method  
712 was modified two times by changing the box shape and the location of the hole on the box wall.  
713 The modifications demonstrated some improvements over the PTI method; however, the  
714 results didn't show a good correlation with field workability evaluations. Afterward, they tried  
715 to measure the mixture workability with a Texas Gyrotory Compactor. The total number of  
716 mold gyrations required to reach the defined compaction pressure was considered for this  
717 purpose. Once again, no correlation was obtained between laboratory and field values. Since  
718 none of the previous procedures were successful, triaxial compression and unconfined  
719 compression tests were employed to quantify the workability of the material. The methods that  
720 were based on the Mohr circles and the Mohr failure envelope showed a relatively satisfactory  
721 workability value. Aside from using more materials than the other methods, it is also time-  
722 consuming and requires costly apparatus [103].

723 In a study by Lesueur [104] in 2002, using the Nynas device for measuring the workability of  
724 cold mixtures was recommended. According to this research, the Nynas device was able to  
725 differentiate the influence of different parameters such as binder content, temperature, the  
726 nature of aggregates, and water. The maximum shear force applied to the loose mixture was a  
727 measure of workability. In another study, the Nynas device and Gyrotory Shear Compactor  
728 (GSC) were employed to investigate the workability of Warm Mix Asphalt (WMA). Unlike  
729 the Nynas device that led to definite results, the GSC was not sensitive to temperature and

730 resulted in similar values [105]. In a research project by TxDOT, it was announced that the  
 731 slope of the GSC compaction curves and the work done by the shear force during the  
 732 compaction (the area under the curve) can be used as a surrogate measure of the cold mixture  
 733 workability [20]. Ferrotti et al. [106] considered the mentioned recommendations to assess the  
 734 workability of high-performance fiber-reinforced cold mixtures. The intercept and the slope of  
 735 the regression compaction (void-number of gyrations) curves were used to analyze the air-void  
 736 content and workability of the mixture, respectively. Besides, TxDOT researchers tried to  
 737 develop a method to measure workability by taking the idea from the concrete slump test. As  
 738 a result, during a similar experiment called the Cold Patch Slump Test (CPST), the required  
 739 time for a cold mixture to slump under its own weight was considered as a measure of  
 740 workability. So, less time to slump indicates more workability and vice versa. The results of  
 741 testing six proprietary CMPMs at three different cold temperature levels showed a good linear  
 742 correlation between the field and laboratory results [20]. Abaffyová and Komačka [107] used  
 743 the slump test to assess the storageability of the CMPMs, not the workability. Through their  
 744 research, the cold mix is poured into the inverted Abram cone or the CBR mold for 10 minutes  
 745 to experience the self-compaction condition. Then, the mold or cone is lifted, and the required  
 746 time for dropping the whole mixture from the mold is recorded and reported as a measure of  
 747 storageability.

748 Hemsley [108] used densification curves of compacted HMA to assess the workability of the  
 749 mixture, and defined the locking point. The locking point is the number of gyrations that after  
 750 three continuous gyrations, no noticeable changes in the height of the samples are detected. In  
 751 their research, less than 30 and higher than 70 gyrations were considered to indicate easy to  
 752 compact and hard to compact mixtures. This approach was employed to measure the cold mix  
 753 workability in other research, and they found the locking point of the mixtures below 100  
 754 gyrations [109, 110].

755 Moreover, in another study, the area under the compaction curves was used to measure the  
 756 workability and compactibility of the mixtures. The energy required to compact the loose  
 757 mixture to 92% density (corresponding to 8% air void in the target mixture) led to defining the  
 758 following energy indices (Eq. (1) and Eq. (2)) that measure the mixture workability [111].

759 Volumetric Energy index from intercept to 92%  $G_{mm}$ :  $EI_{(92\%)} = P \times \frac{\pi d^2}{4} \times \sum_{N=1}^{N_{92}} \Delta h$  (1)

760 Workability Energy index from intercept to 92%  $G_{mm}$ :  $WEI = \frac{EI_{(92\%)}}{N_{92}}$  (2)

Where  $d$  is the sample diameter,  $P$  is the compaction pressure,  $h$  is the sample height during compaction, and  $N$  is the number of gyrations.

According to Eq. (1) and Eq. (2), when a mixture is hard and has low workability, more energy is needed to compact it. On the other hand, the increase in the number of gyrations indicates a lower WEI and vice versa [111].

Table 10. The summary of methods used for measuring the workability of CMPMs

Researcher	Workability measuring method	Indicator of the workability	Ref.
Kandhal and Mellott	Dipping a spatula into the mixture	Subjectively (good, fair, and poor)	[1, 72]
	Penetrating a cement concrete penetrometer into the mix (PTI method)	Maximum penetration force	
Han. et al.	Using a mixer to mix the mixture	Torque needed to rotate the paddle	[34]
Anderson et al	Modified PTI method (changing the bullet-shaped connection of the probe)	Maximum penetration force	[9]
SHRP (H-106)	Using a blade to penetrate into the mix	Maximum penetration force	[47]
Estakhri and Button	Modified PTI method (changing the box)	Maximum penetration force	[39, 82]
	Compacting the mixture with a Texas Gyratory Compactor	Number of gyrations required to reach the defined compaction	
	Triaxial compression test	Cohesion value and friction angle	
	Unconfined axial compression test	Unconfined compressive strength	
Lesueur	Using a Nynas device to apply shear force to the loose mixture	Maximum applied shear force	[104, 105]
TxDOT	Using a Gyratory Compactor to compact the mixture	The slope and the area under the compaction curve	[20, 106]
TxDOT	Cold Patch Slump Test (CPST)	Required time for a cold mixture to slump under its own weight	[20]
Hemsley	Using a Gyratory Compactor to compact the mixture	Locking point of the mixture during the compaction	[108-110]
Bahia et al.	Using a Gyratory Compactor to compact the mixture	Energy required to compact the loose mixture (Energy index)	[111]

### 3.3.2. Adhesion and cohesion characteristics

CMPMs should provide satisfactory cohesion and adhesion to prevent patch failure. Cohesion is the characteristic that makes the mixture components adhere together and work well altogether, while adhesion is a feature that provides better stickiness between the patch and the

1 773 surface of the existing pavement [112]. The weakness of each of these features will cause the  
2 774 patch to prematurely fail, especially when the pothole is not dried and prepared before the  
3 775 repair operation [100]. The initial patch stickiness is usually low and increases over time.  
4 776 However, to ensure adequate bonding between the patching material and the pothole, applying  
5 777 a bond coat to the inside and around the hole is recommended [113]. This bond coat, which  
6 778 usually is a cationic emulsion containing at least 60% asphalt binder, prevents future water  
7 779 seepage and patch debonding, as well [7, 70, 114]. To prevent the patch debonding and increase  
8 780 the durability of the repair, preheating the pothole and heating the mixture were recommended  
9 781 in the literature. To achieve this goal, various techniques using infrared heat [115, 116], radiant  
10 782 heat [58], and high-frequency electromagnetic fields for mixtures with fibers have been  
11 783 conducted through various studies [46, 64]. The 324 repaired potholes with heated and  
12 784 unheated mixtures in a study by Indiana state DOT revealed that heated patches were more  
13 785 durable than unheated ones [117].

14 786 Past studies show that using a tack coat is necessary to repair potholes and will extend patch  
15 787 durability. Plus, it improves crack resistance properties [118]. However, CMPMs should have  
16 788 self-tacking properties to eliminate the need to use a tack coat. The bonding characteristic was  
17 789 assessed through an experiment by Anderson et al. [9] in 1998. The maximum shear force  
18 790 required to bond failure at the interface between the base and the compacted cold patch was  
19 791 considered to measure the self-tacking feature. The results of the tests in dry and wet conditions  
20 792 were not reliable and conclusive.

21 793 To evaluate the bonding characteristics at the interface layer, the Leutner shear test device has  
22 794 been employed in other studies. Lee et al. [119] applied a vertical load across the reinforced  
23 795 interface layer and found that a rough surface improves the bonding, but increasing the  
24 796 temperature (in this case, from 25 °C to 60 °C) impacts the bond feature adversely. The same  
25 797 procedure was also used by Sudarsanan et al. to investigate the bond strength across the  
26 798 interface layer at various temperatures [120]. Also, Collop et al. [121], West et al. [122], and  
27 799 Bae et al. [123] found the same impacts of temperature on the bonding properties.


28 800 Additionally, the inclined shear test was carried out to simulate the effect of vertical and  
29 801 horizontal loads (vehicle tire and braking loads) on the interlayer bonding strength of the  
30 802 composite asphalt. The results declared that using a tacky material is necessary to apply at the  
31 803 interface layer. Plus, the thickness of the tacky coat, temperature, and freeze-thaw cycles affect  
32 804 the interface shear strength [124]. Similar results were achieved in Chen et al. [125] research  
33 805 on the bonding strength of cold patching materials and HMA. Humidity and high temperatures  
34 806 weaken the bonding characteristics at the interface layer. So, increasing the temperatures from

807 -5 to 55 °C reduced the interface shear resistance by 98.6%. Also, according to their results,  
808 the type of the tacky material and the surface roughness had the dominant impact on the  
809 interface bonding characteristics. Another method was used by Virginia DOT to assess the  
810 adhesiveness of the mixture. Through this procedure, the oven-aged (4 hours at 60°C) CPM  
811 is compacted on the HMA specimen and inverted (Fig. 9), then the required time for their  
812 debonding is considered as the adhesion degree. Mixtures with longer adhesion times or more  
813 remnant weight show higher adhesiveness. The 5 to 30 second bonding time is considered the  
814 optimum adhesion degree [41, 53]. Less than 5 seconds may point out excessive binder  
815 contents. Longer than 30 seconds may indicate insufficient or high viscosity binder. As a result,  
816 this experiment may not reflect the adhesion properties of CPMs but may be useful for  
817 measuring mixture quality [1].



818  
819 Figure 9. Adhesion test on the inverted complex specimen

820 In a study at the University of Minnesota, the maximum diametric load applied to a complex  
821 briquette involving half cold mix and half HMA (Fig. 10), was considered to measure bonding  
822 properties [15, 16].

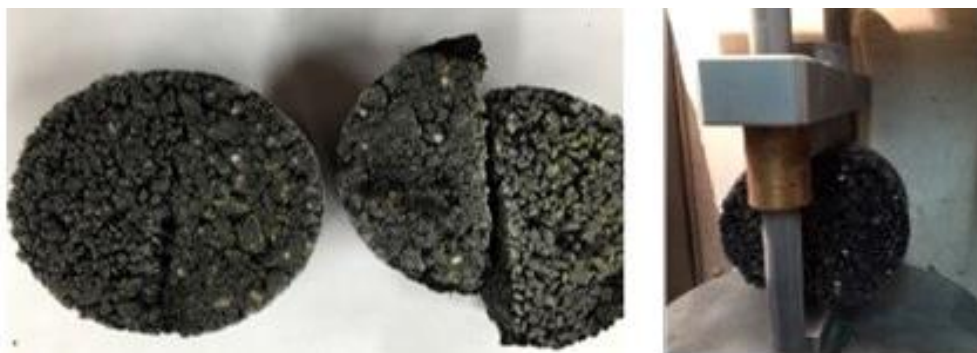

823  
824  
825 Figure 10. Interface shear strength test by applying a diametric load [15]

1 827 The modified Cantabro test has been used to measure the stickiness properties of CMPMs in  
2 828 the literature, as well. The Marshall briquette in the Los Angeles machine is subjected to 100  
3 829 gyrations, and the mass loss during abrasion is considered the stickiness index [92]. This  
4 830 method was also reflected in another study conducted by Ferrotti et al. in 2014 [106]. But the  
5 831 cold mix specimens were subjected to 300 revolutions, not 100 gyrations. Additionally, the  
6 832 Cantabro test was employed to assess the raveling and moisture susceptibility of the cold  
7 833 mixtures. The raveling properties of waterborne epoxy-emulsified asphalt mixture were  
8 834 evaluated by Bi et al. in 2020 [126]. Plus, the mass loss difference between the abraded wet  
9 835 specimens and dry specimens shows the moisture susceptibility of the cold patching materials  
10 836 [99].

11 837 Mixture cohesiveness has also been investigated by the ‘Rolling Sieve Test’ in the literature.  
12 838 This experiment, which simulates the cohesion properties of patching materials under the  
13 839 vehicle tire, is based on the Ministry of Transportation of Ontario (MTO) method. Through  
14 840 this procedure, a compacted Marshall specimen is rolled horizontally in a caped sieve for 20  
15 841 seconds. The remaining weight of the sample after rolling compared to its initial weight is  
16 842 calculated as a measure of mixture cohesion, which should be more than 60% [37, 53, 62]. The  
17 843 MTO report states that a loss of more than 35 percent is unacceptable [97]. Although this test  
18 844 does not guarantee the success of a mix, it indicates the potential for poor performance of a  
19 845 mix [20].

### 20 846

### 21 847 3.3.3. Water sensitivity

22 848 Water sensitivity generally, called stripping, is one of the main concerns of asphalt pavements.  
23 849 This problem can occur in various forms, like; loss of binder-aggregate bonding, cohesion  
24 850 failures within the aggregates, binder emulsification, and freeze-thaw cycles due to trapped  
25 851 water [127]. In CMPMs, moisture impacts the binder and aggregate bonding interactions and  
26 852 results in bonding failure that is dominant distress in cold patches [11]. Therefore, to minimize  
27 853 the cold mixture water damage, the binder-aggregate compatibility, aggregate hydrophobic and  
28 854 hydrophilic features, and overall mix design parameters such as density and air-void should be  
29 855 noticed [15].

30 856 This compatibility and moisture susceptibility of the cold patches have been investigated  
31 857 through similar methods that were previously used to evaluate HMA. Thomas and Anderson  
32 858 [74] determined the water sensitivity of the mixture by a subjective assessment. The percentage  
33 859 of aggregates coated with a binder in a mixture was considered an indicator of this parameter:  
34 860 90% was defined as the minimum acceptable value. To reduce the visual error in coating

1 861 evaluation, Ling et al. [109] used digital imaging analysis to assess the influence of the  
2 862 aggregate coating on moisture susceptibility of the CMPMs. The results showed that the  
3 863 moisture susceptibility of CMPMs is highly dependent on the level of aggregate coating  
4 864 predicted by the quantitative models. Another visual evaluation method was used by SHRP in  
5 865 1993 [38]. In that study, an over 90% coated mixture was kept in a one-liter container filled  
6 866 with distilled water at 60 °C for 16 to 18 hours (static immersion). Then, the container,  
7 867 including water and the mixture, was agitated for 5 sec and drained. The coating percentage of  
8 868 aggregates should not be less than 90% to be accepted [37, 47, 127]. The maximum acceptable  
9 869 stripping value in ASTM and Indian Roads Congress standards is 5% [97]. Kandhal and Mellott  
10 870 [72] conducted this visual evaluation by pouring 50 grams of the cured mixture into 400 ml of  
11 871 distilled boiling water and stirring with a rod for 3 minutes. Then, they decanted water and  
12 872 spread the wet mixture on absorbent paper for coating level. The aggregate should be at least  
13 873 90% coated with an asphalt binder film.

14 874 The TxDOT and other researchers used a “boiling water test” to measure moisture sensitivity.  
15 875 In this method, the mixture is placed in a container of boiling water for 10 minutes. Then the  
16 876 sample is drained and the coating degree should be more than 90% [39, 62]. The results of a  
17 877 study by the Virginia Transportation Research Council showed that the boiling water method  
18 878 had a better ability to detect differences in stripping results than the immersion method [1].  
19 879 Similar results were reported by Tam and Lynch [128]. They claimed that the boiling water  
20 880 test for 10 minutes is a severe and rapid process that doesn’t simulate the field stripping  
21 881 conditions in the lab. In another research, Lavorato et al. [96] used a less severe method, which  
22 882 has been described in the MTO standard (MTO OPSS 307), to assess the mixture stripping.  
23 883 The mixture is placed in boiling water and stirred with a rod at the rate of one rotation per  
24 884 second for 3 minutes. Conversely, to other test methods, the minimum acceptable aggregate  
25 885 coating was set at 75%. The mass loss of the cold mixture after being subjected to boiling water  
26 886 was also considered as an indicator of stripping and mixture water damage. However, the mass  
27 887 loss values were negligible relative to the sample weight, and the test results were highly  
28 888 variable in research [109, 129, 130].

29 889 Besides the mentioned methods, the modified Lottman method was employed by TxDOT to  
30 890 measure the moisture damage. Unlike previous test methods, this procedure is done on  
31 891 compacted samples and the tensile strength ratio of two sets of samples (moisture conditioned  
32 892 and unconditioned) determines the water susceptibility of the mixture. The results of the  
33 893 TxDOT study showed that subjective evaluation with a boiling water test is more logical than  
34 894 the modified Lottman method to measure the stripping potential [60, 67]. However, the

895 Lottman method **has been widely** used in other studies to measure the stripping potential of  
 896 CMPMs under freeze-thaw conditions [53, 92, 131]. **In addition to** the Lottman method, the  
 897 Binder Bond Strength (BBS) test **has also** been employed to assess the relationship between  
 898 mixture water damage and coating level in other studies. **Ling et al. [130]** used the BBS test **to**  
 899 **evaluate** the moisture susceptibility of emulsion–aggregate bonding. The Pull-Off Tensile  
 900 Strength (POTS) in wet and dry conditions was calculated. According to Eq. (3), the Bonding  
 901 Loss Ratio (BLR) was defined as an indicator of moisture susceptibility. The test results of  
 902 limestone aggregate and emulsion were similar to the results obtained from the modified  
 903 boiling test with image processing. Also, this test method was used to assess the water  
 904 sensitivity of the emulsion-aggregate and mastic-aggregate **systems** after 2 h and 24 h water  
 905 conditioning.

$$BLR = 1 - \frac{POTS_{wet}}{POTS_{dry}} \quad (3)$$

907 The Marshall Stability Ratio (MSR), which is the ratio of the Marshall stability values of water-  
 908 damaged samples to **the** Marshall stability of cured specimens (Eq. (4)), was defined to measure  
 909 the moisture sensitivity of cold mixtures in other studies. Higher values of MSR represent lower  
 910 moisture susceptibility [91, 99].

$$MSR = \frac{MS_{wet}}{MS_{dry}} \times 100 \quad (4)$$

912 Given that the open-graded CMPMs' moisture sensitivity is associated with gradation  
 913 proportion, the Moisture Index (MI) was defined (Eq. (5)) by researchers to represent the  
 914 moisture damage resistance of open-graded CMPMs. MI is the ratio of aggregates remaining  
 915 on sieve No. 4 ( $P_{\#4}$ ) to the ratio of aggregates remaining on sieve No. 50 ( $P_{\#50}$ ). The higher  
 916 MI values determine higher mixture porosity, higher water seepage, and higher water damage,  
 917 subsequently [99].

$$MI = \frac{P_{\#4}}{P_{\#50}} \quad (5)$$

919 Besides, **the** Wet Track Abrasion Test (WTAT), which is usually **adopted** for slurry seal  
 920 mixtures, was used to measure the water sensitivity of the CMPMs. The WTAT results of  
 921 **Kwon et al. [95]** research on RAP included cold mix materials proved **that the RAP**  
 922 **introduction in the mix-design** improves the mixture resistance to abrasion loss. Also, even  
 923 though the Hamburg Wheel Tracking Device (HWTDD) **is a severe procedure** for cold mixtures,  
 924 it has been used in wet conditions to measure the water damage of CMPMs [38]. **Table 11**  
 925 **shows the summary of methods used for measuring the water sensitivity of CMPMs.**

In the end, since CMPMs are usually applied during cold and rainy seasons, they should withstand adverse weather and traffic loads that lead to debonding, dislodging and failure of the mixture [100]. Therefore, antistripping additives such as Portland cement, flue dust, hydrated lime, fly ash, etc., should be used in the cold mix to reduce moisture damage during the stockpile, practice, and in-service [60, 78, 98].

**Table 11. The summary of methods used for measuring the water sensitivity of CMPMs**

<b>Researcher</b>	<b>Water sensitivity measuring method</b>	<b>Indicator of the workability</b>	<b>Ref.</b>
Thomas and Anderson	Visual subjective assessment	Coating degree of aggregates	[72, 74]
Omar et al.	Static immersion		[37, 127]
Manolis et al.	Boiling water test		[62, 96]
Ling et al.	Digital imaging analysis	Level of aggregate coating	[109]
Ling et al.	Boiling water test	Mass loss	[129, 130]
Dong et al.	Modified Lottman method	Tensile Strength Ratio (TSR)	[60, 92]
Ling et al.	Binder Bond Strength (BBS)	Bonding Loss Ratio (BLR)	[130]
Wang et al.	Marshall stability	Marshall stability ratio of water-damaged to the cured samples	[91, 99]
Huang et al.	Moisture Index= $P(\#4)/P(\#50)$	Mixture porosity	[99]
Kwon et al.	Wet track abrasion test	Abrasion loss	[95]
Smith et al.	Hamburg wheel tracking device	Rut depth	[38]

### 3.3.4. Stability and initial strength

Stability is one of the main characteristics of patch materials that provides sufficient ability to resist vertical and horizontal displacement of the patch under traffic [6, 53]. This property is especially noticeable immediately after a patching operation is performed, i.e., when the repaired pothole is more sensitive to the traffic flow. In fact, the patched area after compaction should be stable enough to prevent rutting and shoving caused by traffic [20]. To meet this early performance, aggregate gradation and compaction level play a major role. However, the long-term performance of the patch is related to its stability after traffic compaction [34, 126, 131]. Therefore, different factors that affect the stability of the mixture, such as aggregate gradation and compaction level, binder quality and quantity and mixture curing rate should be taken into account [53, 132]. Also, since excessive stability usually leads to low workability, precautions should be considered to strike a balance between the stability and workability of the mixture. An acceptable stability level is achieved over time by the mixture curing, while this process is time-consuming and traffic flow should be established immediately. So, the bonding properties, gradation and internal friction of the aggregates are the main factors in

1 948 improving stability and, subsequently, mechanical properties [2, 62, 101]. Even though there  
2 949 are no accepted test methods in the technical literature to assess CPM stability [9], it is often  
3  
4 950 determined by Indirect Tensile Strength (ITS), Marshall Stability (MS) and Resilient Modulus  
5 951 (RM) **procedures** [39, 83]. Despite the mentioned experiments, a few **pioneering procedures**,  
6  
7 952 such as **the** screwdriver penetration test and steering wheel rotation using a passenger car, are  
8  
9 953 used to assess the suitability of the cold repair mixtures. Although these tests result in useful  
10  
11 954 information, the lack of **standardized** methods makes it difficult to evaluate the potential  
12  
13 955 performance of CPMs [101].

14 956 As most experiments have been designed to assess the performance of HMA, the researchers  
15  
16 957 considered a preliminary aging process to provide sufficient stability for mixture  
17  
18 958 compactibility. Usually, the specimens prepared without the curing and aging process  
19  
20 959 immediately collapse after demolding and during the test [133]. **In the evaluation of the CPM**  
21  
22 960 **performance, Manolis et al. [96] could not measure the bulk density of the compacted specimen**  
23  
24 961 **due to its collapse after demolding.** A similar occurrence was observed in Marin's study [134]  
25  
26 962 on different types of CPMs, **although the samples** were confined during the curing time to  
27  
28 963 prevent them from collapsing before the test. Additionally, another study has reported that the  
29  
30 964 gyratory compacted specimens were unstable even after **being subjected** to up to 96 h at 25 °C  
31  
32 965 curing condition [20]. **Anderson et al. [9]** investigated the stability of the cold **mixtures** by  
33  
34 966 applying **a** haversine load on a cylindrical aged specimen through a steel foot. The results of  
35  
36 967 the experiment after 1000 cycles showed small plastic deformation. Plus, the experiment could  
37  
38 968 **not** simulate the traffic load and was time-consuming. Consequently, the research team did not  
39  
40 969 believe that this test warrants further development. In the SHRP project, the RM and MS tests  
41  
42 970 were conducted on the oven-aged samples to assess the CPM stability. However, the test was  
43  
44 971 an indication of in-placed or utilized materials after being several months under traffic [47].  
45  
46 972 **Maher et al. [6]** used the aforementioned test methods to evaluate the stability of various  
47  
48 973 CPMs. The results of the study showed that there is no correlation between the field  
49  
50 974 performance and the results of the IDT test. The results of the MS and RM test methods showed  
51  
52 975 a similar outcome as well. The authors found that the use of the RM methodology for evaluating  
53  
54 976 CPMs is doubtful. In another research, **Shoenberger et al. [13]** **selected** MS and triaxial  
55  
56 977 compression (confined and unconfined) experiments. The results of the axial strain in the  
57  
58 978 triaxial test were similar for the various **mixtures**. Also, the research team did not find the MS  
59  
60 979 test as a reliable indicator for performance evaluation of CPM due to the unsuitability of this  
61  
62 980 test for open-graded mixtures. Limited use of the Hveem stabilometer has been reported in the  
63  
64 981 literature to measure the cold mix stability [9]. Furthermore, the results of an investigation on

982 a conventional cold mixture (CCM), one type of proprietary cold patch (QPR brand) and HMA  
983 at the University of Minnesota showed a weak MS for the QPR mixture before and after curing.  
984 But the CCM, although it had weak stability before curing, showed comparable stability to  
985 HMA after curing [15, 16]. According to the literature, the MS of the unmodified CMA is  
986 significantly lower than HMA and WMA [11].

987 Through the MS evaluation of the CMPM, Weimin achieved an initial stability of mix not less  
988 than 2.0 kN and 1.5 kN at room and low temperatures, respectively. In a similar study by Jiguo,  
989 these values were obtained at 2.0 kN and 1.0 kN, respectively. The Japan Modified Asphalt  
990 Association standard specifies a minimum of 0.5~0.8 kN and 3.0 kN for initial MS and the 7th  
991 day after opening traffic stability, respectively [14]. In other studies, the minimum initial MS  
992 for CMPMs before opening traffic was suggested to be at least 2.5 kN [19]. However, for some  
993 cold mixtures, it takes about 10 days to reach 3 kN stability [17, 87]. China requirements have  
994 recommended a strength greater than 3 kN and 5 kN for the initial and forming strength of  
995 CMPMs, respectively [126]. In a comparative study on the un-treated cold mix and hot mix  
996 samples, the obtained MS values were 5.88 kN and 3.44 kN for dense-graded and open-graded  
997 mixtures, respectively, while these values were 11.48 and 10.71 kN for asphalt concrete and  
998 stone matrix asphalt, respectively [135]. The stability of open-graded and dense-graded cold  
999 patching mixtures including modified asphalt cement was analyzed through the MS test in  
1000 another investigation. Rapid curing (24 h at 110 °C) and ambient curing (24, 72, 168, and 336  
1001 h at 25 °C) processes were considered before conducting tests at 40°C. As expected, the results  
1002 indicated higher stability values for dense-graded CMPM with respect to the open-graded one.  
1003 Plus, the wheel track test was also carried out on aged and unaged specimens in wet and dry  
1004 conditions for more verification. They found that moisture intensified the sample deformation;  
1005 however, it provides more reasonable results for predicting rut depth, especially in wet weather  
1006 conditions. Furthermore, they inferred that the stability and rutting resistance of the CMPMs  
1007 with high viscosity (130 poise) modified binders are comparable to those of HMA [83]. Also,  
1008 Biswas et al. [53] found similar results through a study on dense-graded and open-graded cold  
1009 mixtures that had been cured at 65°C and 135°C for 14 to 18 h. The authors found that the  
1010 stability of dense graded samples cured at 135°C is comparable to HMA. A similar study was  
1011 done by Rezaei et al. [79] to assess the stability and rutting performance of CMPM in dry and  
1012 wet conditions. The results showed that curing the specimens at ambient temperature, the  
1013 HWTD turned out to be a very harsh test for CMPMs: specimens showed low resistance to  
1014 permanent deformation. However, the research team found that HWTD is a suitable test  
1015 method to evaluate the stability of CMPMs at accelerated-cured (135°C for 18 h) conditions.

1016 Moreover, they claimed that the MS test is an effective way to distinguish the stability of  
1017 CMPMs. HWTD was also considered to evaluate the stability of CMPM in research conducted  
1018 by Chatterjee et al. [20]. Due to the harsh impact of HWTD on uncured samples, the test was  
1019 carried out on 96-hour cured specimens that were compacted at 100 °C. It was concluded that  
1020 the longer the curing time, the higher the rutting resistance. The same test was conducted by  
1021 Visser et al. [131] to assess the rut resistance of CMPMs. The materials were compacted and  
1022 tested at various temperatures, but the authors did not consider HWTD a suitable test method  
1023 to predict rut depth in the field. Even though the long curing time and compacting of the  
1024 samples at high temperatures provide stable specimens before testing under HWTD, it  
1025 drastically changes the properties of the mixture [96, 104]. To solve this issue, the Texas  
1026 Stability Test (TST) was developed to evaluate the stability of cold mixtures. So, the compacted  
1027 specimens with the Texas Gyrotory Compactor (TGC) were cured at room temperature for 0,  
1028 1, and 2 weeks before 2-day conditioning and testing. Then, the MS test was conducted on the  
1029 samples and the maximum compressive load was used as a stability measure of CMPMs.  
1030 Furthermore, the research team employed an MMLS3 to assess the stability of the cold mixture  
1031 under Accelerated Pavement Testing (APT) conditions [104]. Dong et al. [41] in a study used  
1032 the Asphalt Pavement Analyzer (APA) to evaluate CMPM resistance to deformation. Their  
1033 investigation into the cold dump and cold proprietary patches that were cured for 96 hours and  
1034 compacted at 100 °C illustrated that even though cold dump materials had better performance  
1035 than the cold proprietary patches, their rut depth was very high at low load cycles. Kwon et al.  
1036 [95] used the APA and Marshall devices to evaluate the stability and performance of cold  
1037 mixtures, including RAP and virgin aggregates. Their investigation revealed better stability for  
1038 mixtures containing RAP materials.

1039 The permanent deformation of CMPMs was investigated through the Modified Cyclic Creep  
1040 Test (MCCT) and Light Cone Penetrometer (LCP) in research by Diaz in 2016 [101]. Multiple  
1041 Linear Regression Analysis (MLRA) was employed to analyze the data and led to two  
1042 predictive equations to estimate the parameters of MCCT as a function of rutting performance  
1043 with an LCP. The results claimed that to ensure the minimum required initial stability of the  
1044 cold patch, the LCP can be used to estimate the compactibility of the cold mixture during  
1045 operation. Besides, a penetration shear test was employed by Haipeng et al. [87] to simulate  
1046 patch deformation under vehicle loads. The test results of oven-cured Marshall briquettes at  
1047 various temperatures (Fig. 11) demonstrated that at the increased temperature, the deformation  
1048 resistance is low. A similar test, the California Bearing Ratio (CBR), was also used in another

study to assess CPM short-term premature deformation (Fig. 12). The results revealed that the CBR index is affected by the stone skeleton and aggregate gradation of the mixtures [112].



Figure 11. Conducting penetration shear test [87]



Figure 12. CBR test on cold patch mix [112]

As mentioned, adequate patch compaction is necessary to improve patch stability and prevent premature failure due to deformation under traffic [69]. To evaluate the stability of the patch materials, the area under the compaction curves has been used in the literature. Similarly, to the equations mentioned in section 6.1, the following Eq. (7) and Eq. (8) were presented for mix stability evaluation [111]:

$$\text{Shear Energy index (EI) from 92\% to 96\% } G_{mm}: EI_{(92-96)} = P \times \frac{\pi d^2}{4} \times \sum_{N_{92}}^{N_{96}} \Delta h \quad (7)$$

$$\text{Compactibility Energy Index from 92\% to 96\% } G_{mm}: CEI = \frac{EI_{(92-96)}}{N_{92-96}} \quad (8)$$

where  $d$  is the sample diameter,  $P$  is the compaction pressure,  $h$  is the sample height during compaction, and  $N$  is the number of gyrations.

In the indices, the 92% and 96%  $G_{mm}$  (corresponding to 8 to 4% air void in the target mixture) are related to the mix shear strength. CEI is the energy needed to compact the mixture to reach a density of 92 to 96%. Mixes with lower CEI values provide more durability and will be more stable during service life under traffic loads [111].

Another index has been defined by Anderson et al. [136] to measure the HMA stability based on the linear compaction slope ( $K$ ) and the air void ( $AV$ ) corresponding to the design number of gyrations ( $N_{design}$ ). According to the Eq. (9), better stability and rutting resistance are achieved by the higher values of  $K \times AV$ .

$$S = K \times AV \quad (9)$$

The literature has mentioned a maximum of 0.5 and a minimum of 20 for CEI and  $S$ , respectively [111].

As mentioned before, the stability of the CMPMs is low, especially immediately after their compaction. Therefore, different types of modifiers are used in the mix design to achieve higher stability. Usually, additives such as mineral fillers, fiber, rubber, polymer, sulfur, etc., are used in the proprietary or modified binder production process to improve the mixture stability [50, 137]. Table 12 shows the summary of different methods used for measuring the stability of CMPMs.

Table 12. The summary of methods used for measuring the stability of CMPMs

Researcher	Stability Measuring Method	Indicator of the Stability	Ref.
Diaz	Screwdriver test	Penetration of screwdriver	[101]
	Wheel rotation using a car	Patch resistance against wheel rotation	
Anderson et al.	Applying a dynamic haversine load through a steel foot	The plastic deformation	[9]
Jain et al.	Marshall stability, Resilient modulus and Indirect tensile strength tests	Compressive strength, Resilient modulus, and Tensile strength	[13-16]
Shoenberger et al.	Triaxial compression test	Compressive strength	[13]
Anderson et al.	Hveem stabilometer	Degree of plasticity	[9]
Liao et al. Rezaei et al. Visser et al.	Wheel tracking test	Rutting resistance	[20, 79, 83, 131]
Eckmann et al.	Texas stability test	Maximum compressive load	[78, 104]
	Model mobile load simulator	Resistance to deformation	
Kwon et al.	Asphalt Pavement Analyzer	Rutting resistance	[41, 95]
Wang et al.	Penetration shear test	Penetration load	[87]
Riviera et al.	California Bearing Ratio (CBR)	Resistance to applied load	[112]
Bahia et al.	Shear and compactibility energy indices	Energy needed to compact the mixture	[111]
Anderson et al.	Stability index	Compaction curve slope (K) and the air void (AV) corresponding to the design number of gyration ( $N_{design}$ ).	[136]

### 3.3.5. Storageability

Both stockpile and containerized CMPMs need to remain workable and resist stripping and binder draindown during storage. Therefore, this feature, which is called storageability and depends on the environment, storage method, and project size, should be considered for the desired storage period (6 to 12 months) in the mix design [66, 75, 100]. In fact, the improper type and content of the mix component can reduce or extend the storageability of the mixture.

1088 A mixture containing excess binder enables better durability and stickiness due to providing a  
1089 thicker film to coat aggregates [72]. **However**, it may lead to binder draindown and  
1090 accumulation at the bottom of the pile, especially immediately after stockpiling or in warm  
1091 weather. Besides, a low viscosity binder may cause drainage and stripping problems during  
1092 stockpile, while a higher viscosity or quick volatilization of the diluent leads to poor  
1093 workability [75]. Moreover, aggregates with higher water absorption features cause stripping  
1094 and draindown problems during the stockpile. **The mixing temperature should be kept as low**  
1095 **as possible and practicable to prevent binder draindown in the stockpile [94].** Also, storage at  
1096 a depth of less than 0.6 meter facilitates the cooling process and minimizes draindown [9, 74].  
1097 In addition, covering the stockpile with polyethylene or a tarpaulin sheet can help to increase  
1098 storage time [20, 75]. The FHWA and AASHTO test methods have been frequently used in  
1099 previous studies to assess the CMPM draindown and subsequent storageability. In the FHWA  
1100 draindown test method, a plate containing 1000 g of the cold mixture is placed at 60°C for 24  
1101 h. The plate is then turned over and the mixture is removed. The amount of the remained binder  
1102 on the plate, which indicates binder drainage shouldn't exceed 4 percent by mass of binder  
1103 [37]. However, the draindown of the best-performing mixtures in a study by **Prowell and**  
1104 **Franklin [1]** was in the range of 4 to 8 percent. Therefore, they concluded that the 4% limit  
1105 might be too strict and recommended a maximum of 8%. In addition, **Anderson et al. [9]** found  
1106 out that the results of the drainage test could be somewhat erroneous for the following reasons.  
1107 First, after 24 h aging at 60°C, removing all the particles from the plate is difficult. Second, in  
1108 mixtures that include a low amount of binder, the draindown occurs where the mixture is in  
1109 contact with the plate. **The** AASHTO test method for determining the draindown materials of  
1110 uncompacted asphalt mixtures was adapted by MTO for evaluating the draindown of CMPMs.  
1111 In this test, a certain amount of mixture is placed in a wire basket and conditioned for 1-h in a  
1112 forced draft oven. Then, the weight difference between the mixture before and after the  
1113 conditioning process is measured and reported as the drained binder of the mixture [96].

#### 4. Conclusion

1116 This study investigated the different aspects of CMPMs in repairing potholes. The advantages  
1117 and limitations of patching with CMPMs, repair procedures, impacts of patch components,  
1118 cost, curing, and storageability of these mixtures were assessed through this research.  
1119 Additionally, since CMPMs' durability and performance engage with poor workability in cold  
1120 weather, poor stability, especially in deep holes, bonding, and moisture susceptibility, the

1121 different procedures **for** evaluating these properties were investigated in detail. The main  
1 1122 outcomes can be summarized as follows:  
2  
3

- 4 1123 • The purpose of repairing potholes with CMPMs is to provide traffic safety by restoring  
5 serviceability, not a permanent repair. Therefore, these materials are applied in an  
6 1124 emergency as a temporary treatment until proper and definite practice is done.  
7  
8 1125 However, it is not unusual for some road administrations to use these materials with a  
9  
10 1126 desire for a more permanent solution.  
11
- 12 1127 • Although repairing potholes by a standard patching method involving vertical saw cuts  
13  
14 1128 is more durable, this procedure is time-consuming and interrupts traffic. Therefore,  
15 1129 CMPMs that do not need special tools and considerations, are considered by road  
16  
17 1130 administrators to repair potholes.  
18
- 19 1131 • Aggregates and binders play a significant role in the workability and stability of the  
20  
21 1132 CMPMs. Thus, more attention should be paid to the shape, gradation, water absorption  
22  
23 1133 of the aggregate, and binder viscosity to provide optimal performance during storage  
24  
25 1134 and in-service.  
26  
27 1135 • The volatilization of the CMPM solvents takes up to several months, and the curing  
28  
29 1136 process is time-consuming. Still, the CMPM should be cured as fast as possible after  
30 1137 placement to provide maximum stability and re-establish the traffic flow **in** the patched  
31  
32 1138 area. However, if the volatilization rate and curing during the stockpile are too fast, the  
33  
34 1139 mixture will experience premature curing and become unworkable and impractical.  
35  
36 1140 • The expected life of a temporary repaired patch with Proprietary CMPMs is up to one  
37  
38 1141 year. However, the patch longevity **is still** considered to **be** days or months instead of  
39 1142 years.  
40  
41 1143 • Pothole patching main charges involve **materials**, labor, and equipment. Usually, the  
42  
43 1144 highest cost is devoted to crew and equipment, and the cost of materials is just a small  
44  
45 1145 portion of the total patching costs. CMPMs contribute 20% of the overall repair cost,  
46  
47 1146 while this value for hot mix asphalt is 2-5%. Therefore, using high-quality materials is  
48  
49 1147 strongly recommended for patch operations.  
50  
51 1148 • High-quality CMPMs give longer service life even if they cost more. The cost of high-  
52 1149 quality materials with a proper repair method is significantly lower than the cost of  
53  
54 1150 frequent patching operations because high-quality materials offset the **cost** of frequent  
55  
56 1151 repairs that are conducted **with** poor-quality materials. Therefore, using expensive  
57  
58 1152 materials with high longevity leads to a significant cost saving in the long run, and the  
59  
60 1153

1154 cost-effectiveness appears in increased productivity and higher service levels, not  
1 1155 essentially in money-saving for the agency.

- 2 1156 • For all CMPMs that foresee an evolution or reaction of the binder, the packaging and  
3 1157 the relative workability of materials are fundamental and decree the success or failure  
4 1158 of treatment. The inefficiency of CMPMs' workability, which is very frequent  
5 1159 following their storage on pallets or shelves, leads to lower demand for materials and  
6 1160 is a severe discrimination factor in commercial competition.
- 7 1161 • The initial patch bonding is usually low and increases over time. To ensure adequate  
8 1162 bonding between the patching material and the pothole, applying a bond coat to the  
9 1163 inside and around the hole is recommended. However, CMPMs should have self-  
10 1164 tacking properties to eliminate the need to use a tack coat.
- 11 1165 • The gradation and level of compaction have a critical role in the initial stability of the  
12 1166 CMPM. Low compaction levels lead to higher air-void content (up to 30%), and the  
13 1167 patch is prone to rutting and raveling.
- 14 1168 • Through the evaluation of CMPMs' performance and durability, the samples are usually  
15 1169 aged and cured in the oven to provide sufficient stability for testing. Though this  
16 1170 procedure reflects the patch condition after several months in service, the patch  
17 1171 durability may be shorter than a few months, and the patch deteriorates in a short time  
18 1172 after patching. Consequently, evaluation of the CMPMs after long-term curing cannot  
19 1173 indicate their performance immediately after patching. The mixture may show  
20 1174 satisfactory results after long-term curing, but after patching, it distresses instantly  
21 1175 under traffic and weather conditions. A comprehensive standard is required to design  
22 1176 and evaluate the performance of CMPMs.

23 1177 In conclusion, CMPMs are quickly developing for patching potholes as suitable alternatives  
24 1178 to HMA. However, there are still some limitations and issues with their mix design and  
25 1179 performance evaluation. In fact, most of the test methods have been borrowed from the  
26 1180 HMA context. However, those approaches do not always meet the requirements of  
27 1181 CMPMs. Also, there is a conflict between mechanical performance, which is required in  
28 1182 the field and the easiness of application (workability) and compaction that is demanded by  
29 1183 road maintenance operators. Besides, most of the mechanical evaluation tests use thick  
30 1184 specimens (Marshall briquette) that need longer curing time and are not stable enough after  
31 1185 demolding, while in real conditions, patching operations are performed in thinner layers  
32 1186 (less than 50 mm) with almost immediate curing and reopening to traffic. Therefore,

1187 developing new procedures that can evaluate the performance of these kinds of materials  
1188 is essential. It is hoped that a connection between researchers, producers and operators will  
1189 be made in order to develop methods and techniques to achieve durable and superior  
1190 materials and facilitate the quality control and assurance steps.

## References

- [1] B.D. Prowell, A.G. Franklin, Evaluation of cold mixes for winter pothole repair, Transportation research record.1529(1) (1996) 76-85. <https://doi.org/10.1177/0361198196152900110>
- [2] J. Yuan, Q. Dong, T. Zhang, X. Gu, Design and performance evaluation of cement enhanced cold patch asphalt mixture, GeoShanghai International Conference (2018) 463-470. [https://doi.org/10.1007/978-981-13-0011-0\\_50](https://doi.org/10.1007/978-981-13-0011-0_50)
- [3] Y. Pei, C. Mao, M. Song, Driving mode at pothole-subsidence pavement based on wheel path, Advanced Materials Research, Trans Tech Publ, (2012) 847-851. <https://doi.org/10.4028/www.scientific.net/AEF.5.77>
- [4] A. NS, T. Thasni, N.S. Kumar, Pothole Reclamation using different pavement mixes, International Journal of Engineering Research & Technology (IJERT) 8(6) (2019) 902-904.
- [5] C. Nicholls, K. Kubanek, C. Karcher, et al., Durable pothole repairs, TRA-transport research arena, 2014.
- [6] A. Maher, N. Gucunski, W. Yanko, F. Petsi, Evaluation of pothole patching materials, Report no. FHWA 2001-02, Washington, D.C., U.S.A., 2001.
- [7] M.D. Nazzal, S.-S. Kim, A.R. Abbas, Evaluation of winter pothole patching methods, Report No. FHWA/OH-2014/2, Ohio. Dept. of Transportation. Office of Statewide Planning and Research, 2014.
- [8] T.R. Wing, Road accidents in India, Government of India, ministry of road transport and highways, New Delhi, India, 2019.
- [9] D. Anderson, H. Thomas, Z. Siddiqui, D. Krivohlavek, More effective cold, wet weather patching materials for asphalt pavements, Report No. FHWA-RD-88-001, Federal Highway Administration, Pennsylvania Transportation Institute, 1988.
- [10] G. Maupin, C.W. Payne, Evaluation of spray injection patching, Report No. VTRC 03-TAR11, Virginia Transportation Research Council, 2003.
- [11] S. Jain, B. Singh, Cold mix asphalt: An overview, Journal of Cleaner Production. 280 (2021) 124378. <https://doi.org/10.1016/j.jclepro.2020.124378>
- [12] K. Kaito, K. Kobayashi, E. Fujiwara, R. Okizuka, Durability analysis of pothole patching mixture in snowy cold region, Society for Social Management Systems Internet Journal, 5(1) (2009).
- [13] J.E. Shoenberger, W.D. Hodo, C.A. Weiss Jr, P.G. Malone, T.S. Poole, Expedient repair materials for roadway pavements, Geotechnical and Structures Laboratory, U.S. Army Engineer Research and Development Center, 2005.
- [14] L.D. Zhao, Y.Q. Tan, A summary of cold patch material for asphalt pavements, Advanced Materials Research, Trans Tech Publ. 168-170 (2011) 864-869. <https://doi.org/10.4028/www.scientific.net/AMR.168-170.864>
- [15] M. Marasteanu, D. Ghosh, M. Turos, M. Hartman, R. Milavitz, J.-L. Le, Pothole prevention and innovative repair, Report No. 2018-14, Minnesota. Dept. of Transportation. Research Services & Library, 2018.
- [16] D. Ghosh, M. Turos, M. Marasteanu, Experimental investigation of pothole repair materials, Proceedings of the 9th International Conference on Maintenance and Rehabilitation of Pavements—Mairepav9, Lecture Notes in Civil Engineering 76 (2020) 13-22. [https://doi.org/10.1007/978-3-030-48679-2\\_2](https://doi.org/10.1007/978-3-030-48679-2_2)
- [17] S. Huang, J. Ren, M. Li, Z. Li, S. Zhou, Development and evaluation of solvent-based cold patching asphalt mixture based on multiscale, Advances in Materials Science and Engineering 2020 (2020). <https://doi.org/10.1155/2020/1984972>

1236 [18] L. Geng, Q. Xu, X. Yu, C. Jiang, Z. Zhang, C. Li, Laboratory performance evaluation of a cold  
1237 patching asphalt material containing cooking waste oil, *Construction and Building Materials* 246 (2020)  
1238 117637. <https://doi.org/10.1016/j.conbuildmat.2019.117637>  
1239 [19] T. Liu, G. Hu, Y. Gu, Influence of cold patch asphalt mixture gradation on pavement performance,  
1240 Fourth International Conference on Transportation Engineering (ICTE) (2013) 1405-1410.  
1241 <https://doi.org/10.1061/9780784413159.205>  
1242 [20] S. Chatterjee, R.P. White, A. Smit, J. Prozzi, J.A. Prozzi, Development of mix design and testing  
1243 procedures for cold patching mixtures, Report No. FHWA/TX-05/0-4872-1, Federal Highway  
1244 Administration, Texas Department of Transportation, Austin, Texas, 2006.  
1245 [21] J.S. Miller, W.Y. Bellinger, Distress identification manual for the long-term pavement performance  
1246 program, Report No. FHWA-HRT-13-092, Federal Highway Administration, Office of  
1247 Infrastructure Research and Development, United States, 2003.  
1248 [22] M. McHale, C. Nicholls, I. Carswell, Guidance for the selection of pothole repair options, 6th  
1249 Eurasphalt & Eurobitume Congress, Prague, Czech Republic, 2016. (DOI):  
1250 <dx.doi.org/10.14311/EE.2016.422>  
1251 [23] A.O. Odumade, J.C. Agunwamba, Mechanistic modelling of potholes development from cracks  
1252 due to axle loads and time, *International Journal of Advancements in Research & Technology*, 9(1)  
1253 (2020).  
1254 [24] M. McHale, C. Nicholls, I. Carswell, Best practice guide for the selection of pothole repair options,  
1255 Report No. RN44, Transport Research Laboratory, 2016.  
1256 [25] F. Saeed, S. Qamariatul, M. Rahman, A. Woodside, The state of pothole management in UK local  
1257 authority, *Bituminous Mixtures and Pavements VI* (2015) 153-159.  
1258 [26] A. Ipavec, Study of existing standards, techniques, materials and experience with them on the  
1259 European market, Project No. 832700, FEHRL Brussels, 2012.  
1260 [27] J. Komba, M. Roux, G. Mvelase, Scoping study for establishment of an effective pothole and patch  
1261 repair program for the rural road network of LGED in Bangladesh, Project NO. BAN2169A, ReCAP  
1262 Project Management Unit, London, 2019.  
1263 [28] Clifton Associates Ltd., Pothole identification, assessment and repair guidelines, Leveraged  
1264 Municipal Innovation Fund, Prince Albert, Saskatoon, 2012.  
1265 [29] K.S. Jassal, Development of potholes from cracks in flexible pavements, Thesis for the Degree of  
1266 Master of Applied Science in Engineering, Concordia University, Montreal, Quebec, 1998.  
1267 [30] Anonymous, Prevention and a better cure: potholes review, UK Department for Transport, 2012.  
1268 [31] L.M. Zanko, D.M. Hopstock, W. DeRocher, Evaluate and develop innovative pavement repair and  
1269 patching: Taconite-based repair options, Report No. MN/RC 2016-03, Natural Resources Research  
1270 Institute, University of Minnesota Duluth, 2016.  
1271 [32] S. Biswas, L. Hashemian, A. Bayat, Investigation of pothole severity and maintenance methods in  
1272 Canada through questionnaire survey, *Journal of cold regions engineering* 32(2) (2018) 04018002.  
1273 [https://doi.org/10.1061/\(ASCE\)CR.1943-5495.0000161](https://doi.org/10.1061/(ASCE)CR.1943-5495.0000161)  
1274 [33] Q. Dong, M.A. Onyango, B. Huang, Investigation on service time and effective cost of typical  
1275 pothole patches in Tennessee, *Climatic Effects on Pavement and Geotechnical Infrastructure* (2014)  
1276 152-158. <https://doi.org/10.1061/9780784413326.015>  
1277 [34] S. Han, M. Liu, W. Shang, X. Qi, Z. Zhang, S. Dong, Timely and durable polymer modified  
1278 patching materials for pothole repairs in low temperature and wet conditions, *Applied Sciences* 9(9)  
1279 (2019). <https://doi.org/10.3390/app9091949>  
1280 [35] The Association of Directors of Environment, Economy, Planning & Transport (ADEPT)  
1281 Engineering Board, Potholes - a repair guide, Department for Transport, United Kingdom, 2019.  
1282 [36] M.Y. Shahin, *Pavement management for airports, roads, and parking lots*, Springer, 1994.  
1283 [37] T.P. Wilson, A. Romine, *Materials and procedures for repair of potholes in asphalt-surfaced  
1284 pavements--manual of practice*, Report No. FHWA-RD-99-168, Federal Highway Administration, U.S.  
1285 Department of Transportation, 2001.  
1286 [38] K.L. Smith, A. Romine, T.P. Wilson, *Asphalt pavement repair manuals of practice—materials and  
1287 procedures for sealing and filling cracks in asphalt-surfaced pavements*, Project No. SHRP-348,  
1288 Strategic Highway Research Program , National Research Council, Washington D.C., 1993.

- 1289 [39] C.K. Estakhri, J.W. Button, Evaluation and improvement of bituminous maintenance mixtures,  
1 1290 Report No. FHWA/TX-96/1377-1F, Federal Highway Administration, Texas Transportation Institute,  
2 1291 1995.
- 3 1292 [40] P. Paige-Green, A. Maharaj, J. Komba, Potholes: Technical guide to their causes, identification  
4 1293 and repair, CSIR Built Environment, Stellenbosch, South Africa, 2010.
- 5 1294 [41] Q. Dong, B. Huang, S. Zhao, Field and laboratory evaluation of winter season pavement pothole  
6 1295 patching materials, International Journal of Pavement Engineering 15(4) (2014) 279-289.  
7 1296 <https://doi.org/10.1080/10298436.2013.814772>
- 8 1297 [42] R. McDaniel, J. Olek, B. Magee, A. Behnood, R. Pollock, pavement patching practices-A synthesis  
9 1298 of highway practice, NCHRP Synthesis 463, National Cooperative Highway Research Program,  
10 1299 Transportation Research Board, Washington D.C., 2014.
- 11 1300 [43] C. Nicholls, K. Kubanek, C. Karcher, A. Hartmann, A. Adesiyun, A. Ipavec, J. Komacka, E.  
12 1301 Nielsen, Assessment of generic pothole repair materials, 6th International Conference on Bituminous  
13 1302 Mixtures and Pavements (2015) 759-766. DOI: 10.1201/b18538-108
- 14 1303 [44] A.M. Johnson, Best practices handbook on asphalt pavement maintenance, Report No. 2000-04,  
15 1304 Minnesota Department of Transportation, USA, 2000.
- 16 1305 [45] M. Isabela, R. Spielhofer, Rapid and durable maintenance methods and techniques, Final report,  
17 1306 ERA-NET Road – Design, Austria, 2014.
- 18 1307 [46] H.I.A. Obaidi, Development of innovative pothole repair materials using induction heating  
19 1308 technology, Thesis for the degree of Doctor of Philosophy, University of Nottingham, 2018. DOI:  
20 1309 [10.13140/RG.2.2.15618.53449](https://doi.org/10.13140/RG.2.2.15618.53449)
- 21 1310 [47] T.P. Wilson, A.R. Romine, Innovative materials development and testing. Volume 2: Pothole  
22 1311 repair, Report No. SHRP-H-353, Strategic Highway Research Program, Washington, D.C., 1993.
- 23 1312 [48] A. Griffith, Improved winter pothole patching, Report No. OR-RD 99-10, Oregon. Department of  
24 1313 Transportation, 1999.
- 25 1314 [49] H.R. Thomas, D.A. Anderson, Pothole repair: you can't afford not to do it right, Transportation  
26 1315 Research Record 1102 (1986) 32-40.
- 27 1316 [50] K. Smith, D. Peshkin, E. Rmeili, T. Vandam, K. Smith, Innovative materials and equipment for  
28 1317 pavement surface repairs. Volume 1: Summary of material performance and experimental plans, Report  
29 1318 No. SHRP-M/UFR-91-504, Strategic Highway Research Program (SHRP), hington, D.C., 1991.
- 30 1319 [51] Q. Dong, C. Dong, B. Huang, Statistical analyses of field serviceability of throw-and-roll pothole  
31 1320 patches, Journal of Transportation Engineering 141(9) (2015) 04015017.  
32 1321 [https://doi.org/10.1061/\(ASCE\)TE.1943-5436.0000786](https://doi.org/10.1061/(ASCE)TE.1943-5436.0000786)
- 33 1322 [52] G. Jennings, Spray injection pothole filling, AHMCT Research Center, University of California-  
34 1323 Davis, 2013.
- 35 1324 [53] S. Biswas, L. Hashemian, M. Hasanuzzaman, A. Bayat, A study on pothole repair in Canada  
36 1325 through questionnaire survey and laboratory evaluation of patching materials, Canadian Journal of Civil  
37 1326 Engineering 43(5) (2016) 443-450. <https://doi.org/10.1139/cjce-2015-0553>
- 38 1327 [54] J. Davis, Preventing and repairing potholes and pavement cracks.  
39 1328 <http://asphaltmagazine.com/preventing-and-repairing-potholes-and-pavement-cracks/>, (May 2021).
- 40 1329 [55] L. Uzarowski, V. Henderson, M. Henderson, B. Kiesswetter, Innovative infrared crack repair  
41 1330 method, Maintenance and Construction Session: Successes and Innovations in Maintenance Methods  
42 1331 of the 2011 Annual Conference of the Transportation Association of Canada, Edmonton, Alberta, 2011.
- 43 1332 [56] J. Byzyka, M. Rahman, D.A. Chamberlain, An innovative asphalt patch repair pre-heating method  
44 1333 using dynamic heating, Construction and Building Materials 188 (2018) 178-197.  
45 1334 <https://doi.org/10.1016/j.conbuildmat.2018.08.086>
- 46 1335 [57] L. M Zanko, D. M Hopstock, Taconite-enhanced pothole repair using portable microwave  
47 1336 technology, University of Minnesota Duluth Natural Resources Research Institute (NRRI), 2011.
- 48 1337 [58] J. Byzyka, D.A. Chamberlain, M. Rahman, A novel control pothole repair system using radiant  
49 1338 heat for long lasting patch repairs, Transportation Research Board 96th Annual Meeting, Washington  
50 1339 DC, United States, 2017.
- 51 1340 [59] J.M. Fragachan, Accelerated testing methodology for evaluating pavement patching materials,  
52 1341 Thesis for the Degree of Master of Science in Civil Engineering, Worcester Polytechnic Institute, 2007.

- 1342 [60] Q. Dong, J. Yuan, X. Chen, X. Ma, Reduction of moisture susceptibility of cold asphalt mixture  
 1 1343 with Portland cement and bentonite nanoclay additives, *Journal of Cleaner Production* 176(6) (2018)  
 2 1344 320-328. DOI:10.1016/J.JCLEPRO.2017.12.163
- 3 1345 [61] G. Indahl, J. Quinn, K. Afferton, Pavement patching techniques and materials, New Jersey  
 4 1346 Department of Transportation, 1975.
- 5 1347 [62] M. Berlin, E. Hunt, Asphalt concrete patching material evaluation: interim report, Report No. OR-  
 6 1348 RD-01-19, Oregon. Dept. of Transportation, Research Unit, 2001.
- 8 1349 [63] Q. Dong, J. Gao, X. Chen, X. Wang, Development of a turpentine cutback asphalt mixture for  
 9 1350 porous pavement pothole repair, *Journal of Materials in Civil Engineering* 32(3) (2020) 05020001.  
 10 1351 [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003075](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003075)
- 11 1352 [64] H. Obaidi, B. Gomez-Meijide, A. Garcia, A fast pothole repair method using asphalt tiles and  
 12 1353 induction heating, *Construction and Building Materials* 131 (2017) 592-599.  
 13 1354 <https://doi.org/10.1016/j.conbuildmat.2016.11.099>
- 14 1355 [65] Y. Yang, Z. Qian, X. Song, A pothole patching material for epoxy asphalt pavement on steel  
 15 1356 bridges: Fatigue test and numerical analysis, *Construction and Building Materials* 94(7) (2015) 299-  
 16 1357 305. DOI: 10.1016/j.conbuildmat.2015.07.017
- 18 1358 [66] I. Thanaya, S. Zoorob, J. Forth, A laboratory study on cold-mix, cold-lay emulsion mixtures,  
 19 1359 *Proceedings of the Institution of Civil Engineers-Transport*, Thomas Telford Ltd. (2009) 47-55.
- 20 1360 [67] S. Al-Busaltan, H. Al Nageim, W. Atherton, G. Sharples, Mechanical properties of an upgrading  
 21 1361 cold-mix asphalt using waste materials, *Journal of materials in civil engineering* 24(12) (2012) 1484-  
 22 1362 1491. [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0000540](https://doi.org/10.1061/(ASCE)MT.1943-5533.0000540)
- 23 1363 [68] A. Stanley, Value engineering study of highway shoulder maintenance, Report No.FHWA-TS-77-  
 24 1364 210, Washington Department of Transportation, Federal Highway Administration, 1977.
- 25 1365 [69] Q. Dong, B. Huang, X. Jia, Long-term cost-effectiveness of asphalt pavement pothole patching  
 26 1366 methods, *Transportation Research Record* 2431(1) (2014) 49-56. <https://doi.org/10.3141/2431-07>
- 28 1367 [70] K. Kubanek, Guidelines for pothole repairs (Annex of Final Report of the project "POTHOLE"),  
 29 1368 Project No. 832700, Karlsruhe Institute of Technology, 2013.
- 30 1369 [71] W.H. Kao, L. Carlson, J.-M. Yang, J.-W.W. Ju, Application of high toughness, low viscosity nano-  
 31 1370 molecular resin for reinforcing pothole patching materials in asphalt and concrete base pavement, Patent  
 32 1371 No. US 9328024B2, University of California, Oakland, CA (US), 2016.
- 33 1372 [72] P.S. Kandhal, D.B. Mellott, Rational approach to design of bituminous stockpile patching mixtures,  
 34 1373 *Transportation Research Record* 821 (1981) 16-22.
- 35 1374 [73] L. Hammel, Reparatur asphalte – Stand der Technik und aktuelle Entwicklungen, Thesis for the  
 36 1375 degree of Doctor of Philosophy, TU Dresden, 2015.
- 38 1376 [74] H.R. Thomas, D.A. Anderson, Evaluation of experimental cold-stockpiled patching materials for  
 39 1377 repairs in cold and wet weather, *Transportation Research Record* 1268 (1990).
- 40 1378 [75] C. Wei, S. Tighe, Development of preventive maintenance decision trees based on cost-  
 41 1379 effectiveness analysis: an Ontario case study, *Transportation research record* 1866(1) (2004) 9-19.  
 42 1380 <https://doi.org/10.3141/1866-02>
- 43 1381 [76] D. Bennett, S.A. Velinsky, Continued evaluation of pothole patching equipment, materials, and  
 44 1382 processes, Report No. CA14-2338, California. Department of Transportation, 2014.
- 45 1383 [77] L. O'Brien, Value engineering study of bituminous patching, Rural and Urban Roads, Washington  
 46 1384 D.C., 1976.
- 48 1385 [78] V. Rosales, J. Prozzi, J. Prozzi, Mixture design and performance-based specifications for cold  
 49 1386 patching mixtures, Report No. FHWA/TX-08/0-4872-2, The University of Texas at Austin, Center for  
 50 1387 Transportation Research, 2007.
- 51 1388 [79] M. Rezaei, L. Hashemian, A. Bayat, B. Huculak, Investigation of rutting resistance and moisture  
 52 1389 damage of cold asphalt mixes, *Journal of Materials in Civil Engineering* 29(10) (2017) 04017193.  
 53 1390 [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0002042](https://doi.org/10.1061/(ASCE)MT.1943-5533.0002042)
- 54 1391 [80] Anonymous, Recycled asphalt shingles - Material description. <https://rmrc.wisc.edu/ug-mat-roofing-shingle-scraper/>. (Accessed May 2021).
- 56 1392 [81] M. Pasetto, E. Pasquini, A. Baliello, Recycling bituminous shingles in cold mix asphalt for high  
 57 1393 performance patching repair of road pavements, *Pavement and Asset Management* (2019) 627-634.  
 58 1394 DOI: 10.1201/9780429264702-75  
 59 1395

- 1396 [82] C.K. Estakhri, J.W. Button, Test methods for evaluation of cold-applied bituminous patching  
1 1397 mixtures, Transportation research record 1590(1) (1997) 10-16. <https://doi.org/10.3141/1590-02>
- 2 1398 [83] M.-C. Liao, C.-C. Luo, T.-Y. Wang, X. Xie, Developing effective test methods for evaluating cold-  
3 1399 mix asphalt patching materials, Journal of Materials in Civil Engineering 28(10) (2016) 04016108.  
4 1400 [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0001639](https://doi.org/10.1061/(ASCE)MT.1943-5533.0001639)
- 5 1401 [84] J.-M. Torrenti, F. La Torre, Materials and infrastructures 1, Research for innovative transports set  
6 1402 Wiley, Great Britain and the United States, 2016.
- 7 1403 [85] P. Redelius, J.-A. Östlund, H. Soenen, Field experience of cold mix asphalt during 15 years, Road  
8 1404 Materials and Pavement Design 17(1) (2016) 223-242.  
9 1405 <https://doi.org/10.1080/14680629.2015.1068702>
- 11 1406 [86] H. Moriyasu, H. Taniguchi, K. Koshi, K. Hatakeyama, Development of water-based curing  
12 1407 reactive cold asphalt repair material, Asphalt Pavements 1 (2015) 343-353.  
13 1408 <https://doi.org/10.1201/b17219>
- 14 1409 [87] H.P. Wang, R. Zhang, Z.Y. He, J.Z. Wang, Deformation behaviors of dilution type cold patch  
15 1410 asphalt mixture under different stress modes, Applied Mechanics and Materials (2017) 114-118.  
16 1411 <https://doi.org/10.4028/www.scientific.net/AMM.872.114>
- 18 1412 [88] I. Gawel, J. Pilat, P. Radziszewski, L. Niczke, J. Krol, M. Sarnowski, Bitumen fluxes of vegetable  
19 1413 origin, Polimery 55(1) (2010). DOI: 10.14314/polimery.2010.055
- 20 1414 [89] J.-P. Serfass, J.-E. Poirier, J.-P. Henrat, X. Carbonneau, Influence of curing on cold mix mechanical  
21 1415 performance, Materials and structures 37(5) (2004) 365-368. <https://doi.org/10.1007/BF02481685>
- 22 1416 [90] I.N.A. Thanaya, Review and recommendation of cold asphalt emulsion mixtures CAEMS design,  
23 1417 Civil Engineering Dimension 9(1) (2007) 49-56. <https://doi.org/10.9744/ced.9.1.pp.%2049-56>
- 24 1418 [91] X. Wang, X. Chen, Q. Dong, A. Jahanzaib, Material properties of porous asphalt pavement cold  
25 1419 patch mixtures with different solvents, Journal of Materials in Civil Engineering 32(10) (2020)  
26 1420 06020015. [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0003399](https://doi.org/10.1061/(ASCE)MT.1943-5533.0003399)
- 27 1421 [92] Z. Zhang, S. Wang, G. Lu, Properties of new cold patch asphalt liquid and mixture modified with  
28 1422 waterborne epoxy resin, International Journal of Pavement Engineering (2018) 1-11.  
29 1423 <https://doi.org/10.1080/10298436.2018.1559314>
- 30 1424 [93] S.C. Somé, V. Gaudefroy, D. Delaunay, Effect of vegetable oil additives on binder and mix  
31 1425 properties: laboratory and field investigation, Materials and structures 49(6) (2016) 2197-2208.  
32 1426 <https://doi.org/10.1617/s11527-015-0643-1>
- 33 1427 [94] C.K. Estakhri, L.M. Jimenez, J.W. Button, Evaluation of Texas DOT Item 334, hot-mix, cold-laid  
34 1428 asphalt concrete paving mixtures, Report No. FHWA/TX-00/1717-1, Texas Transportation Institute,  
35 1429 Texas A & M University System, 1999.
- 36 1430 [95] B.J. Kwon, D. Kim, S.K. Rhee, Y.R. Kim, Spray injection patching for pothole repair using 100  
37 1431 percent reclaimed asphalt pavement, Construction and Building Materials 166 (2018) 445-451.  
38 1432 <https://doi.org/10.1016/j.conbuildmat.2018.01.145>
- 39 1433 [96] S. Lavorato, S. Manolis, G. Vasiliu, et al. , Evaluation of laboratory and field performance of high  
40 1434 performance cold mix patching material with reduced volatile organic compound content, Proceedings  
41 1435 of the Fifty-Eighth Annual Conference of the Canadian Technical Asphalt Association (CTAA), St.  
42 1436 John's, Newfoundland and Labrador (2013) 177-205.
- 43 1437 [97] K.P. Chong, Health monitoring of civil structures, Journal of Intelligent Material Systems and  
44 1438 Structures 9(11) (1998) 892-898. <https://doi.org/10.1177/1045389X9800901104>
- 45 1439 [98] M. Mejias-Santiago, F.d. Valle-Roldan, L.P. Priddy, Certification tests on cold patch asphalt repair  
46 1440 materials for use in airfield pavements, Report No. ERDC/GSL TR-10-14, Vicksburg Engineer  
47 1441 Research and Development Center, 2010.
- 48 1442 [99] C.-W. Huang, T.-H. Yang, G.-B. Lin, The evaluation of short-and long-term performance of cold-  
49 1443 mix asphalt patching materials, Advances in Materials Science and Engineering 2020 (2020).  
50 1444 <https://doi.org/10.1155/2020/8968951>
- 51 1445 [100] M. Liu, S. Han, X. Han, X. Qi, S. Dong, Microcapsule and polymer reinforcement techniques  
52 1446 developed asphalt for use of pothole repairs in winter and rainy seasons, Cold Regions Science and  
53 1447 Technology 167 (2019) 102865. <https://doi.org/10.1016/j.coldregions.2019.102865>
- 54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65