



UNIVERSITÀ DI PARMA

ARCHIVIO DELLA RICERCA

University of Parma Research Repository

Photoelectron Holographic Study for Atomic Site Occupancy for Si Dopants in Si-Doped κ -Ga₂O₃(001)

This is the peer reviewed version of the following article:

Original

Photoelectron Holographic Study for Atomic Site Occupancy for Si Dopants in Si-Doped κ -Ga₂O₃(001) / Tsai, Yuhua; Hashimoto, Yusuke; Sun, Zexu; Moriki, Takuya; Tadamura, Takashi; Nagata, Takahiro; Mazzolini, Piero; Parisini, Antonella; Bosi, Matteo; Seravalli, Luca; Matsushita, Tomohiro; Yamashita, Yoshiyuki. - In: NANO LETTERS. - ISSN 1530-6984. - 24:(2024), pp. 3978-3985. [10.1021/acs.nanolett.4c00482]

Availability:

This version is available at: 11381/2973476 since: 2024-11-13T19:08:22Z

Publisher:

ACS Publications

Published

DOI:10.1021/acs.nanolett.4c00482

Terms of use:

Anyone can freely access the full text of works made available as "Open Access". Works made available

Publisher copyright

note finali coverpage

(Article begins on next page)

02 May 2026

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

**Photoelectron holographic study for atomic sites occupancy
for Si dopant in Si-doped κ -Ga₂O₃(001)**

Journal:	<i>Nano Letters</i>
Manuscript ID	nl-2024-00482p.R1
Manuscript Type:	Communication
Date Submitted by the Author:	15-Feb-2024
Complete List of Authors:	<p>Tsai, Yuhua; National Institute for Materials Science; Kyushu University Faculty of Engineering Graduate School of Engineering Department of Applied Chemistry Hashimoto, Yusuke ; Nara Institute of Science and Technology, Graduate School of Science and Technology Sun, Zexu; Nara Institute of Science and Technology, Graduate School of Science and Technology Moriki, Takuya; Nara Institute of Science and Technology Tadamura, Takashi; Nara Institute of Science and Technology Nagata, Takahiro; National Institute for Materials Science Mazzolini, Piero; University of Parma; IMEM CNR Parisini, Antonella; Universita degli Studi di Parma Dipartimento di Fisica e Scienze della Terra Macedonio Melloni, Bosi, Matteo; IMEM CNR Seravalli, Luca; Istituto dei Materiali per l'Elettronica ed il Magnetismo Consiglio Nazionale delle Ricerche, Matsushita, Tomohiro ; Nara Institute of Science and Technology, Graduate School of Science and Technology Yamashita, Yoshiyuki; National Institute for Materials Science; Kyushu University Faculty of Engineering Graduate School of Engineering Department of Applied Chemistry</p>

SCHOLARONE™
Manuscripts

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Photoelectron holographic study for atomic sites occupancy for Si dopant in Si-doped κ -Ga₂O₃(001)

Yuhua Tsai,^{1,2} Yusuke Hashimoto,³ ZeXu Sun,³ Takuya Moriki,³ Takashi
Tadamura,³ Takahiro Nagata,¹ Piero Mazzolini,^{4,5} Antonella Parisini,⁴
Matteo Bosi,⁵ Luca Seravalli,⁵ Tomohiro Matsushita,³ and Yoshiyuki
Yamashita^{1,2,*}

¹National Institute for Materials Science, Tsukuba, Ibaraki 305-0044, Japan

²Department of Applied Chemistry, Faculty of Engineering, Kyushu University,
Fukuoka 819-0395, Japan

³Nara Institute of Science and Technology, Ikoma, Nara 630-0192, Japan

⁴Department of Mathematical Physical and Computer Sciences, University of Parma,
Parco Area delle Scienze 7/A, 43124 Parma, Italy

⁵IMEM-CNR, Parco Area delle Scienze 37/A, 43124 Parma, Italy

KEYWORDS: Ga₂O₃, κ -Ga₂O₃, Si-doped κ -Ga₂O₃, photoelectron holography.

*E-mail: YAMASHITA.Yoshiyuki@nims.go.jp

Abstract

We investigated atomic sites occupancy for the Si dopant in Si-doped κ -
Ga₂O₃(001) using photoelectron spectroscopy (PES) and photoelectron holography
(PEH). From PES and PEH, we found that the Si dopant had one chemical state and three

1
2
3
4
5
6 types of inequivalent Si substitutional sites (Si_{Ga}) were formed. The ratios for the
7
8
9 inequivalent tetrahedral, pentahedral, and octahedral Si_{Ga} sites were estimated to be
10
11
12 55.0%, 28.1%, and 16.9%, respectively. Higher (lower) ratios for the three inequivalent
13
14
15 Si_{Ga} sites may come from lower (higher) formation energy. The Tetra (Octa) Si_{Ga} site has
16
17
18 the highest (lowest) ratio of the three Si_{Ga} sites since it has the lowest (highest) formation
19
20
21 energy. We suggest that the tetrahedral Si_{Ga} site is due to the active dopant site, whereas
22
23
24 the pentahedral and octahedral Si_{Ga} sites can be attributed to the inactive dopant sites for
25
26
27 the Si-doped $\kappa\text{-Ga}_2\text{O}_3(001)$.
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Introduction

In recent years, gallium oxide (Ga_2O_3) has attracted considerable interest as an ultra-wide bandgap semiconductor because of a bandgap of around 5 eV, high thermal stability, and the availability of large-scale $\beta\text{-Ga}_2\text{O}_3$ single crystal wafers. Such superior Ga_2O_3 properties can apply to the field of power electronics.¹⁻⁷ For Ga_2O_3 , there are five crystal polymorphs: α -, β -, δ -, γ -, and $\kappa\text{-Ga}_2\text{O}_3$.^{3,4} Among them, the most thermodynamically stable is $\beta\text{-Ga}_2\text{O}_3$, which has been widely investigated.⁶⁻⁹

Recently, the orthorhombic $\kappa\text{-Ga}_2\text{O}_3$ polymorph is gaining attention due to its higher symmetry with respect to monoclinic structure, its large spontaneous polarization along the (001) direction, and its ferroelectricity.¹⁰⁻¹³ According to previous studies, this structure can be synthesized by several chemical- and physical-vapor phase epitaxial techniques (e.g., metal-organic vapor phase epitaxy MOVPE, halide vapor phase epitaxy, molecular beam epitaxy, and pulsed laser deposition) on various substrates.¹⁴ Among them, c-plane sapphire has been so far the most frequently used substrate for $\kappa\text{-Ga}_2\text{O}_3$ epitaxy.^{7,15-18} The $\kappa\text{-Ga}_2\text{O}_3$ structure is shown in Figure 1(a). There are three inequivalent Ga atomic sites in $\kappa\text{-Ga}_2\text{O}_3$: octahedral (Octa), pentahedral (Penta), and tetrahedral (Tetra).^{11,19}

For $\kappa\text{-Ga}_2\text{O}_3$, both Si and Sn have been experimentally found to be extrinsic

1
2
3
4
5
6 donors.^{7,11,16,20,21} According to electron paramagnetic resonance (EPR), Si is suggested to
7
8
9 be an effective mass donor when it is positioned as a substitutional of Ga (Si_{Ga}) in the
10
11 tetrahedral site of the orthorhombic $\kappa\text{-Ga}_2\text{O}_3$ lattice.¹⁶ Nonetheless, despite the possible
12
13 incorporation of Si at cation concentrations that might exceed 1% in the metal-organic
14
15 vapor phase deposited (MOVPE) layers, the reported Hall-measured charge carrier
16
17 density n never exceeded the mid 10^{18} cm^{-3} range.⁷ This net donor density concentration
18
19 range was independently confirmed by capacitance-voltage measurements performed in
20
21 Schottky diodes based on Si-doped $\kappa\text{-Ga}_2\text{O}_3$.²²
22
23
24
25
26
27
28
29

30 In this framework, the following could all play an important role in the resulting
31
32 Si dopant activation efficiency in $\kappa\text{-Ga}_2\text{O}_3$:⁷ (i) the presence of a large concentration of
33
34 extended defects (*i.e.*, rotational domain boundaries and plane defects), (ii) the possible
35
36 occupation of different reticular Ga sites, and (iii) the presence of a large amount of
37
38 compensating defects (deep level acceptors). In particular for point (i) and (iii), the (001)-
39
40 oriented heteroepitaxy of $\kappa\text{-Ga}_2\text{O}_3$ on various substrates [*e.g.*, c-plane sapphire, (0001)-
41
42 GaN, (111)-MgO]¹⁴ results in the formation of large density of structural defects that are
43
44 mostly perfectly vertically oriented, *i.e.*, $3 \times 120^\circ$ rotated domains and anti-phase
45
46 boundaries.^{7,23,24} According to the recent work of Vyvenko *et al.*, these vertically oriented
47
48 structural defects could be electrically charged.²⁴ We believe that the discrepancy
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4
5
6 between the detected level of incorporated Si in the κ -Ga₂O₃ matrix and the net doping
7
8
9 level is in line with a high level of compensation that can be largely induced by such
10
11
12 vertically oriented structural defects. A similar picture of large charge carrier
13
14
15 compensation related to charged structural defects has been reported and modelled in the
16
17
18 case of defective β -Ga₂O₃ layers by Fiedler *et al.*²⁵ In this work, we describe the first
19
20
21 experimental confirmation that the Si impurities incorporated in κ -Ga₂O₃ lattice sites
22
23
24 substitute Ga (target point (ii)), particularly to experimentally clarify the respective
25
26
27 fraction of different reticular Ga sites that are actually occupied by Si (Si_{Ga}), possibly
28
29
30 causing active and inactive dopant in Si-doped κ -Ga₂O₃ thin films.
31

32
33 We employed photoelectron holography (PEH) to clarify the Si dopant site for
34
35
36 the Si-doped κ -Ga₂O₃. In the PEH, the photoelectrons of the target atoms (*e.g.*, dopants)
37
38
39 are excited as the emitter under photoirradiation and scattered by the surrounding atoms.
40
41
42 Finally, interference patterns are formed in the core-level photoelectron angular
43
44
45 distribution. PEH has a great advantage in which non-periodic atomic structures are
46
47
48 applicable. Additionally, since PEH is based on photoelectron spectroscopy, chemical
49
50
51 state-discriminated PEHs can be achieved.²⁶⁻²⁹ Therefore, we can clarify the atomic
52
53
54 structures and the chemical states of the Si dopants in κ -Ga₂O₃. The PEH schematic is
55
56
57 shown in Figure 1(b).
58
59
60

1
2
3
4
5
6 We also performed PEH simulations for the atomic position of the Si dopants in
7 κ -Ga₂O₃ to clarify the Si dopant sites. Since the structure around the dopant atom should
8
9 be relaxed as the dopant is introduced into κ -Ga₂O₃, the bond length around the dopant
10
11 atom may be different from the length before the dopant introduction. Thus, we performed
12
13 extended x-ray absorption fine structure (EXAFS) to estimate the bond length after the
14
15 dopant introduction. PEH simulations were done using the bond length after introducing
16
17 the dopant. In the present study, we investigated the atomic position of the Si dopant for
18
19 Si-doped κ -Ga₂O₃ using PEH to clarify the atomic structures of the active and inactive Si
20
21 dopants for the Si-doped κ -Ga₂O₃.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

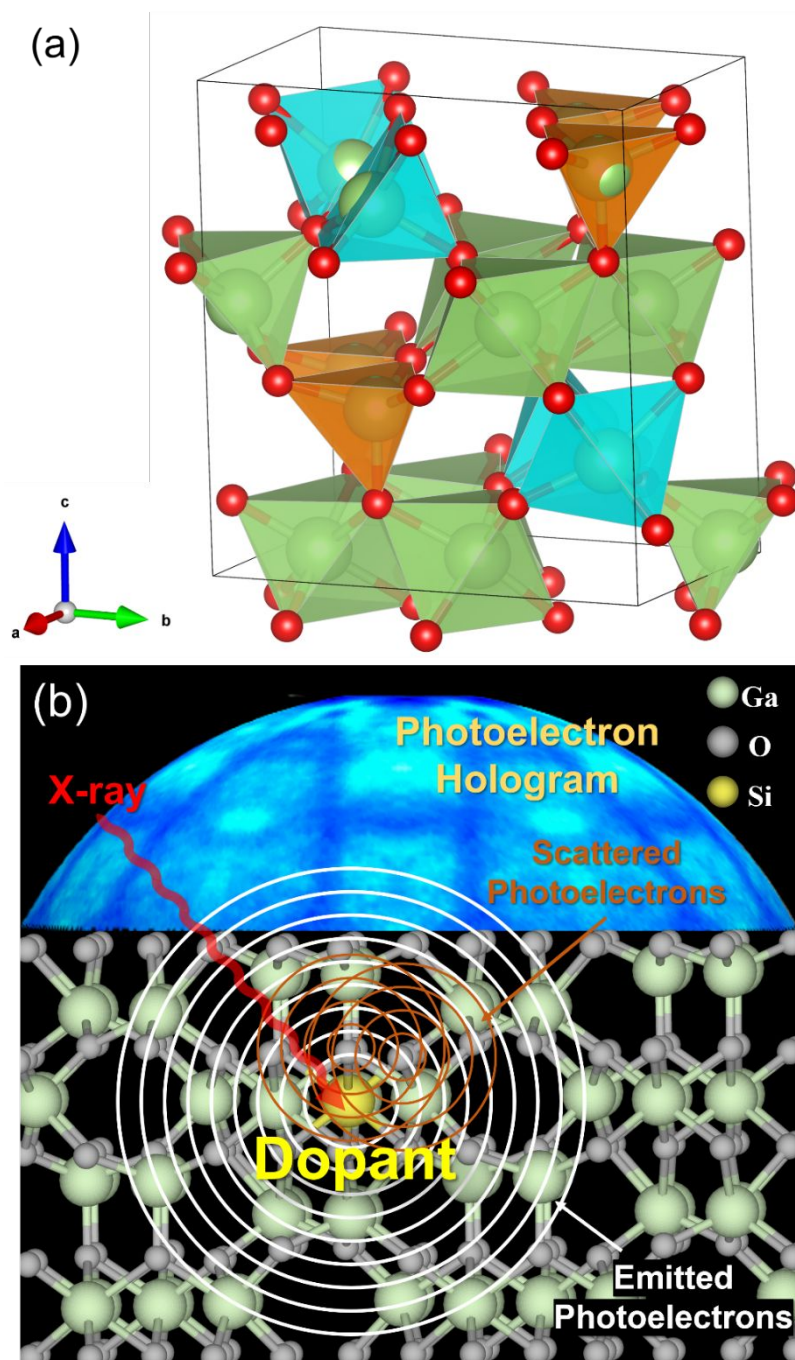


Figure 1. (a) Unit cell of κ - Ga_2O_3 : Green, blue, and brown polyhedrons represent Octa, Penta, and Tetra Ga sites. (b) PEH schematic for Si-doped κ - Ga_2O_3 . Yellow, green, and gray balls represent Si, Ga, and O atoms.

Experimental

1
2
3
4
5
6
7 A κ -Ga₂O₃ epitaxial layer was grown on a c-plane sapphire substrate with
8
9 MOVPE. Trimethylgallium and ultrapure H₂O were used as a metal precursor and an
10
11 oxidizing gas. H₂ was used as the gas carrier. The reaction was carried out at a H₂ pressure
12
13 of 60 mbar in the growth chamber with a substrate temperature of 610°C. A H₂-diluted
14
15 mixture of 0.05% SiH₄ was employed as the Si dopant source. Using a SiH₄ flow of 15
16
17 standard cubic centimeters per minute resulted in a Si concentration of 1.02 cation % in
18
19 the κ -Ga₂O₃ layer (determined by atom probe tomography, which is the same sample that
20
21 was previously investigated.) evenly distributed in the analyzed film volume.⁷ The
22
23 dopant's carrier concentration was experimentally determined by Hall effect
24
25 measurements to be $2.6 \times 10^{18} \text{ cm}^{-3}$ where the electronic transport was dominated by a
26
27 hopping mechanism (further details on the electrical characterization of the very same
28
29 sample are available.).⁷ Before PES and PEH measurements, the substrates were cleaned
30
31 by the RCA method so that surface contaminations were removed. Then the surface oxide
32
33 layer and the particles were removed by concentrated hydrochloric acid for 1 min.,
34
35 followed by washing with deionized water.
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50

51 X-ray photoelectron spectroscopy (XPS) and hard x-ray photoelectron
52
53 spectroscopy (HAXPES) measurements were performed using PHI Quantes (ULVAC-
54
55 PHI). Monochromatic Al K α (1486.6 eV) and Cr K α (5414.9 eV) were used as incident
56
57
58
59
60

1
2
3
4
5
6 x-rays sources for the XPS and HAXPES. The take-off angle (TOA) was 90° (surface
7 normal). We employed the pass energies of 55 and 112 eV for XPS and HAXPES
8 measurements, respectively. The energy resolutions for XPS and HAXPES
9 measurements were estimated to be 0.51 and 1.11 eV, respectively. The total energy
10 resolutions were estimated by measuring the Fermi level of Au polycrystalline sample.
11 We used KolXPD software to perform the XPS and HAXPES peaks fitting.³⁰ We used
12 Voight function (convolution of Lorentzian and Gaussian functions) for peaks fitting after
13 removal of the background of the Shirley function.³¹⁻³³
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29

30 PEH measurements were performed at BL25SU at SPring-8. We used a retarding
31 field analyzer (RFA) for PEH measurements. The RFA energy resolution was
32 approximately 0.5 eV.³⁴⁻³⁶ RFA's acceptance angle was approximately $\pm 49^\circ$, and the
33 angular resolution was 0.5° .³⁶ The base pressure of the main chamber was 2.8×10^{-8} Pa.
34 PEH simulations were performed using 3D-AIR-IMAGE software (version 1.1.09). The
35 total analysis multiple scattering pattern simulation code was included in the software.³⁷⁻⁴⁰
36 For the simulations, we employed an electron kinetic energy of 800 eV, a temperature of
37 300 K, and an inelastic mean free path of 10 Å.
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53

54 The EXAFS measurements were carried out at the BL6N1 in the Aichi
55 Synchrotron Radiation Center. The base pressure of the main chamber was 3.1×10^{-7} Pa.
56
57
58
59
60

1
2
3
4
5
6 The spot-size of the incident photon at the sample position was 2.0 mm × 1.0 mm
7
8
9 (horizontal × vertical). A SPECS PHOIBOS 150 was used as an electron analyzer.⁴¹ The
10
11
12 pass energy was set to 20 eV. The angle between the incident photon and the sample
13
14
15 surface normal was 55°. The TOA was set to 90° (surface normal).^{42,43} For the EXAFS
16
17
18 measurements, the total electron yield was employed. The energy range for the EXAFS
19
20
21 measurements was from 1800 to 2100 eV with 1.0-eV energy steps.
22
23
24
25
26

27 Results and discussion

28
29
30 Figure 2 shows the XPS and HAXPES spectra for the Si-doped κ -Ga₂O₃(001).
31
32
33 In the Ga 2*p* XPS spectrum (Figure 2(a)), the peak at 1119.0 eV is attributed to the Ga-O
34
35
36 species.⁴⁴⁻⁴⁶ In the Si 1*s* HAXPES spectrum (Figure 2(b)), the peak at 1843.5 eV is due
37
38
39 to the Si-O species.^{47,48} When the different Si oxidation states (from 1⁺ to 4⁺) exist, the
40
41
42 corresponding peaks appear at lower binding energy position from 1 to 3 eV (depend on
43
44
45 the oxidation states),^{49,50} forming an asymmetric peak structure. However, the Si 1*s*
46
47
48 HAXPES spectrum shows a symmetric peak structure. Therefore, we can exclude the
49
50
51 possibility of the presence of the different Si oxidation states. Thus, the chemical state of
52
53
54 the Ga and Si atoms shows one chemical component. Since Si 1*s* shows one chemical
55
56
57 species, the Si atom in the Si-O species may be due to the Si dopants.
58
59
60

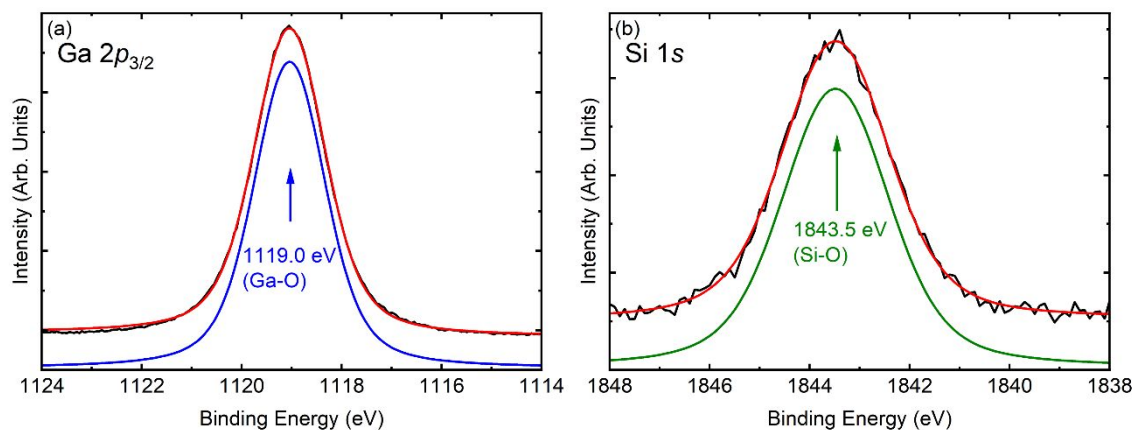


Figure 2. (a) Ga $2p_{3/2}$ XPS (b) Si $1s$ HAXPES spectra measured at photon energies of 1486.6 eV (XPS) and 5414.9 eV (HAXPES), respectively.

Figure 3(a) shows the Ga $3p$ and Si $2p$ PES spectrum for the Si-doped κ -Ga₂O₃(001) measured at an incident photon energy of 911 eV. For them, spin-orbit splitting of 3.46 eV and 0.60 eV was employed for the peaks fitting.⁵¹⁻⁵⁴ The corresponding PEHs for Ga $3p$ and Si $2p$ are shown in Figures. 3(b) and (c). The Si $2p$ PEH shows clear patterns, indicating that the Si dopant may be located at the atomic positions of κ -Ga₂O₃(001).

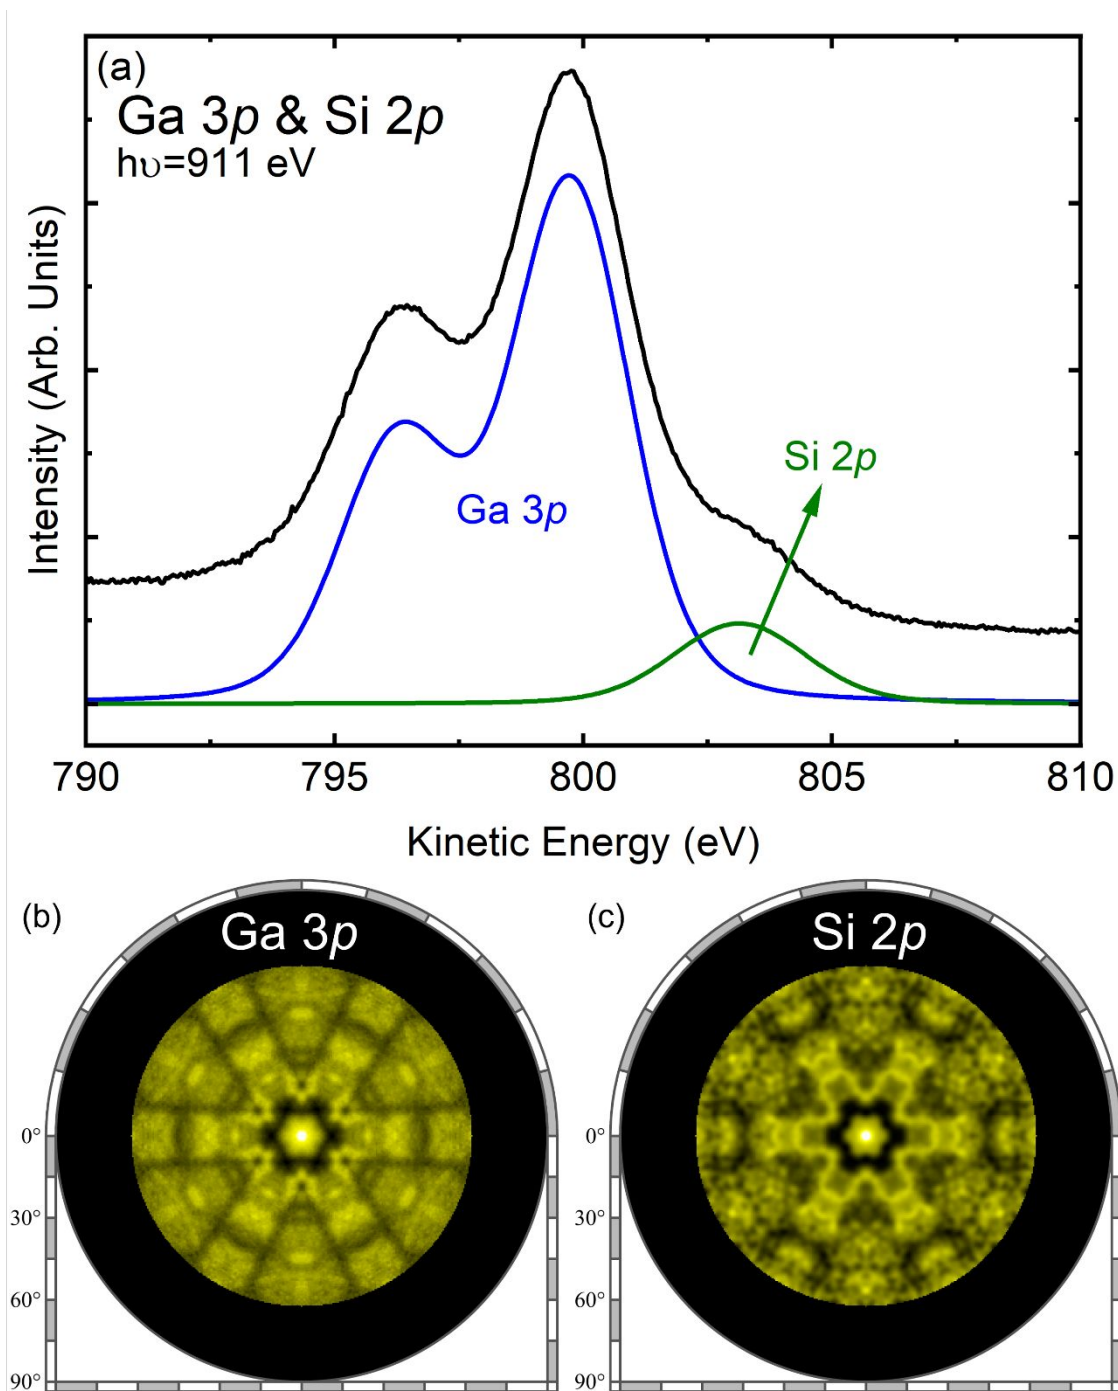


Figure 3. (a) Ga 3p and Si 2p PES spectrum for Si-doped κ -Ga₂O₃(001). PEHs of (b) Ga 3p and (c) Si 2p for Si-doped κ -Ga₂O₃(001).

Figures 4(a) and (b) show the EXAFS and the oscillation for the Si-doped κ -Ga₂O₃(001). Fig. 4(c) shows k^2 -weighted Si *K*-edge EXAFS spectrum plotted with the

1
2
3
4
5
6 fitting result for Si-doped κ -Ga₂O₃(001). The fitting range in k-space was chosen at 2–
7
8
9 7.2 Å⁻¹ with a good signal-to-noise ratio. Fig. 4(d) shows the radial distribution function
10
11
12 of the k²-weighted EXAFS and the fitting result of the Octa Si_{Ga} site as an example. The
13
14
15 fitting was performed using ARTEMIS software, and the reliable factor was set to
16
17
18 0.015.^{55,56} The nearest Si-O distance was estimated to be 2.01 Å, a value shorter than the
19
20
21 Ga-O bond length of 2.02 Å observed for the non-doped κ -Ga₂O₃ Octa site.²³
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

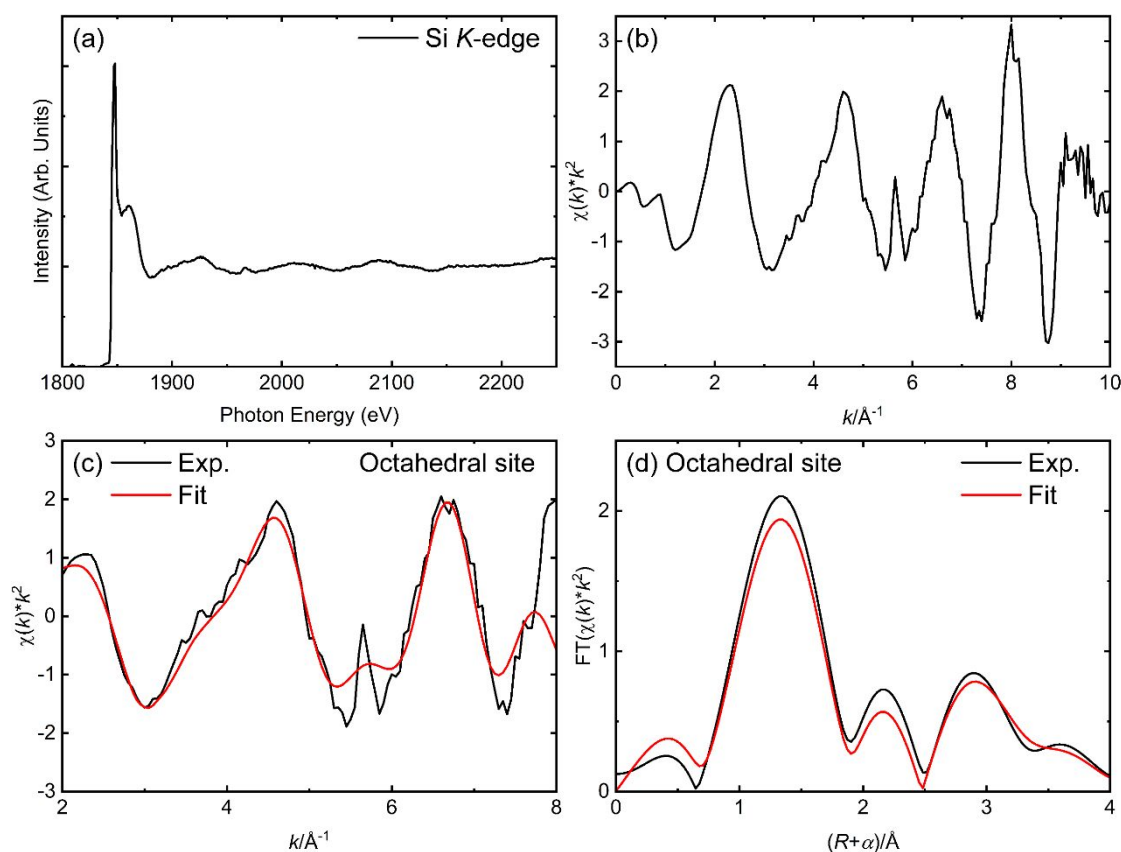


Figure 4. (a) Si *K*-edge EXAFS and (b) k^2 -weighted Si *K*-edge EXAFS for Si-doped κ - $\text{Ga}_2\text{O}_3(001)$. (c) k^2 -weighted Si *K*-edge EXAFS spectrum (black solid line) plotted with best fit (red solid line) for Si-doped κ - $\text{Ga}_2\text{O}_3(001)$ sample. The fitting range was 2–7.2 \AA^{-1} . (d) Radial distribution function of the k^2 -weighted EXAFS (black solid line) and the fitting results (red solid line) for Si_{Ga} in Octa site. The fitting range was 1–4 \AA . The amplitude reduction factors, ΔR , and MSRD values were set to 1, -0.011 \AA , and 0.015, respectively.

We also performed fitting for the other Si_{Ga} sites in κ - Ga_2O_3 (Figure S2). The first nearest Si-O distance was estimated to be 2.02 \AA and 1.83 \AA for the Penta and Tetra Si_{Ga} sites. We performed PEH simulations based on the bond length obtained from EXAFS. This is because when the dopants are introduced to the sample, the bond length should be changed around the dopant atom. Thus, we have to use the bond lengths around the Si dopant atom obtained from EXAFS.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

According to previous studies, dopant atomic positions are Ga replaced by Si, that is, Si_{Ga} in κ -Ga₂O₃.^{7,20} Therefore, PEH simulations were performed for the Octa, Penta, and Tetra Si_{Ga} sites. Figure 5 shows the experimental and simulated Si 2*p* PEHs for the Octa, Penta, and Tetra Si_{Ga} sites. Not every simulated PEH for the respective Octa, Penta, and Tetra Si_{Ga} sites explains the experimental Si 2*p* PEH, indicating that the Si dopant sites may be due to the mixture of inequivalent Si_{Ga} sites.

To determine the dopant site ratio for the Si-doped κ -Ga₂O₃, we mixed the simulated Si 2*p* PEHs of the Tetra, Penta, and Octa Si_{Ga} sites. The simulated PEH with the three inequivalent Si_{Ga} site ratios is shown in Figure 5(d). The best fit for the experimental PEH data was obtained using the ratios for Tetra, Penta, and Octa Si_{Ga} sites of 55.0%, 28.1%, and 16.9%, respectively. Note that the occupancy ratios of the Tetra, Penta, and Octa Si_{Ga} sites were estimated using the equations shown in Supporting Information.

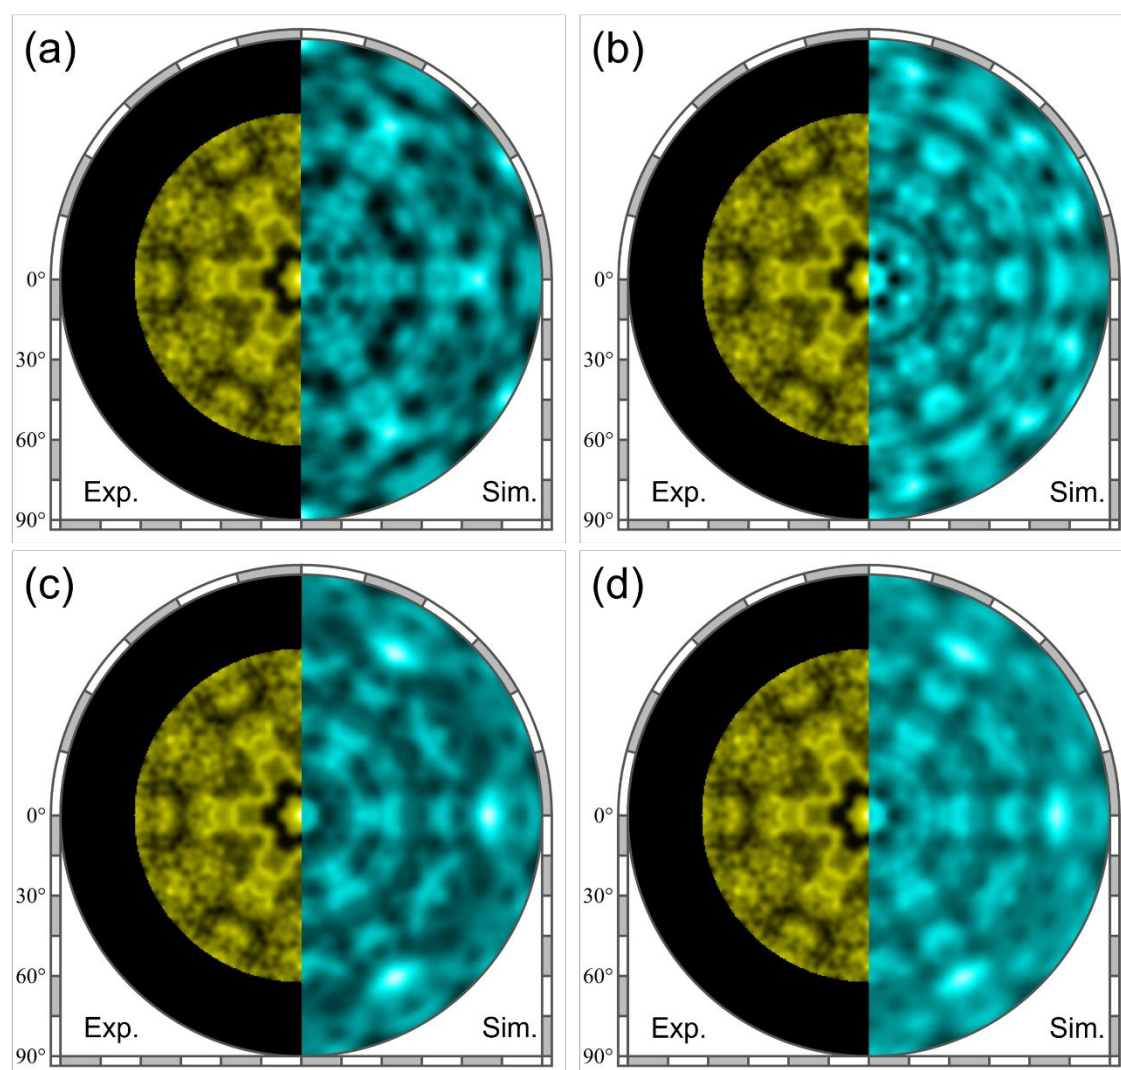


Figure 5. Experimental (yellow) Si 2*p* and the simulated (blue) PEHs. The simulated PEHs of (a) Octa Si_{Ga} site (b) Penta Si_{Ga} site (c) Tetra Si_{Ga} site, and (d) their sum are 16.9%, 28.1%, and 55.0%.

For the undoped κ -Ga₂O₃, the ratios for the Tetra, Penta, and Octa sites were 25%, 25%, and 50%.^{11,19} Therefore, based on our results, in the case of the Si-doped κ -Ga₂O₃, the Tetra Si_{Ga} site is strongly favored with respect to the Penta and Octa sites (55.0% with respect to the presence of just 25% of the Ga tetrahedral sites in the κ -Ga₂O₃ lattice). The Penta Si_{Ga} (28.1%) is almost half of the tetrahedral site occupation despite sharing an identical amount of available sites in the orthorhombic lattice (25% of the

1
2
3
4
5
6 Penta Ga sites in the undoped κ -Ga₂O₃). Even though the Octa Ga sites are the highest
7
8
9 occupation in the κ -Ga₂O₃ lattice (50%), the Octa Si_{Ga} site occupation in Si-doped κ -
10
11
12 Ga₂O₃ is the lowest (16.9%).

13
14
15 The difference in these Si_{Ga} ratios might be related to the formation energy of
16
17
18 such defects. In this framework, our data suggest that the Tetra sites of the Si_{Ga} defect
19
20
21 should have the lowest formation energy with respect to the Octa and Penta coordinations.
22
23
24 Nevertheless, this does not fully agree with the first principles calculations of Zeman et
25
26
27 al. that predicted the Octa Si_{Ga} site to have the lowest formation energy for the κ
28
29
30 polymorph, followed by the Tetra and Penta sites.⁵⁷

31
32
33 The discrepancy between the experimental and theoretical results might be
34
35
36 explained as follows. As we already described the introduction section, our sample has
37
38
39 large density of structural defects. The defects are mostly perfectly vertically oriented,
40
41
42 *i.e.*, 3 x 120° rotated domains and anti-phase boundaries.^{7,23,24} In addition, these vertically
43
44
45 oriented structural defects could be electrically charged.²⁴ On the other hand, the first
46
47
48 principles calculations of Zeman et al. do not contain the charged structural defects,
49
50
51 vertically oriented and rotated domains, and anti-phase boundaries.⁵⁷ As a result, the first
52
53
54 principles calculations might not fully agree with the experimental results.⁵⁸⁻⁶⁰

55
56
57 Von Bardeleben et al. investigated the electrically active dopant in Si-doped κ -
58
59
60

1
2
3
4
5
6 Ga₂O₃ with EPR and concluded that the detected dopant site was due to the Tetra Si_{Ga}
7
8
9 site.¹⁶ Thus, based on the present investigation, that site may be attributed to the active
10
11
12 dopant site for the Si-doped κ-Ga₂O₃. The Si impurity in other Ga sites might be
13
14
15 electrically inactive dopants for the Si-doped κ-Ga₂O₃ (Penta and Octa Si_{Ga} sites). Further
16
17
18 investigations are required to clarify the origin of the suggested inactivity of the Si_{Ga} Penta
19
20
21 and Octa sites.
22
23
24
25
26

27 Conclusion

28
29
30 We used XPS, HAXPES, PEH, and EXAFS to clarify the chemical states and
31
32
33 the atomic positions of Si dopants for Si-doped κ-Ga₂O₃(001). From XPS and HAXPES,
34
35
36 we found that the Si dopant shows one chemical state for the Si-O species in Si-doped κ-
37
38
39 Ga₂O₃(001). Since the Si 2*p* PEH showed clear hologram patterns for the Si dopant, it
40
41
42 should be located at the cationic positions of κ-Ga₂O₃(001). We experimentally
43
44
45 demonstrated that Si is effectively incorporated in Ga sites. We simulated the PEH
46
47
48 patterns to clarify the precise occupation site of Si dopants in the orthorhombic lattice and
49
50
51 found that the simulated PEH of each inequivalent Si_{Ga} site (i.e., Tetra, Penta, Octa) could
52
53
54 not explain the experimental Si 2*p* PEH. Thus, the Si dopant was found to occupy all the
55
56
57 different cationic sites (i.e., mixture of inequivalent Si_{Ga} sites). With the ratios of the Tetra,
58
59
60

1
2
3
4
5
6 Penta, and Octa Si_{Ga} sites of 55.0%, 28.1% and 16.9%, respectively, we obtained a best
7
8
9 fit of the PEH experimental data. The recorded differences should be considered in light
10
11
12 of the overall amount of different Ga inequivalent sites in the orthorhombic unit cell (i.e.,
13
14
15 Tetra, Penta, and Octa sites of 25%, 25%, and 50%) and may be attributed to different
16
17
18 Si_{Ga} formation energies. In this framework, the Tetra Si_{Ga} site has by far the highest
19
20
21 occupation ratio among the three inequivalent Ga sites in the lattice. We suggest that this
22
23
24 result is related to the Si_{Ga} in the Tetra site that has the lowest formation energy; whereas,
25
26
27 the Octa Si_{Ga} site exhibited the lowest ratio, suggesting that this defect configuration has
28
29
30 the highest formation energy. The current findings in the framework of previous
31
32
33 investigations suggest that the Tetra Si_{Ga} site may be the only active dopant site in Si-
34
35
36 doped $\kappa\text{-Ga}_2\text{O}_3$, and the Penta and Octa Si_{Ga} sites may be inactive.
37
38
39
40
41

42 **Supporting Information**

43
44
45

46 The supporting information contains additional experimental data. Figure S1 shows Si 2s
47
48
49 XPS spectrum of Si-doped $\kappa\text{-Ga}_2\text{O}_3(001)$. Figure S2 shows k^2 -weighted Si *K*-edge
50
51
52 EXAFS and the radial distribution function of the k^2 -weighted EXAFS and the fitting
53
54
55 results for the Penta and the Tetra Si_{Ga} sites for Si-doped $\kappa\text{-Ga}_2\text{O}_3(001)$ sample. Figure
56
57
58 S3 shows the difference images between experimental PEH and simulated PEHs for Octa,
59
60

1
2
3
4
5
6 Penta, Tetra Si_{Ga} sites, and the sum of Octa, Penta, and Tetra Si_{Ga} sites where the
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
respective ratio of 16.9%, 28.1%, and 55.0% (the best fit). (Figure 5(d))

Acknowledgments

We acknowledge Dr. H. Oji at the Aichi Synchrotron Center for the experimental support.

The synchrotron radiation experiments were performed with the approval of the Japan Synchrotron Radiation Research Institute (JASRI, proposal no. 2023A1221). This work was supported by JSPS Grant-in-Aid for Transformative Research Areas (A) “Hyper-Ordered Structures Science”: Grant Number 20H05882, 20H05884. This work was also supported by JSPS KAKENHI: Grant Number 20H01841. The epitaxial growth of Ga_2O_3 is supported by Italian National Recovery and Resilience Plan (PNRR) funded by NextGenerationEU, Mission 4, Component 2, Project “Ecosystem for Sustainable Transition in Emilia-Romagna - (Ecosister)”.

Author Contributions

Y.Y. designed, planned, led the research. Data analysis was performed by Y.T and Y.Y.

P.M., A.P., M.B. and L.S. fabricated the Si-doped $\kappa\text{-Ga}_2\text{O}_3$ samples. Y.T., Z.S., T.M.,

T.T. and T.N. performed the experiments under the supervision of Y.H., T.M. and Y.Y.

References

- (1) Pearton, S. J.; Yang, J.; Cary, P. H.; Ren, F.; Kim, J.; Tadjer, M. J.; Mastro, M. A. A Review of Ga₂O₃ materials, processing, and devices. *Appl. Phys. Rev.* **2018**, *5*, 011301.
- (2) Zhang, J.; Shi, J.; Qi, D.-C.; Chen, L.; Zhang, K. H. Recent progress on the electronic structure, defect, and doping properties of Ga₂O₃. *APL Mater.* **2020**, *8*, 020906.
- (3) Kaneko, K.; Uno, K.; Jinno, R.; Fujita, S. Prospects for phase engineering of semi-stable Ga₂O₃ semiconductor thin films using mist chemical vapor deposition. *J. Appl. Phys.* **2022**, *131*, 090902.
- (4) Wang, Y.; Su, J.; Lin, Z.; Zhang, J.; Chang, J.; Hao, Y. Recent progress on the effects of impurities and defects on the properties of Ga₂O₃. *J. Mater. Chem. C* **2022**, *10*, 13395–13436.
- (5) Hu, Z.; Feng, Q.; Feng, Z.; Cai, Y.; Shen, Y.; Yan, G.; Lu, X.; Zhang, C.; Zhou, H.; Zhang, J.; Hao, Y. Experimental and Theoretical Studies of Mo/Au Schottky Contact on Mechanically Exfoliated β-Ga₂O₃ Thin Film. *Nanoscale Res. Lett.* **2019**, *14*, 1–7.
- (6) Jamwal, N. S.; Kiani, A. Gallium Oxide Nanostructures: A Review of Synthesis, Properties and Applications. *Nanomaterials* **2022**, *12*, 2061.
- (7) Mazzolini, P.; Fogarassy, Z.; Parisini, A.; Mezzadri, F.; Diercks, D.; Bosi, M.; Seravalli, L.; Sacchi, A.; Spaggiari, G.; Bersani, D.; Bierwagen, O.; Janzen, B.; Marggraf, M.; Wagner, M.; Cora, I.; Pécz, B.; Tahraoui, A.; Bosio, A.; Borelli, C.; Leone, S.; Fornari, R. Silane-Mediated Expansion of Domains in Si-Doped κ-Ga₂O₃ Epitaxy and its Impact on the In-Plane Electronic Conduction. *Adv. Funct. Mater.* **2022**, *33*, 2207821.
- (8) Tippins, H. H. Optical Absorption and Photoconductivity in the Band Edge of β-Ga₂O₃. *Phys. Rev.* **1965**, *140*, A316.
- (9) Mu, S.; Van de Walle, C. G. Phase stability of (Al_xGa_{1-x})₂O₃ polymorphs: A first-principles study. *Phys. Rev. Mater.* **2022**, *6*, 104601.
- (10) Mezzadri, F.; Calestani, G.; Boschi, F.; Delmonte, D.; Bosi, M.; Fornari, R. Crystal Structure and Ferroelectric Properties of ε-Ga₂O₃ Films Grown on (0001)-Sapphire. *Inorg. Chem.* **2016**, *55*, 12079–12084.
- (11) Kang, H. Y.; Choi, Y.; Pyeon, K.; Lee, T. H.; Chung, R. B. Experimental and theoretical investigation of the effect of Sn on κ-Ga₂O₃ Growth. *J. Mater. Sci.* **2022**, *57*, 19882–19891.
- (12) Cho, S. B.; Mishra, R. Epitaxial engineering of polar ε-Ga₂O₃ for tunable two-dimensional electron gas at the heterointerface. *Appl. Phys. Lett.* **2018**, *112*, 162101.
- (13) Ranga, P.; Cho, S. B.; Mishra, R.; Krishnamoorthy, S. Highly tunable, polarization-engineered two-dimensional electron gas in ε-AlGaO₃/ε-Ga₂O₃ heterostructures. *Appl. Phys. Express* **2020**, *13*, 061009.
- (14) Bosi, M.; Mazzolini, P.; Seravalli, L.; Fornari, R. Ga₂O₃ polymorphs: tailoring the epitaxial growth conditions. *J. Mater. Chem. C* **2020**, *8*, 10975–10992.

- 1
2
3
4
5
6 (15)Janzen, B. M.; Mazzolini, P.; Gillen, R.; Peltason, V. F.; Grote, L. P.; Maultzsch, J.; Fornari, R.;
7 Bierwagen, O.; Wagner, M. R. Comprehensive Raman study of orthorhombic κ/ϵ -Ga₂O₃ and the
8 impact of rotational domains. *J. Mater Chem. C* 2021, 9, 14175–14189.
- 9
10 (16)von Bardeleben, H. J.; Cantin, J. L.; Parisini, A.; Bosio, A.; Fornari, R. Conduction mechanism
11 and shallow donor properties in silicon-doped ϵ -Ga₂O₃ thin films: An electron paramagnetic
12 resonance study. *Phys. Rev. Mater.* **2019**, 3, 084601.
- 13
14 (17)Girolami, M.; Bosi, M.; Serpente, V.; Mastellone, M.; Seravalli, L.; Pettinato, S.; Salvatori, S.;
15 Trucchi, D. M.; Fornari, R. Orthorhombic undoped κ -Ga₂O₃ epitaxial thin films for sensitive, fast,
16 and stable direct X-ray detectors. *J. Mater Chem. C* **2023**, 11, 3759–3769.
- 17
18 (18)Ardenghi, A.; Bierwagen, O.; Lähnemann, J.; Kler, J.; Falkenstein, A.; Martin, M.; Mazzolini, P.
19 Phase-selective growth of κ - vs β -Ga₂O₃ and (In_xGa_{1-x})₂O₃ by In-mediated metal exchange
20 catalysis in plasma-assisted molecular beam epitaxy. *arXiv preprint* **2023**, 2311, 13318.
- 21
22 (19)Seacat, S.; Lyons, J. L.; Peelaers, H. Properties of orthorhombic Ga₂O₃ Alloyed with In₂O₃ and
23 Al₂O₃. *Appl. Phys. Lett.* **2021**, 119, 042104.
- 24
25 (20)Parisini, A.; Bosio, A.; Montedoro, V.; Gorreri, A.; Lamperti, A.; Bosi, M.; Garulli, G.; Vantaggio,
26 S.; Fornari, R. Si and Sn doping of ϵ -Ga₂O₃ Layers. *APL Mater.* **2019**, 7, 031114.
- 27
28 (21)Polyakov, A.; Lee, I.; Nikolaev, V.; Pechnikov, A.; Miakonkikh, A.; Scheglov, M.; Yakimov, E.;
29 Chikiryaka, A.; Vasilev, A.; Kochkova, A.; Shchemerov, I.; Chernykh, A.; Pearton, S. Properties
30 of κ -Ga₂O₃ Prepared by Epitaxial Lateral Overgrowth. *Adv. Mater. Interfaces* **2023**, 2300394.
- 31
32 (22)Rajabi Kalvani, P.; Parisini, A.; Sozzi, G.; Borelli, C.; Mazzolini, P.; Bierwagen, O.; Vantaggio,
33 S.; Egbo, K.; Bosi, M.; Seravalli, L.; Fornari, R. Interfacial Properties of the SnO/ κ -Ga₂O₃ p-n
34 Heterojunction: A Case of Subsurface Doping Density Reduction via Thermal Treatment in κ -
35 Ga₂O₃. *ACS Appl. Mater. Interfaces* 2023, 15, 45997–46009.
- 36
37 (23)Cora, I.; Mezzadri, F.; Boschi, F.; Bosi, M.; Čaplovičová, M.; Calestani, G.; Dódony, I.; Pécz, B.;
38 Fornari, R. The real structure of ϵ -Ga₂O₃ and its relation to κ -phase. *Cryst. Eng. Comm.* **2017**, 19,
39 1509–1516.
- 40
41 (24)Vyvenko, O. F.; Shapenkov, S. V.; Ubyivovk, E. V.; Bondarenko, A. S.; Pechnikov, A. I.;
42 Nikolaev, V. I.; Stepanov, S. I. Twin domain and antiphase boundaries in microcrystals of κ -
43 Phase Ga₂O₃. *Materialia* **2023**, 32, 101942.
- 44
45 (25)Fiedler, A.; Schewski, R.; Baldini, M.; Galazka, Z.; Wagner, G.; Albrecht, M.; Irmscher, K.
46 Influence of incoherent twin boundaries on the electrical properties of β -Ga₂O₃ layers
47 homoepitaxially grown by metal-organic vapor phase epitaxy. *J. Appl. Phys.* **2017**, 122 (16),
48 165701.
- 49
50 (26)Tsutsui, K.; Matsushita, T.; Natori, K.; Muro, T.; Morikawa, Y.; Hoshii, T.; Kakushima, K.;
51 Wakabayashi, H.; Hayashi, K.; Matsui, F.; Kinoshita, T. Individual Atomic Imaging of Multiple
52 Dopant Sites in As-Doped Si Using Spectro-Photoelectron Holography. *Nano Lett.* **2017**, 17,
53
54
55
56
57
58
59
60

- 7533–7538.
- (27) Tang, J.; Takeuchi, S.; Tanaka, M.; Tomita, H.; Hashimoto, Y.; Nagata, T.; Chen, J.; Ohkochi, T.; Kotani, Y.; Matsushita, T.; Yamashita, Y. Direct Observation of Atomic Structures and Chemical States of Active and Inactive Dopant Sites in Mg-Doped GaN. *ACS Appl. Electron. Mater.* **2022**, *4*, 4719–4723.
- (28) Yokoya, T.; Terashima, K.; Takeda, A.; Fukura, T.; Fujiwara, H.; Muro, T.; Kinoshita, T.; Kato, H.; Yamasaki, S.; Oguchi, T.; Wakita, T.; Muraoka, Y.; Matsushita, T. Asymmetric Phosphorus Incorporation in Homoepitaxial P-Doped (111) Diamond Revealed by Photoelectron Holography. *Nano Lett.* **2019**, *19*, 5915–5919.
- (29) Uenuma, M.; Kuwaharada, S.; Tomita, H.; Tanaka, M.; Sun, Z.; Hashimoto, Y.; Fujii, M. N.; Matsushita, T.; Uraoka, Y. Atomic structure analysis of gallium Oxide at the Al₂O₃/GaN interface using photoelectron holography. *Appl. Phys. Express* **2022**, *15*, 085501.
- (30) Libra, J. *KolXPD: Software for Spectroscopy Data Measurement and Processing*. <https://www.kolibrik.net/kolxpd/> (accessed Feb 14, 2024).
- (31) Jain, V.; Biesinger, M. C.; Linford, M. R. The Gaussian-Lorentzian Sum, Product, and Convolution (Voigt) functions in the context of Peak Fitting X-ray photoelectron spectroscopy (XPS) narrow scans. *Appl. Surf. Sci.* **2018**, *447*, 548–553.
- (32) Castle, J. E.; Salvi, A. M. Interpretation of the Shirley background in x-ray photoelectron spectroscopy analysis. *J. Vac. Sci. Technol. A* **2001**, *19*, 1170–1175.
- (33) Vègh, J. The Shirley Background Revised. *J. Electron Spectros. Relat. Phenomena* **2006**, *151*, 159–164.
- (34) Muro, T.; Ohkochi, T.; Kato, Y.; Izumi, Y.; Fukami, S.; Fujiwara, H.; Matsushita, T. Wide-angle display-type retarding field analyzer with high energy and angular resolutions. *Rev. Sci. Instrum.* **2017**, *88*, 123106.
- (35) Muro, T.; Matsushita, T.; Sawamura, K.; Mizuno, J. Spherical micro-hole grid for high-resolution retarding field analyzer. *J. Synchrotron. Radiat.* **2021**, *28*, 1669–1671.
- (36) Matsushita, T.; Hashimoto, Y.; Tomita, H.; Sun, Z.; Kawamura, S.; Fujii, M. N.; Mizuno, J. An Algorithm to Correct the Sensitivity Distribution of a Retarding Field Analyzer for Photoelectron Holography. *e-J. Surf. Sci. Nanotechnol.* **2023**, *21*, 183–187.
- (37) Matsushita, T.; Matsui, F.; Daimon, H.; Hayashi, K. Photoelectron holography with improved image reconstruction. *J. Electron. Spectrosc.* **2010**, *178*, 195–220.
- (38) Matsushita, T. Algorithm for Atomic Resolution Holography Using Modified L_1 -regularized Linear Regression and Steepest Descent Method. *Phys. Status. Solidi. B* **2018**, *255*, 180091.
- (39) Li, Y.; Sun, Z.; Kataoka, N.; Setoguchi, T.; Hashimoto, Y.; Takeuchi, S.; Koga, S.; Demura, S.; Noguchi, K.; Sakata, H.; Mizuguchi, Y.; Matsushita, T.; Wakita, T.; Muraoka, Y.; Yokoya, T. Photoelectron Holography Study of La(O,F)BiS₂. *J. Phys. Soc. Jpn.* **2023**, *92*, 044801.

- 1
2
3
4
5
6 (40) Matsushita, T.; Muro, T.; Yokoya, T.; Terashima, K.; Kato, Y.; Matsui, H.; Maejima, N.;
7 Hashimoto, Y.; Matsui, F. Theory for High-angular-resolution Photoelectron Holograms
8 Considering the Inelastic Mean Free Path and the Formation Mechanism of Quasi-Kikuchi Band.
9 *Phys. Status. Solidi. B* **2020**, *257*, 2000117.
- 10
11 (41) Oji, H.; Murai, T.; Shibata, Y.; Tabuchi, M.; Watanabe, Y.; Takeda, Y. Current Status of BL6N1
12 of AichiSR: A Tender X-Ray Beamline for XAFS and Photoemission Spectroscopy. *J. Surf. Anal.*
13 **2020**, *26*, 228–244.
- 14
15 (42) Indari, E. D.; Yamashita, Y.; Hasunuma, R.; Oji, H.; Yamabe, K. Relationship between electrical
16 properties and interface structures of SiO₂/4H-SiC prepared by dry and wet oxidation. *AIP Adv.*
17 **2019**, *9*, 105018.
- 18
19 (43) Yamashita, Y.; Nara, J.; Indari, E. D.; Yamasaki, T.; Ohno, T.; Hasunuma, R. Experimental and
20 theoretical studies on atomic structures of the interface states at SiO₂/4H-SiC(0001) interface. *J.*
21 *Appl. Phys.* **2022**, *131*, 215303.
- 22
23 (44) Bhuiyan, A. F.; Feng, Z.; Huang, H.-L.; Meng, L.; Hwang, J.; Zhao, H. MOCVD growth and band
24 offsets of κ-phase Ga₂O₃ on c-plane sapphire, GaN- and AlN-on-sapphire, and (100) YSZ
25 substrates. *J. Vac. Sci. Technol. A* **2022**, *40*, 062704.
- 26
27 (45) Hellwig, M.; Xu, K.; Barreca, D.; Gasparotto, A.; Winter, M.; Tondello, E.; Fischer, R. A.; Devi,
28 A. Novel Gallium Complexes with Malonic Diester Anions as Molecular Precursors for the
29 MOCVD of Ga₂O₃ Thin Films. *Eur. J. Inorg. Chem.* **2009**, *2009*, 1110–1117.
- 30
31 (46) Ghosh, S. C.; Biesinger, M. C.; LaPierre, R. R.; Kruse, P. X-ray photoelectron spectroscopic study
32 of the formation of catalytic gold nanoparticles on ultraviolet-ozone oxidized GaAs(100)
33 substrates. *J. Appl. Phys.* **2007**, *101*, 114322.
- 34
35 (47) Vanleenhove, A.; Hofliijk, I.; Vaesen, I.; Zborowski, C.; Artyushkova, K.; Conard, T. High-energy
36 x-ray photoelectron spectroscopy spectra of SiO₂ measured by Cr Kα. *Surf. Sci. Spectra* **2022**, *29*,
37 014014.
- 38
39 (48) Chourasia, A. R.; Hood, S. J.; Chopra, D. R. A study of Si compounds by Zr Lα photoelectron
40 spectroscopy. *J. Vac. Sci. Technol. A* **1996**, *14*, 699–703.
- 41
42 (49) Kobayashi, K. High-resolution hard X-ray photoelectron spectroscopy: Application of valence
43 band and core-level spectroscopy to materials science. *Nucl. Instrum. Meth. A* **2005**, *547*, 98–112.
- 44
45 (50) Zhang, L.; Kuramoto, N.; Azuma, Y.; Kurokawa, A.; Fujii, K. Thickness Measurement of Oxide
46 and Carbonaceous Layers on a ²⁸Si Sphere by XPS. *IEEE T. Instrum. Meas.* **2016**, *66*, 1297–1303.
- 47
48 (51) Gibbon, J. T.; Jones, L.; Roberts, J. W.; Althobaiti, M.; Chalker, P. R.; Mitrovic, I. Z.; Dhanak,
49 V. R. Band alignments at Ga₂O₃ heterojunction interfaces with Si and Ge. *AIP Adv.* **2018**, *8*,
50 065011.
- 51
52 (52) Thompson, A.; Attwood, D.; Gullikson, E.; Howells, M.; Kim, K. J.; Kirz, J.; Winick, H. X-ray
53 data booklet; Lawrence Berkeley National Laboratory, University of California: Berkeley, CA,
54
55
56
57
58
59
60

- 1
2
3
4
5
6 2001
- 7 (53)Ulgut, B.; Suzer, S. XPS Studies of SiO₂/Si System under External Bias. *J. Phys. Chem. B* **2003**,
8 *107*, 2939–2943.
- 9
10
11 (54)Nesbitt, H. W.; Bancroft, G. M.; Davidson, R.; McIntyre, N. S.; Pratt, A. R. Minimum XPS core-
12 level line widths of insulators, including silicate minerals. *Am. Mineral.* **2004**, *89*, 878–882.
- 13 (55)Ravel, B.; Newville, M. ATHENA, ARTEMIS, HEPHAESTUS: data analysis for X-ray absorption
14 spectroscopy using IFEFFIT. *J. Synchrotron Radiat.* **2005**, *12*, 537–541.
- 15
16 (56)Ravel, B.; Newville, M. ATHENA and ARTEMIS: interactive graphical data analysis using
17 IFEFFIT. *Phys. Scripta* **2005**, *2005*, 1007.
- 18
19 (57)Zeman, C. J.; Kielar, S. M.; Jones, L. O.; Mosquera, M. A.; Schatz, G. C. Investigation of p-type
20 doping in β- and κ-Ga₂O₃. *J. Alloy. Compd.* **2021**, *877*, 160227.
- 21
22 (58)Shokri, A.; Melikhov, Y.; Syryanyy, Y.; Demchenko, I. N. Point Defects in Silicon-Doped β-
23 Ga₂O₃: Hybrid-DFT Calculations. *ACS Omega* **2023**, *8*, 43732–43738.
- 24
25
26 (59)Tadger, M. J.; Lyons, J. L.; Nepal, N.; Freitas, J. A.; Koehler, A. D.; Foster, G. M. Review-Theory
27 and Characterization of Doping and Defects in β-Ga₂O₃. *ECS J. Solid State SC.* **2019**, *8*, Q3187–
28 Q3194.
- 29
30 (60)Lany, S. Defect phase diagram for doping of Ga₂O₃. *APL Mater.* **2018**, *6*, 046103.
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60