



UNIVERSITÀ DI PARMA

ARCHIVIO DELLA RICERCA

University of Parma Research Repository

Effect of GO nanosheets on microstructure, mechanical and fracture properties of cement composites

This is the peer reviewed version of the following article:

Original

Effect of GO nanosheets on microstructure, mechanical and fracture properties of cement composites / Vantadori, Sabrina; Magnani, Giacomo; Mantovani, Luciana; Pontiroli, Daniele; Ronchei, Camilla; Scorza, Daniela; Sidoli, Michele; Zanichelli, Andrea; Riccò, Mauro. - In: CONSTRUCTION AND BUILDING MATERIALS. - ISSN 0950-0618. - 361:(2022), p. 129368. [10.1016/j.conbuildmat.2022.129368]

Availability:

This version is available at: 11381/2940272 since: 2024-11-11T14:34:08Z

Publisher:

Published

DOI:10.1016/j.conbuildmat.2022.129368

Terms of use:

Anyone can freely access the full text of works made available as "Open Access". Works made available

Publisher copyright

note finali coverpage

(Article begins on next page)

~~EFFECT OF GO NANOSHEETS ON FRACTURE TOUGHNESS OF CEMENT COMPOSITES~~

EFFECT OF GO NANOSHEETS ON MICROSTRUCTURE, MECHANICAL

AND FRACTURE PROPERTIES OF CEMENT COMPOSITES

Sabrina Vantadori^{a*}, Giacomo Magnani^b, Luciana Mantovani^c,
Daniele Pontiroli^b, Camilla Ronchei^d, Daniela Scorza^e,
Michele Sidoli^b, Andrea Zanichelli^a, Mauro Riccò^b

^aDepartment of Engineering & Architecture, University of Parma,
Parco Area delle Scienze 181/A, 43124 Parma - Italy

^bDepartment of Mathematical, Physical and Computer Sciences &
INSTM, University of Parma, Parco Area delle Scienze 7/A, 43124
Parma, Italy

^cDepartment of Chemistry, Life Sciences and Environmental
Sustainability, University of Parma, Parco Area delle Scienze
157/A, 43124 Parma, Italy

^dDepartment of Civil Engineering, University of Calabria, via
Pietro Bucci, 87036 Arcavacata di Rende (CS), Italy

^eDepartment of Engineering, University of Naples Parthenope, Centro
Direzionale Isola C4, 80143 Napoli, Italy

***Corresponding author:** sabrina.vantadori@unipr.it

FIGURES AND TABLES

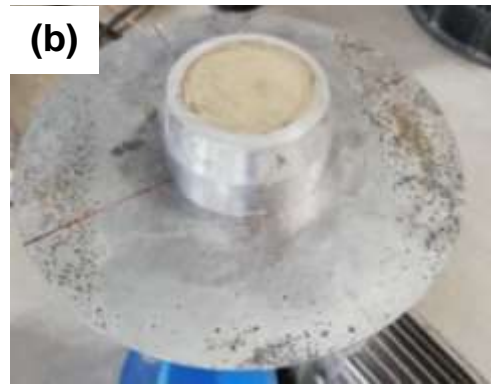
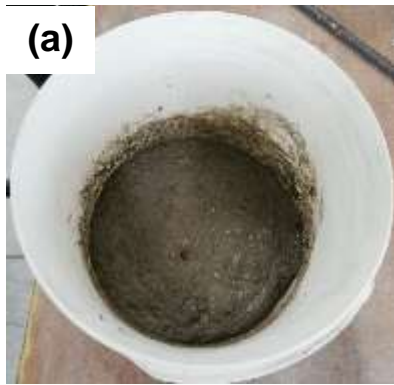


Figure 1. Preparation of GO-B specimens: (a) fresh slurry, (b) flow table test, (c) fresh slurry compacted in prismatic moulds.

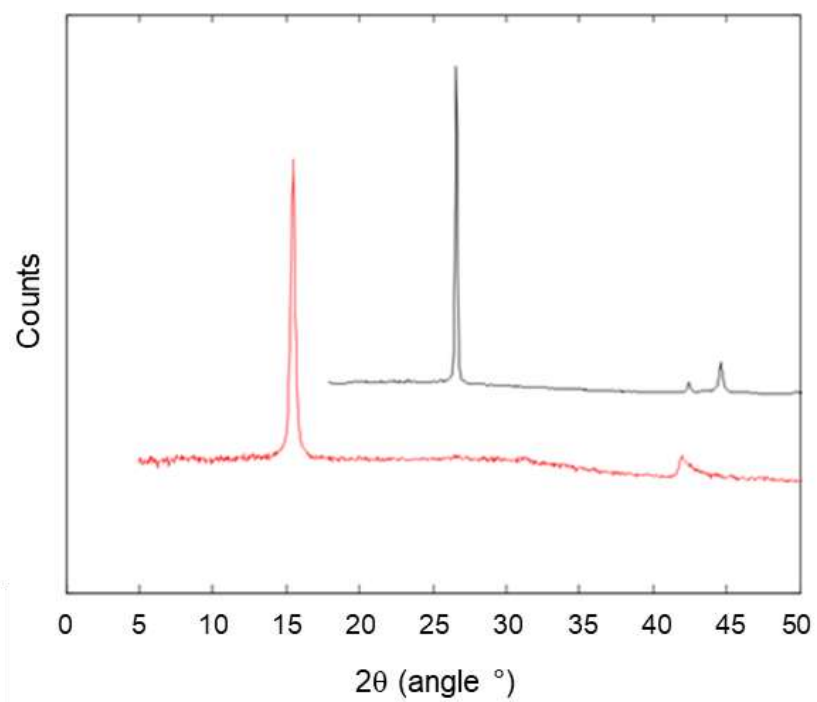


Figure 2. XRD spectra of pure graphite (black line) and GO (red line).

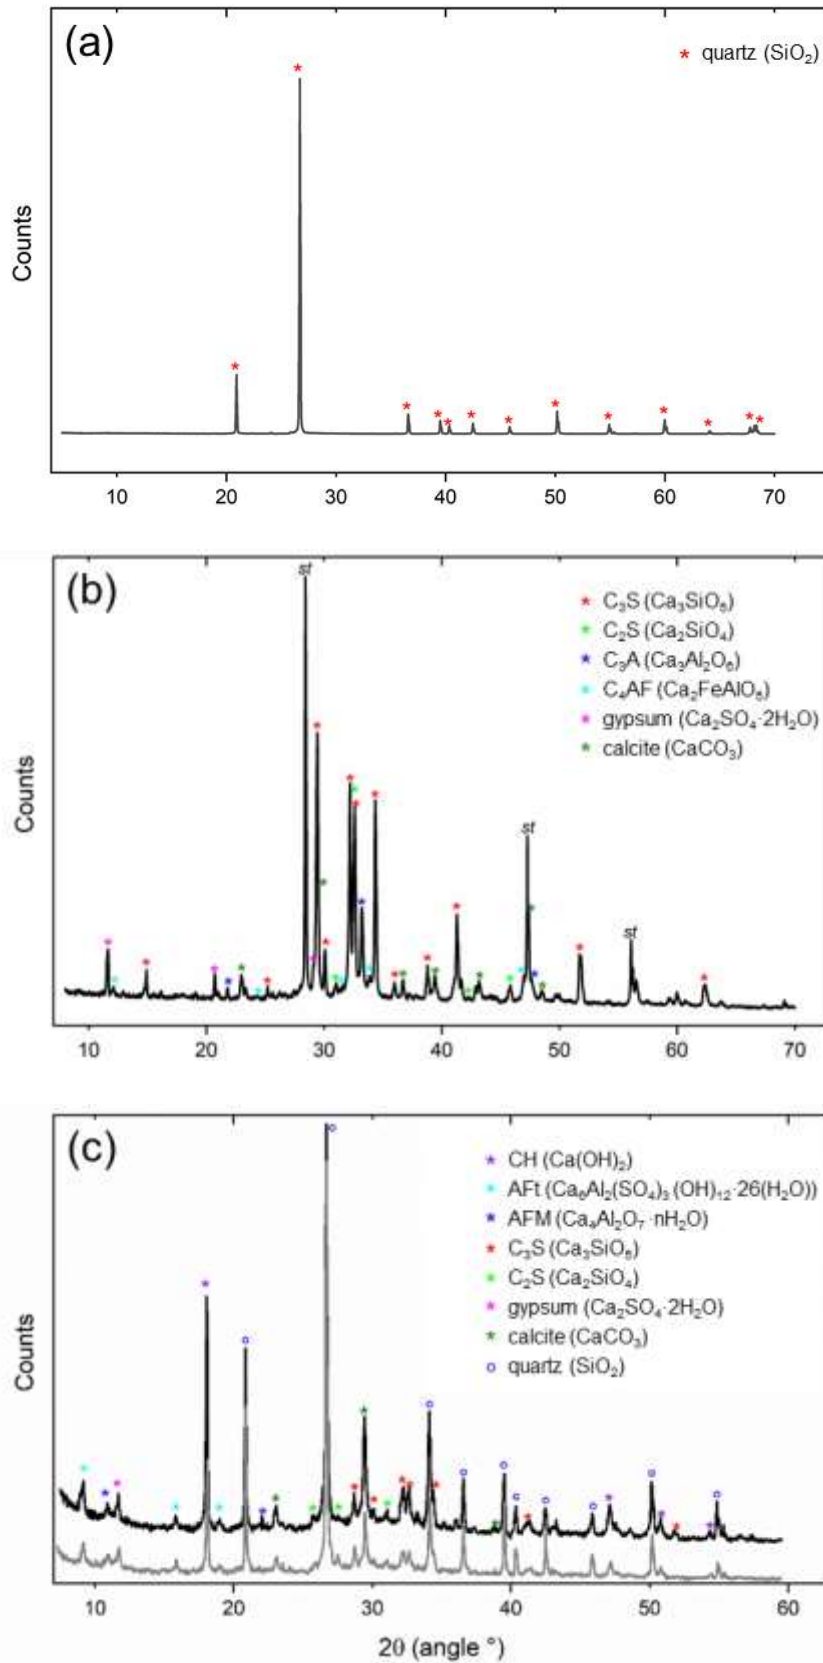


Figure 3. X-ray diffraction patterns of: (a) aggregates, (b) cement, (c) PM (black line) and GO-B specimens (grey line).

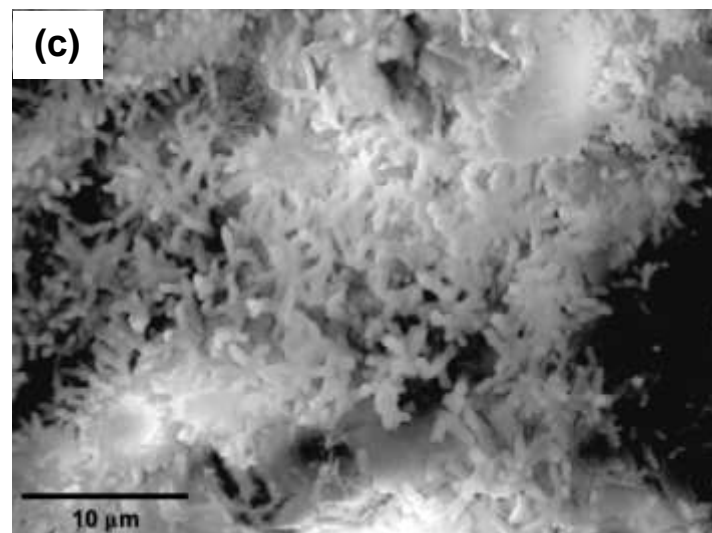
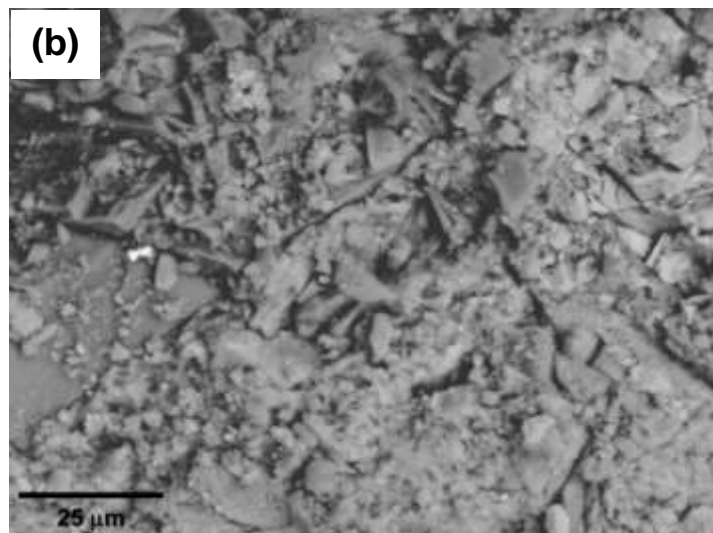
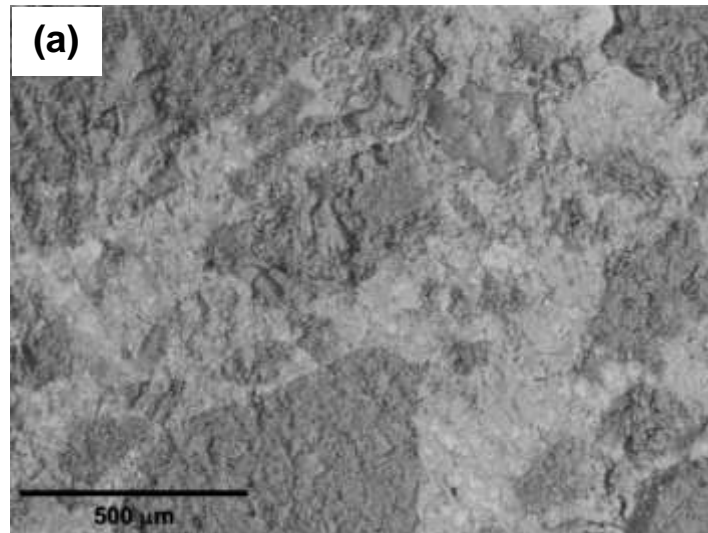


Figure 4. SEM images (in BSE) of PM specimen at different levels of magnification: (a) 55X, (b) 800X and (c) 1000X.

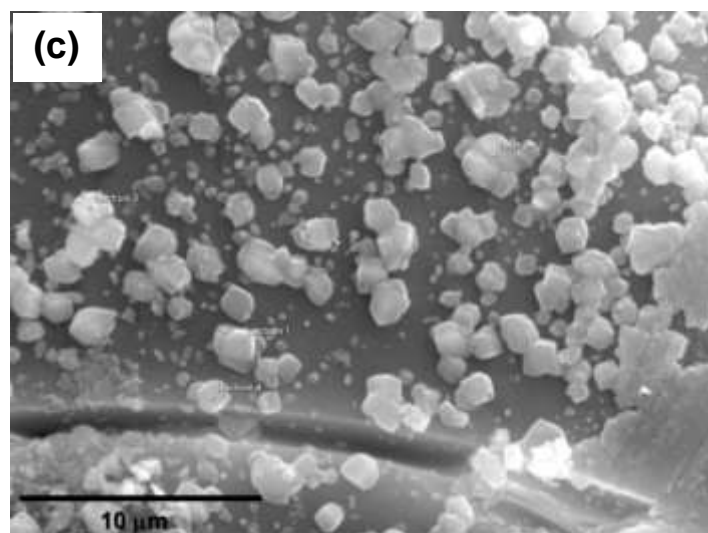
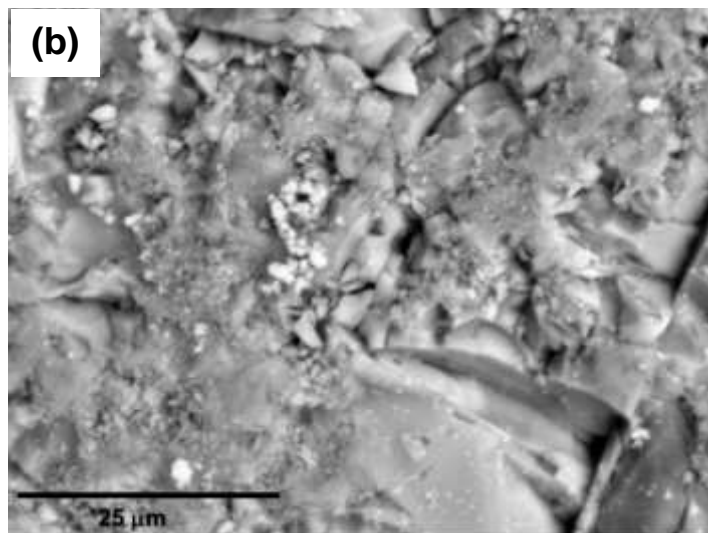
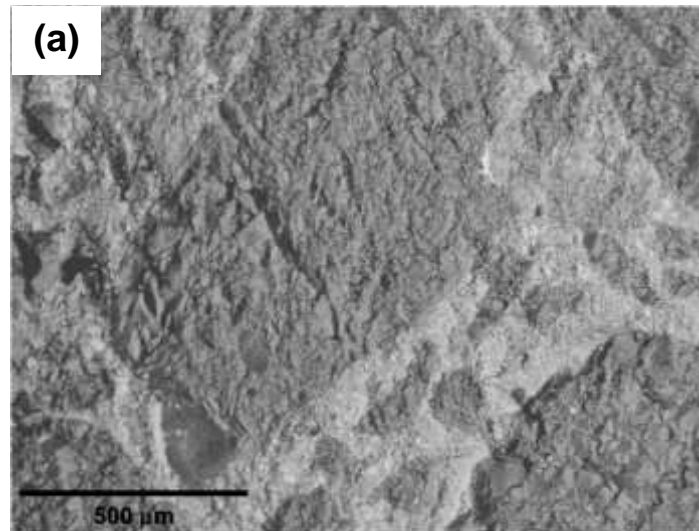


Figure 5. SEM images (in BSE) of GO-B specimen at different levels of magnification: (a) 55X, (b) 800X and (c) 1000X.

Table 1. Flexural and compression test results for both PM and GO-B specimen type.

SPECIMEN TYPE	P_f [kN]		R_f [MPa]		P_c [kN]		R_c [MPa]	
	μ	σ	μ	σ	μ	σ	μ	σ
PM	1.994	0.103	5.285	0.297	151.027	6.660	87.517	2.980
GO-B	1.993	0.108	5.516	0.213	155.915	7.410	90.567	3.496

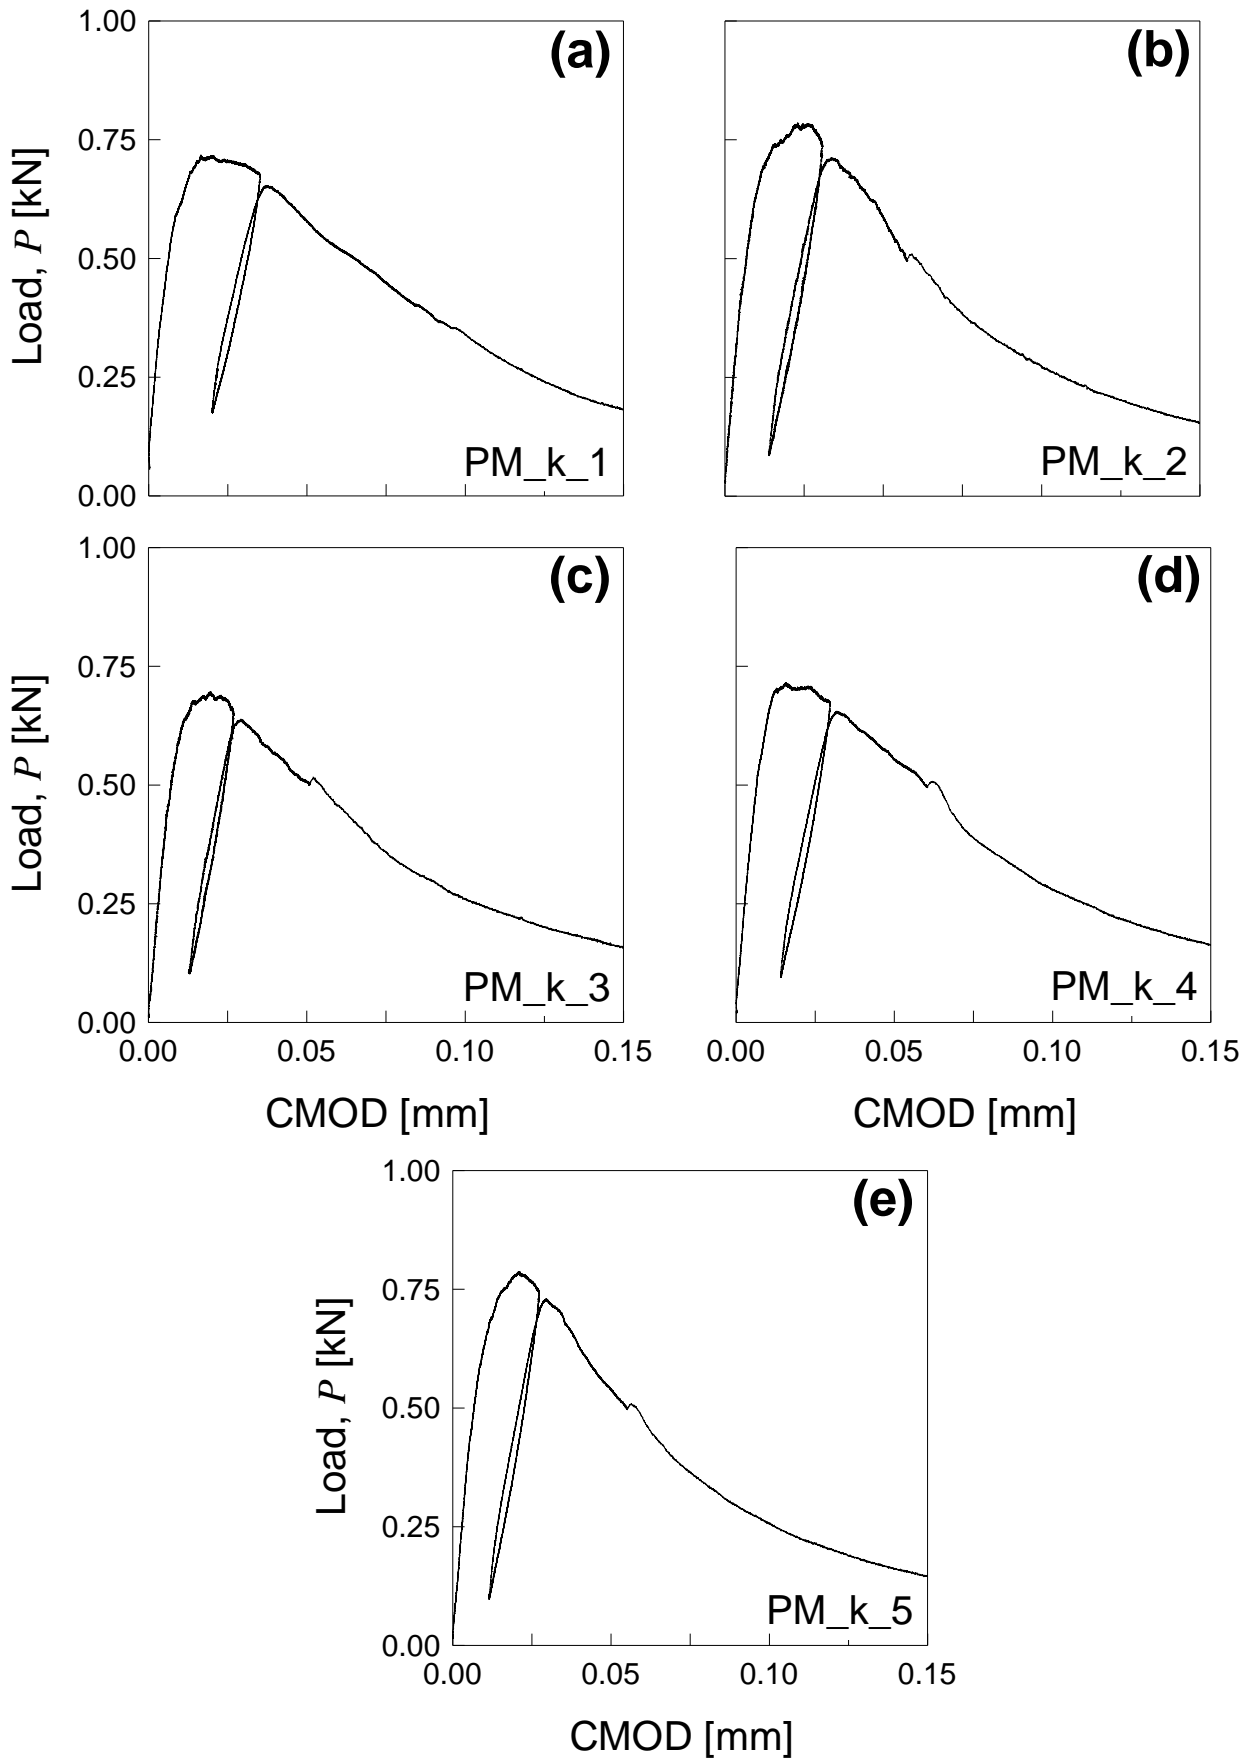


Figure 6. Load - Crack Mouth Opening Displacement (CMOD) curves for PM_k specimens.

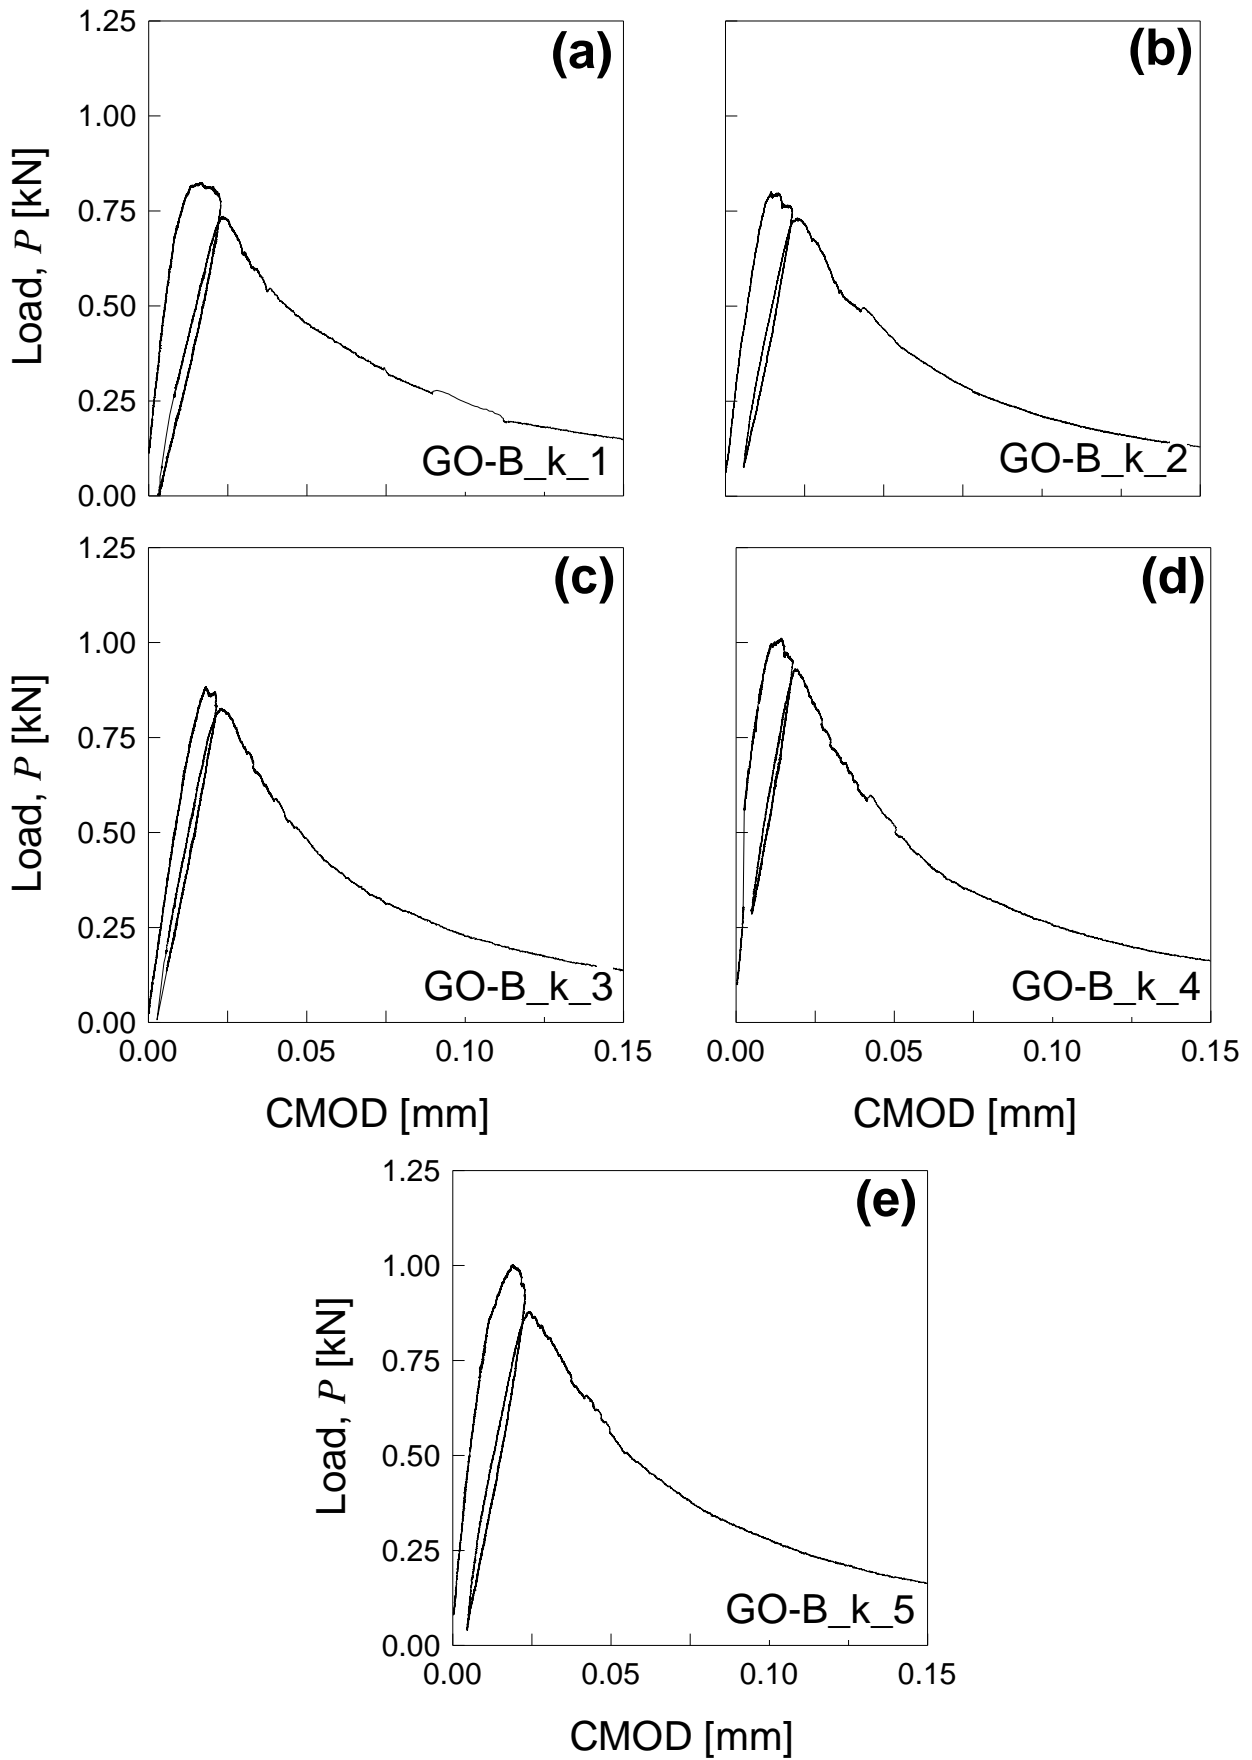


Figure 7. Load - Crack Mouth Opening Displacement (CMOD) curves for GO-B_k specimens.

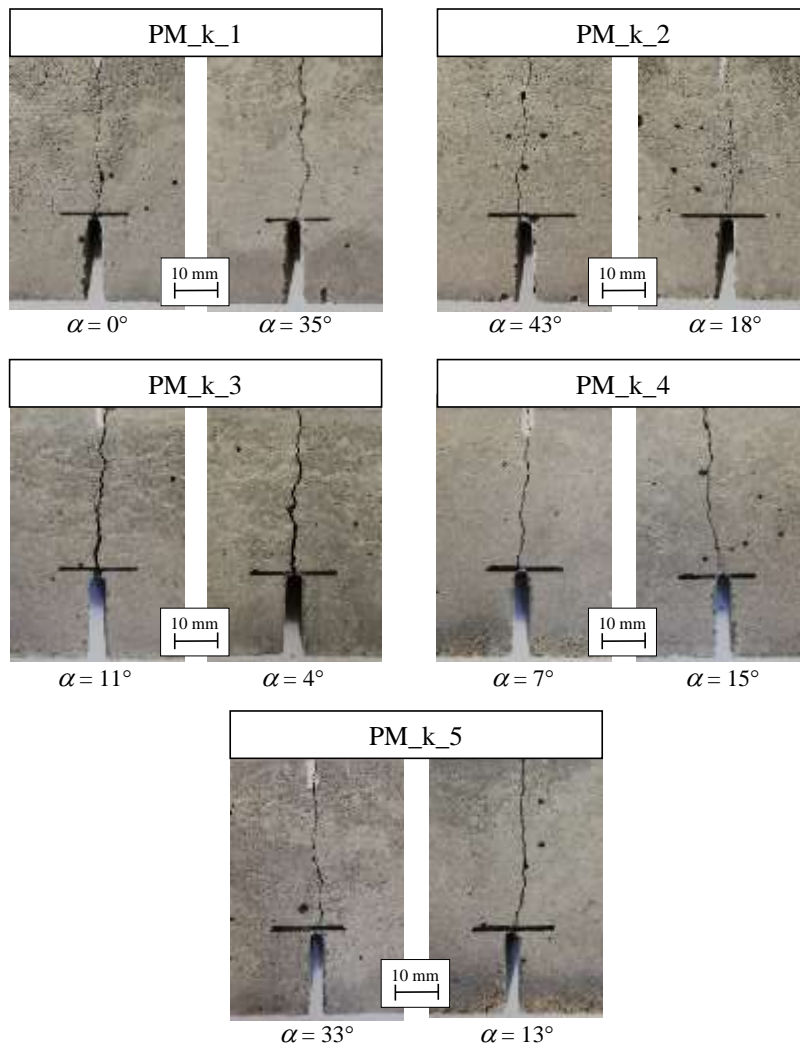


Figure 8. Crack paths and kinking angle values for PM_k specimens.

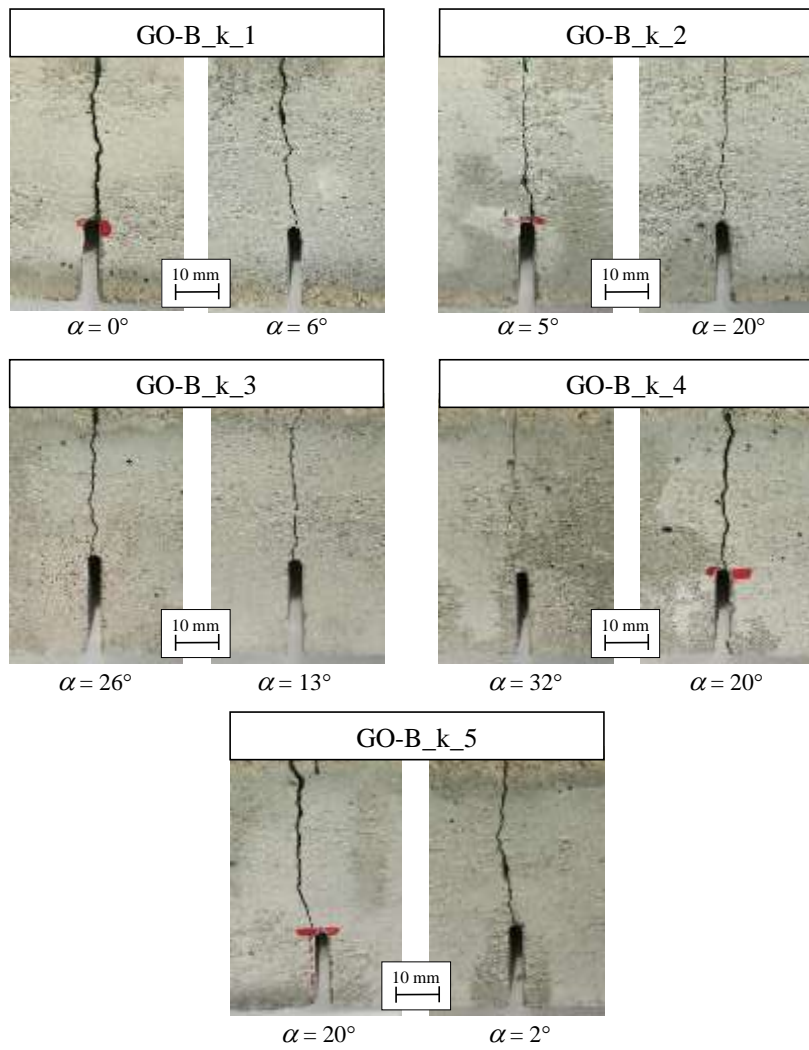


Figure 9. Crack paths and kinking angle values for GO-B_k specimens.

Table 2. Fracture test results for both PM and GO-B specimen type.

SPECIMEN TYPE	P_{max} [kN]		α [°]		E [GPa]		$K_{(I+II)C}^S$ [MPa·m ^{0.5}]	
	μ	σ	μ	σ	μ	σ	μ	σ
PM	0.741	0.043	17.9	9.229	31.873	1.571	0.788	0.027
GO-B	0.916	0.086	14.4	8.742	33.529	1.529	0.992	0.072