

SCIENTIFIC REPORTS



OPEN

The strength of electron electron correlation in Cs_3C_{60}

L. Baldassarre¹, A. Perucchi², M. Mitrano^{3,4}, D. Nicoletti^{3,4}, C. Marini⁵, D. Pontiroli⁶, M. Mazzani⁶, M. Aramini⁶, M. Ricc6⁶, G. Giovannetti⁷, M. Capone⁷ & S. Lupi⁸

Received: 17 March 2015

Accepted: 24 August 2015

Published: 15 October 2015

Cs_3C_{60} is an antiferromagnetic insulator that under pressure (P) becomes metallic and superconducting below $T_c = 38\text{ K}$. The superconducting dome present in the $T - P$ phase diagram close to a magnetic state reminds what found in superconducting cuprates and pnictides, strongly suggesting that superconductivity is not of the conventional Bardeen-Cooper-Schrieffer (BCS) type. We investigate the insulator to metal transition induced by pressure in Cs_3C_{60} by means of infrared spectroscopy supplemented by Dynamical Mean-Field Theory calculations. The insulating compound is driven towards a metallic-like behaviour, while strong correlations survive in the investigated pressure range. The metallization process is accompanied by an enhancement of the Jahn-Teller effect. This shows that electronic correlations are crucial in determining the insulating behaviour at ambient pressure and the bad metallic nature for increasing pressure. On the other hand, the relevance of the Jahn-Teller coupling in the metallic state confirms that phonon coupling survives in the presence of strong correlations.

The allotropic forms of carbon exhibit a wealth of fascinating properties that triggered an intensive research, in particular after the discovery of nanotubes, fullerenes, and graphene^{1,2}. Indeed, the outstanding mechanical, thermal, electronic, and electrical properties of carbon nanostructures and their functional derivatives, coupled with their chemical robustness, have been the key to the development of a broad range of applications in Physics, Chemistry, and Bio-Medicine³. In addition to applications, these materials turned out to be the perfect test bench for studying various physical phenomena, as for instance in fullerides, Insulator-to-Metal transitions (IMT) and Superconductivity: C_{60} is a molecular solid and shows at ambient conditions an f.c.c. structure with a three-fold degenerate t_{1u} band⁴. Alkali-intercalated compounds A_3C_{60} are also insulators due to a combined effect of molecular Jahn-Teller (JT) and Mott-Hubbard interactions⁵. A_3C_{60} ($A = \text{Rb}, \text{K}$) are instead metallic and superconductors with a maximum critical temperature T_c of 33 K. Superconductivity in A_3C_{60} has been explained in the past through a Bardeen-Cooper-Schrieffer (BCS) phononic mechanism based on the intramolecular H_g Jahn-Teller vibrational modes⁶, which is seemingly supported by a wealth of experimental reports⁷⁻⁹.

Even if the JT active phonon modes remain the most likely candidates for pairing, the limitations of a simple BCS phononic mechanism for C_{60} materials start to be evident in compounds with an expanded lattice¹⁰⁻¹² suggesting a strong role of electronic correlations¹³⁻¹⁵. The synthesis of the insulating, expanded polymorphs of Cs_3C_{60} , as the A15 structure, has set a new agenda: Unlike the other members of the A_3C_{60} family, both f.c.c. and b.c.c. Cs_3C_{60} are magnetic insulators and become superconducting only under pressure (P)¹⁶, reaching the highest critical temperature in the fullerides, $T_c = 38\text{ K}$. The $T - P$ phase diagram

¹Center for Life Nano Science@Sapienza, Istituto Italiano di Tecnologia, V.le Regina Elena 291, Rome, Italy.

²INSTM Udr Trieste-ST and Elettra - Sincrotrone Trieste S.C.p.A. in Area Science park, S.S. 14, km 163,5, Basovizza, Trieste, Italy.

³Max Planck Institute for the Structure and Dynamics of Matter, 22761 Hamburg, Germany.

⁴Center for Free-Electron Laser Science (CFEL), 22761 Hamburg, Germany.

⁵CELLS-ALBA, Carretera B.P. 1413, Cerdanyola del Valles, 08290, Spain.

⁶Dipartimento di Fisica e Scienze della Terra, Università di Parma, Parma, Italy.

⁷CNR-IOM-Democritos National Simulation Centre and International School for Advanced Studies (SISSA), Trieste, Italy.

⁸CNR-IOM, and Dipartimento di Fisica, Università di Roma "La Sapienza", Rome, Italy.

Correspondence and requests for materials should be addressed to L.B. (email: leonetta.baldassarre@roma1.infn.it) or S.L. (email: stefano.lupi@roma1.infn.it)

of Cs_3C_{60} shows the emergence of superconductivity from an insulating antiferromagnetic parent state, resembling what found in other high-temperature superconducting families^{17–19} and calls for a deeper understanding of the role of electron-electron interactions in A_3C_{60} compounds^{20,21}, and in particular in Cs_3C_{60} ²².

In this work we have combined novel infrared experimental data with theoretical calculations to shed more light on the strength of electron correlation and on the evolution of the Jahn-Teller interaction in $\text{A15 Cs}_3\text{C}_{60}$ under pressure. Infrared spectroscopy is a powerful technique to study the low-energy electro-dynamics of solids as it yields information on both the electronic and vibrational degrees of freedom. By measuring the optical conductivity, the pressure-driven metallization process can be traced by the emergence of a Drude term in the spectra. On the other hand, a splitting of the phonon lines indicates a symmetry reduction, possibly associated with a Jahn-Teller distortion.

In this paper we investigate the low-energy electro-dynamics and the insulator to metal transition of Cs_3C_{60} under pressure at room temperature. We find that a strongly correlated bad metallic state is established at rather low pressures in concomitance with the Jahn-Teller distortion which maintains and stabilizes in the metallic phase. This result suggests that in the proximity of the Mott transition may enhance the electron-phonon interaction leading to the relatively high superconducting critical temperature in the A15 structure.

Results

Infrared Data. At ambient conditions the reflectivity at the sample-diamond interface R_{S-D} is almost flat, and shows the infrared signatures of the T_{1u} vibrational modes at about 570 and 1370 cm^{-1} . For increasing values of the applied pressure (indicated in Fig. 1 by the grey arrow), R_{S-D} raises towards low-frequency, suggesting the onset of a carrier-delocalisation process. In Fig. 1E are reported the optical conductivity curves $\sigma_1(\omega)$ achieved by Kramers-Kronig transformation from R_{S-D} data (see the Method section) up to 6000 cm^{-1} . Already at 4.0 and 6.0 kbar the conductivity level increases towards low frequency through a transfer of spectral weight from above to below an isosbestic point around 2000 cm^{-1} . The insulator to metal transition occurs around 13 kbar where a Drude term clearly shows up in the spectra and $\sigma_1(\omega)$ monotonically increases for $\omega \rightarrow 0$. Noteworthy, in the metallic phase of Cs_3C_{60} the absolute value of $\sigma_1(\omega)$ is that of a poor metal as also observed in Rb_3C_{60} , K_3C_{60} ²³ and in $\text{Na}_2\text{CsC}_{60}$ ²⁴.

At the lowest pressure the phonon mode at 570 cm^{-1} is symmetric (see Fig. 1F), as found also in ref. 25. When the system at high pressure becomes metallic, this phonon mode couples with the electronic continuum and shows the signature of a Fano-like distortion, similarly to what found in the metallic A_3C_{60} ($A = \text{Rb}, \text{K}$) compounds. The phonon mode centered at 1370 cm^{-1} (Fig. 1G) shows instead a splitting in three peaks, that becomes more evident at the highest measured pressure. Let us observe that the splitting of this phonon is in excellent agreement with what shown in ref. 25, also perfectly confirming the calculations performed in ref. 26.

Discussion

Electronic correlation. To assess the importance and the strength of the Coulomb repulsion U in determining the ground state of Cs_3C_{60} we can compare the experimental results with theoretical calculations.

The ratio between the experimental kinetic energy (K_{exp}) and that obtained via band structure “mean-field” calculations (K_{LDA}) can be used to determine the “degree of correlation” of a material. Such a ratio spans between 0 (characteristic of a Mott insulator) to 1, as in the case of conventional metals^{27–30}. The K_{exp}/K_{LDA} ratio is shown in Fig. 2 for Cs_3C_{60} . K_{exp} was obtained from the integral of $\sigma_1(\omega)$ for a cut-off frequency of 900 cm^{-1} , which captures practically all the Drude spectral-weight, as can be seen in the Drude-Lorentz fit shown in Fig. 1D. The error-bars in Fig. 2 take into account an indetermination of $\pm 100\text{ cm}^{-1}$ in choosing the cutoff energy for the Drude term. K_{LDA} are instead calculated through Density-Functional Theory (DFT) using the crystal structure relative to different pressure values (see Methods). K_{exp}/K_{LDA} values are below 0.1, placing Cs_3C_{60} at the verge of the Mott transition²⁷. With increasing pressure K_{exp}/K_{LDA} raises, mirroring the increase of spectral weight at the Fermi energy, i.e. representing the emergence of a quasi-particle peak in the density of states. The Drude peak that shows up in Cs_3C_{60} above 13 kbar does not resemble that measured in the metallic phases of K_3C_{60} or Rb_3C_{60} ³¹. Here, a broad Drude term can be found, superimposed to the HOMO-LUMO excitations at about 1 eV . Instead in Cs_3C_{60} , a relatively small Drude term is present, whereas a broad absorption band is still visible slightly below 2000 cm^{-1} .

To further understand the importance of electron-electron correlation on Cs_3C_{60} , we compare the experimental results with calculations combining DFT with Dynamical Mean-Field Theory (DMFT). The impurity model is solved at 300 K by finite-temperature exact diagonalization³². From DMFT we have computed K_{exp}/K_{DMFT} that turns out to be (Fig. 2) nearly constant (and equal to 1), for increasing pressure. This highlights that DMFT correctly captures the pressure-driven appearance of the quasi-particle peak and its effect on the kinetic energy. (see Fig. 2). The corresponding theoretical optical conductivity curves are reported in Fig. 3 where it is possible to follow the partial closure of the gap and at the same time the growth of the Drude term by increasing pressure. The theoretical result describes the evolution of $\sigma_1(\omega)$ with pressure accurately, corroborating that electron-electron correlation plays a major role in the physics of Cs_3C_{60} and mainly determines the Insulator-to-Metal transition. Noteworthy, both

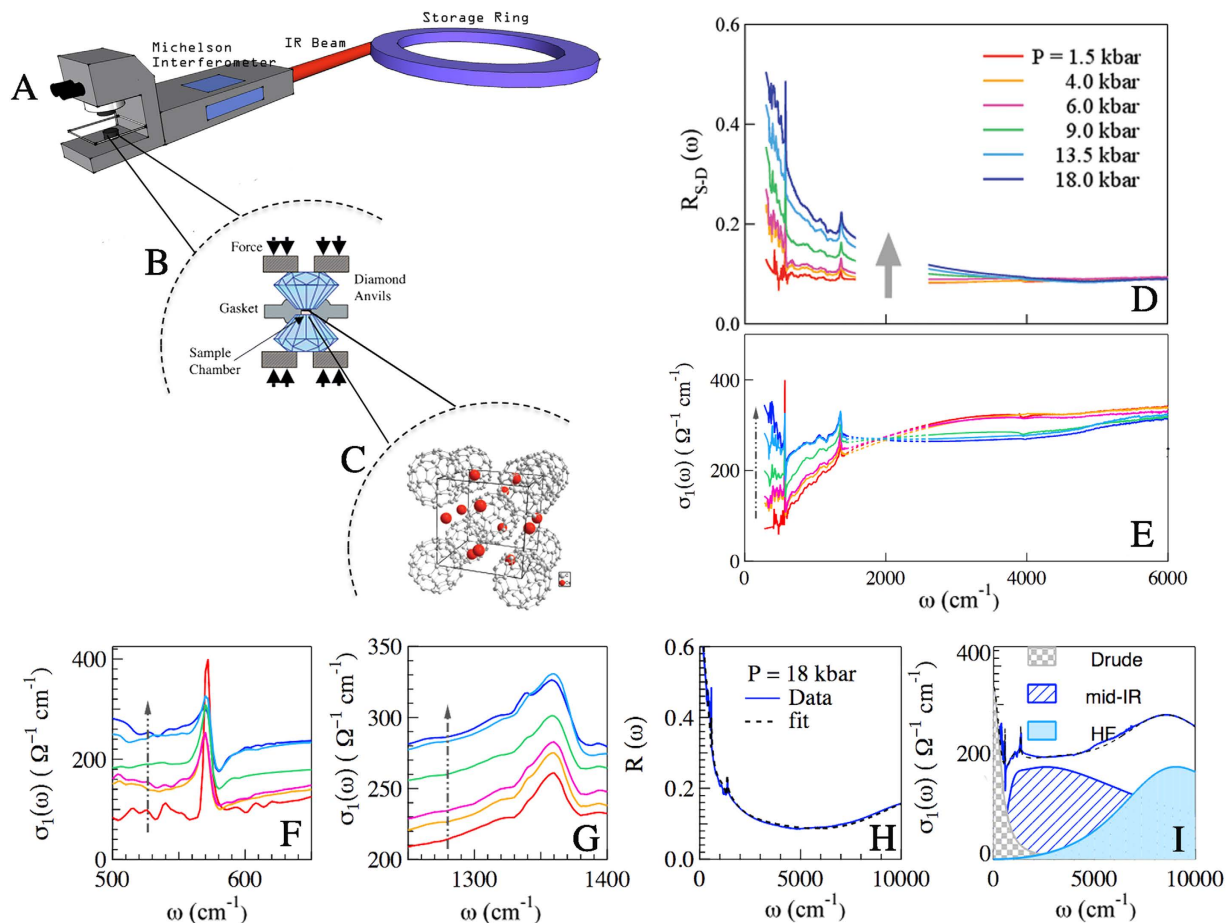


Figure 1. (A) Sketch of the experimental end station of SISSI beam line at ELETTRA Storage Ring. A Michelson interferometer from Bruker is coupled to an IR Hyperion 2000 microscope able to measure both the infrared spectra and, in the same experimental condition, the ruby fluorescence. (B) Cartoon of the Diamond Anvil Cell (DAC). A Cs_3C_{60} pellet is placed in the DAC sample chamber creating a clean interface with the upper diamond culet; (C) Crystal structure of A-15 Cs_3C_{60} ; (D) Reflectivity at the sample-diamond interface at a number of pressures indicated in Figure. The arrow indicates the direction of increasing pressure. Data are not shown between $1700\text{--}2600\text{ cm}^{-1}$ due to not perfect compensation of the diamond phonon absorptions in this spectral region. (E) The optical conductivity is shown in the same frequency range and at the same pressures. The dashed area corresponds to the frequency range where diamond absorption occurs; $\sigma_1(\omega)$ is shown in (F,G) over a reduced frequency range to better highlight the evolution of the phonon modes with pressure; In (H,I) are reported the experimental reflectivity and the optical conductivity obtained by Kramers-Kronig transformation with the fitting curves resulting from simultaneous fitting of R_{S-D} and $\sigma_1(\omega)$ with a Drude-Lorentz model.

theoretical and experimental curves show the coexistence of the Drude term with a mid-infrared absorption band, as an infrared signature of strong correlation³³. This also occurs at the pressure values where superconductivity is found at low temperature, confirming the belief that the superconductivity emerges from a strongly correlated metallic phase²⁰.

Phonon modes. Besides the strong electron-electron interactions, the molecular Jahn-Teller effect plays a pivotal role in the physics of fullerides. The coupling with the Jahn-Teller active H_{1g} modes is the largest contribution to the electron-phonon coupling, and it is widely believed to be responsible of the superconducting pairing. In particular, it has been demonstrated that a Jahn-Teller coupling can survive and even benefit from the strong correlations identified in the present study¹⁴.

Recently some authors²⁵ have discussed the fingerprints of the molecular Jahn-Teller effect in the optical spectra of Cs_3C_{60} at ambient pressure. By lowering the temperature below 300 K, a splitting of this phonon mode has been detected, hinting to the presence of a dynamical Jahn-Teller distortion. While at room temperature and above, the thermal expansion results in a weaker crystal field that does not select

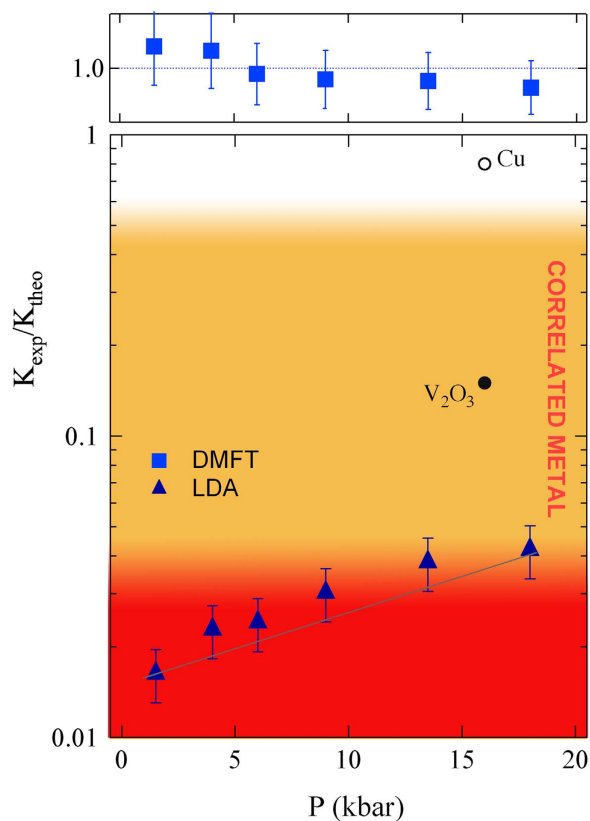


Figure 2. Evolution with pressure of the degree of correlation. The ratio of the experimental and the “mean-field” theoretical kinetic energy K_{exp}/K_{LDA} ratio (triangles) is compared with data from ref. 28 on V_2O_3 and Cu. K_{exp}/K_{LDA} increases with increasing pressure indicating a smooth transition from a Mott insulator to a correlated metal. On the other hand, K_{exp}/K_{DMFT} (squares) is nearly constant at 1. This indicates that DMFT is taking correctly into account the electron-electron correlation, capturing the pressure-driven appearance of the quasi-particle peak.

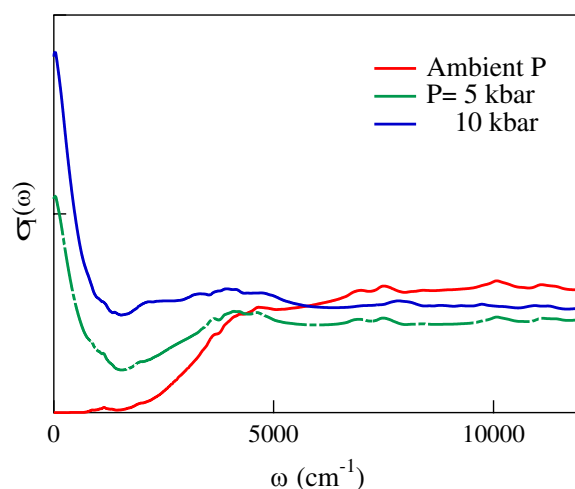


Figure 3. Optical conductivity curves obtained by DMFT calculations at room temperature, at ambient pressure and at 5 and 10 kbar.

a preferred direction of the distorted molecule, by decreasing T the population of two possible solid-state conformers starts to differ and a clear splitting in the phonon mode at 1370 cm^{-1} is found.

In our study a shoulder in the 1370 cm^{-1} phonon is visible already at the lowest measured pressure, however the splitting becomes more evident for increasing pressure, even at room- T , where instead at

ambient pressure, it was argued²⁵ that no preferred direction was chosen by the distorted molecule. A preferred direction seems to be present instead at high-pressure, likely due to a modification of the local crystal field with pressure. A similar behaviour has been recently discussed on $\text{Rb}_x\text{Cs}_{3-x}\text{C}_{60}$, where the interfulleride distance is controlled via chemical substitution rather than by external pressure³⁴.

Therefore, our data show that pressure can drive the system metallic while maintaining (and stabilizing) a dynamical Jahn-Teller distortion. These results confirm that the Jahn-Teller effect is not a main force in the stabilization of the insulating behavior, which is indeed solely due to the Mott localization of carriers. Interestingly, the present data show that the Jahn-Teller coupling is more effective when the system becomes metallic, either by increasing the pressure or reducing the temperature, a result fully compatible with the scenario in which a Jahn-Teller coupling leads to superconductivity in the strongly correlated metal close to the Mott transition²⁰.

Conclusions

In conclusion, pressures in the kbar range are sufficient to drive Cs_3C_{60} in a metallic state, while signatures of strong electron correlation persist up to the highest measured pressure. Cs_3C_{60} is thus found to be at the verge of a Mott-Hubbard Insulator-to-Metal transition: by applying an external pressure a carrier-delocalization is induced corresponding to a poor-metallic state where dynamical Jahn-Teller distortions are maintained and stabilized.

The comparisons with DMFT theoretical calculations support the claim that electron-electron correlation is the sole responsible for the insulating state at ambient conditions and can alone explain the low-energy Cs_3C_{60} evolution across the IMT. Noteworthy, strong correlation persists at high pressure and therefore it has to be considered in order to reach a full understanding of superconductivity in Cs_3C_{60} . On the other hand, the relevance of the Jahn-Teller coupling in the metallic state confirms the theoretical scenario in which the phonon coupling survives in the presence of strong correlations.

Methods

Sample preparation and characterization. A15-rich Cs_3C_{60} sample was obtained via a solvent-mediated synthesis route. Stoichiometric amount of Cs metal (Aldrich, >99.5% purity) and C_{60} powder (MER >99.9%) were put in a Pyrex vial in a controlled atmosphere (Ar glove-box, <0.1 ppm O_2 and H_2O), having particular care to avoid the direct contact between the reagents in this stage. The vial was then evacuated ($P < 10^4$ mbar) and placed in a methanol bath at -60 degrees Celsius and previously degassed anhydrous methylamine (Aldrich >98% purity) was condensed under continuous stirring. At this step the solution became dark-red, due to the dissolution of the alkali metal in the solvent. Hence, the vessel was sealed and slowly heated at $T = 50$ degrees Celsius and let react for one night under stirring. After reaction took place the color of the suspension became dark brown. Methylamine was slowly evaporated at -5 degrees Celsius and the dry product was collected in glove box, then it was pelletized and further treated in dynamic vacuum for 20 h at 200 degrees Celsius. Quantitative Phase Analysis (QPA) of the product was performed by synchrotron radiation powder diffraction, and indicated a phase fraction of respectively 74(1)% A15, 14(1)% fcc and 12(1)% bco.

Infrared Spectroscopy under pressure. High pressure measurements were performed with a screw-driven opposing plate Diamond-Anvil-Cell. An Al gasket was chosen to span over the desired pressure range (0–20 kbar) in a reproducible and cyclic way. A hole of about $300 \mu\text{m}$ diameter was drilled in the pre-indented gasket. A small amount of Cs_3C_{60} sample was pressed between the diamond anvils to form a pellet with a thickness of about tens of microns^{35,36}. This thickness yields zero transmission, allowing for reflectivity measurements. The pellet was then loaded in the cell with CsI as pressure medium, taking great care of obtaining a clean diamond-sample interface. As these samples are strongly air-sensitive the whole procedure was done in a glove box and the pressure cell was carefully kept closed for the experiment. The pressure was measured *in-situ* by the standard ruby fluorescence technique³⁷ with a procedure described elsewhere³⁸. Infrared reflectivity measurements were performed with the aid of the Hyperion 2000 Bruker microscope coupled to an IFv66/s Michelson interferometer, exploiting the high brilliance of synchrotron radiation at the infrared beam line SISSI of ELETTRA storage ring³⁹. Reflectivity at the sample diamond interface R_{S-D} was measured with 1 cm^{-1} resolution between $250 \div 15000 \text{ cm}^{-1}$. The real part of the optical conductivity $\sigma_1(\omega)$ was then extracted via Kramers-Kronig (KK) transformations taking care of the sample diamond interface^{38,40}. Simultaneous fitting of R_{S-D} and $\sigma_1(\omega)$ with a Drude-Lorenz model is performed to make sure that the KK procedure has been performed correctly.

Dynamical Mean Field Theory calculations. Our theoretical data are based on the combination of density functional theory (DFT) with Dynamical Mean-Field Theory (DMFT). The DFT band structure of Cs_3C_{60} has been calculated using the Perdew-Burke-Ernzerhof recipe for the generalized gradient approximation by means of the Quantum Espresso package⁴¹ employing a grid of $6 \times 6 \times 6$ k-points. The cutoff energies for wavefunctions and charge densities were set to 45 Ry and 450 Ry, respectively. The calculations are based on the A15 structure of Cs_3C_{60} with Pm3n symmetry with b.c.c. anion packing²³ at ambient pressure without performing structural relaxations, and the pressure dependence is deduced

from the experimental data for the lattice spacings. A tight-binding representation of the band structure is built using Wannier90⁴² to compute the maximally localized Wannier orbitals restricting to the bands originated from the t_{1u} LUMO.

We combine the DFT band structure with the on-site interactions acting on the three-fold degenerate t_{1u} manifold. We considered the large Hubbard U estimated in ref. 43, and we included an attraction term which results from the Jahn-Teller electron-phonon interaction, even if significantly reduced by the Hund's rule coupling, which involves exactly the same operators⁵. As we did not consider structural relaxations, we do not account for the static Jahn-Teller distortions, while we account for the dynamical Jahn-Teller interaction and its effects of the electronic properties. Indeed the two interaction terms have been shown to reproduce the low-temperature phase-diagram of Cs_3C_{60} within model calculations.

Here, we chose the value of the attractive interaction in order to reproduce the spectral gap of the insulating compound at ambient pressure. The value used is $J = 0.07$ eV. The DMFT calculations employ an exact diagonalization solver at finite temperature in the implementation of³² 4 impurity levels per orbital are included for a total number of 15 levels including the impurity site, and the full orbital rotational symmetry is implemented to reduce the Hilbert space. The optical conductivity is computed from the single-particle Green's functions including the vertex functions obtained by differentiation of the DFT band structure with respect to momentum.

References

- Kroto, H. W., Heath, J. R., O'Brien, S. C., Curl, R. F. & Smalley, R. E. C₆₀: Buckminsterfullerene. *Nature* **318**, 162 (1985).
- Iijima, S. Helical microtubules of graphitic carbon. *Nature* **354**, 56 (1991).
- Martin, N., Guldi, D. M. & Echegoyen, L. Carbon nanostructures: Introducing the latest web themed issue. *Chem. Commun.* **47**, 604 (2011).
- Haddon, R. C. *et al.* Conducting films of C₆₀ and C₇₀ by alkali-metal doping. *Nature* **350**, 320 (1991).
- Capone, M., Fabrizio, M., Giannozzi, P. & Tosatti, E. Theory of the metal-nonmagnetic Mott-Jahn-Teller insulator transition in A₃C₆₀. *Phys. Rev. B* **62**, 7619 (2000).
- Gunnarsson, O. Superconductivity in fullerides. *Rev. Mod. Phys.* **69**, 575 (1997).
- Burkhardt, G. J. & Meingast, C., High-resolution thermal expansion of superconducting fullerides A₃C₆₀ (A = K, Rb). *Phys. Rev. B* **54**, R6865 (1996).
- Kortan, A. R. *et al.* Superconductivity in barium fulleride. *Nature* **355**, 529 (1992).
- Ramirez, A. P. C₆₀ and its superconductivity. *Supercond. Rev.* **1**, 1 (1994).
- Riccó, M. *et al.* Metal-to-insulator evolution in (NH₃)_xNaK₂C₆₀: An NMR study. *Phys. Rev. B* **68**, 035102 (2003).
- Durand, P., Darling, G. R., Dubitsky, Y., Zaopo, A. & Rosseinsky, M. J. The Mott-Hubbard insulating state and orbital degeneracy in the superconducting C₆₀- fulleride family. *Nature Mater.* **2**, 605 (2003).
- Dahlke, P., Denning, M. S., Henry, P. F. & Rosseinsky, M. J. Superconductivity in Expanded fcc C₆₀³⁻ Fullerides. *J. Am. Chem. Soc.* **122**, 12352 (2000).
- Capone, M., Fabrizio, M. & Tosatti, E. Direct transition between a Singlet-Mott Insulator and a Superconductor. *Phys. Rev. Lett.* **86**, 5361 (2001).
- Capone, M., Fabrizio, M., Castellani, C. & Tosatti, E. Strongly Correlated Superconductivity. *Science* **296**, 2364 (2002).
- Capone, M., Fabrizio, M., Castellani, C. & Tosatti, E. Strongly Correlated Superconductivity and Pseudogap Phase near a multi-band Mott Insulator. *Phys. Rev. Lett.* **93**, 047001 (2004).
- Ihara, Y. *et al.* NMR Study of the Mott Transitions to Superconductivity in the Two Cs₃C₆₀ Phases. *Phys. Rev. Lett.* **104**, 256402 (2010).
- Timusk, T. & Statt, B. The pseudogap in high-temperature superconductors: an experimental survey. *Rep. Prog. Phys.* **62**, 1 (1999).
- Zorkovska, A. *et al.* Phase diagram of the sodium-rich Na_xCoO₂ cobaltates. *Phys. Status Solidi B* **247**, 665 (2010).
- Paglione, J. P. & Greene, R. L. High-temperature superconductivity in iron-based materials. *Nature Phys.* **6**, 645 (2010).
- Capone, M., Fabrizio, M., Castellani, C. & Tosatti, E. Modeling the unconventional superconducting properties of expanded A₃C₆₀ fullerides. *Rev. Mod. Phys.* **81**, 943 (2009).
- Giovannetti, G. & Capone, M. Electronic Correlations Stabilize the Antiferromagnetic Mott State in Cs₃C₆₀. *Phys. Rev. Lett.* **109**, 166404 (2012).
- Wzietek, P. *et al.* NMR Study of the Superconducting Gap Variation near the Mott Transition in Cs₃C₆₀. *Phys Rev Lett* **112** 066401 (2014).
- Ganin, A. Y. *et al.* Bulk superconductivity at 38 K in a molecular system. *Nature Mater.* **7**, 367 (2008).
- Ruzicka, B., Degiorgi, L. & Forro, L. *AIP Conf. Proc.* **544**, 116 (2000).
- Klupp, G. *et al.* Dynamic Jahn-Teller effect in the parent insulating state of the molecular superconductor Cs₃C₆₀. *Nat. Commun.* **3**, 912 (2012).
- Tosatti, E. Perspective: Fullerides in a Squeeze. *Science* **323**, 1570 (2009).
- Basov, D. N. & Chubukov, A. V. Manifesto for a higher T_c. *Nature Phys.* **7**, 272 (2011).
- Quazilbash, M. M. *et al.* Electronic correlations in the iron pnictides. *Nature Phys.* **5**, 647 (2009).
- Baldassarre, L. *et al.* Electrodynamics of BaFe₂As₂ from infrared measurements under pressure. *Phys. Rev. B* **85**, 174522 (2012).
- Lo Vecchio, I. *et al.* Infrared evidence of a Slater metal-insulator transition in NaOsO₃. *Sci. Rep.* **3**, 2990 (2013).
- Ganin, A. Y. *et al.* Polymorphism control of superconductivity and magnetism in Cs₃C₆₀ close to the Mott transition. *Nature* **466**, 221 (2010).
- Capone, M., De Medici, L. & Georges, A. Solving Dynamical Mean-Field Theory at very low temperature using Lanczos Exact Diagonalization. *Phys. Rev. B* **76**, 245116 (2007).
- Baldassarre, L. *et al.* Quasiparticle evolution and pseudogap formation in V₂O₃: An infrared spectroscopy study. *Phys. Rev. B* **77**, 113107 (2008).
- Zadik, R. H. *et al.* Optimized unconventional superconductivity in a molecular Jahn Teller metal. *Sci. Adv.* **1**, e1500059 (2015).
- Arcangeletti, E. *et al.* Evidence of a Pressure-Induced Metallization Process in Monoclinic VO₂. *Phys. Rev. Lett.* **98**, 196406 (2007).
- Marini, C. *et al.* Optical properties of high-pressure V_{1-x}Cr_xO₂ compound. *Phys. Rev. B* **67**, 165132 (2008).
- Mao, H.-K., Xu, J. & Bell, P. M. Calibration of the ruby pressure gauge to 800 kbar under quasi-hydrostatic conditions. *J. Geophys. Res.* **91**, 4673 (1986).
- Lupi, S. *et al.* A microscopic view on the Mott transition in chromium-doped V₂O₃. *Nat. Commun.* **3**, 652 (2010).

39. Lupi, S. *et al.* Performances of the infrared SISSI beamline at Elettra. *J. Opt. Soc. Am. B* **24**, 959 (2007).
40. Plaskett, J. S. & Schatz, P. N. On the Robinson and Price (Kramers-Kronig) method of interpreting reflection data taken through a transparent window. *J. Chem. Phys.* **38**, 612 (1963).
41. Giannozzi *et al.* QUANTUM ESPRESSO: a modular and open-source software project for quantum simulations of materials *J. Phys. Condens. Matter* **21**, 395502 (2009).
42. McMahan, A. K., Annett, J. F. & Martin, R. M. Cuprate parameters from numerical Wannier functions. *Phys. Rev. B* **42**, 6268 (1990).
43. Nomura, Y., Nakamura, K. & Arita, R. Ab initio derivation of electronic low-energy models for C_{60} and aromatic compounds. *Phys. Rev. B* **85**, 155452 (2012).

Acknowledgements

A.P. acknowledges support from Italian Ministry of Research (MIUR) program FIRB “Futuro in Ricerca” grant no. RBFR10PSK4.

Author Contributions

L.B., A.P., M.M., D.N. and C.M. performed the infrared measurements and data analysis. M.C. and G.G. wrote the theoretical code; D.P., M.M., M.A. and M.R. synthesized the samples. S.L. proposed and coordinated the experiment. L.B. and M.C. discussed the results and wrote the paper with inputs from all the co-authors.

Additional Information

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Baldassarre, L. *et al.* The strength of electron electron correlation in Cs_3C_{60} . *Sci. Rep.* **5**, 15240; doi: 10.1038/srep15240 (2015).



This work is licensed under a Creative Commons Attribution 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>