



UNIVERSITÀ DI PARMA

ARCHIVIO DELLA RICERCA

University of Parma Research Repository

Tuning the magnetic and structural phase transitions of PrFeAsO via Fe/Ru spin dilution

This is the peer reviewed version of the following article:

Original

Tuning the magnetic and structural phase transitions of PrFeAsO via Fe/Ru spin dilution / Yuen, Yiu; Bonfa', Pietro; Samuele, Sanna; DE RENZI, Roberto; Pietro, Carretta; Michael A., Mcguire; Ashfia, Huq; Stephen E., Nagler. - In: PHYSICAL REVIEW. B, CONDENSED MATTER AND MATERIALS PHYSICS. - ISSN 1098-0121. - 90:(2014), p. 064515. [10.1103/PhysRevB.90.064515]

Availability:

This version is available at: 11381/2753111 since: 2017-05-12T19:27:00Z

Publisher:

Published

DOI:10.1103/PhysRevB.90.064515

Terms of use:

Anyone can freely access the full text of works made available as "Open Access". Works made available

Publisher copyright

note finali coverpage

(Article begins on next page)

Tuning the magnetic and structural phase transitions of PrFeAsO via Fe/Ru spin dilution

Yuen Yiu,^{1,*} Pietro Bonfà,² Samuele Sanna,³ Roberto De Renzi,² Pietro Carretta,³ Michael A. McGuire,⁴ Ashfia Huq,⁵ and Stephen E. Nagler^{1,6,7}

¹*Department of Physics and Astronomy, University of Tennessee, Knoxville, TN 37996, USA*

²*Department of Physics and Earth Sciences, University of Parma, 43124 Parma, Italy*

³*Department of Physics, University of Pavia, 27100 Pavia, Italy*

⁴*Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

⁵*Chemical and Engineering Materials Division, Neutron Sciences Directorate, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

⁶*Quantum Condensed Matter Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

⁷*CIRE, University of Tennessee, Knoxville, TN 37996, USA*

(Received 11 July 2014; revised manuscript received 7 August 2014; published 25 August 2014)

Neutron diffraction and muon spin relaxation measurements are used to obtain a detailed phase diagram of PrFe_{1-x}Ru_xAsO. The isoelectronic substitution of Ru for Fe acts effectively as spin dilution, suppressing both the structural and magnetic phase transitions. The temperature T_S of the tetragonal-orthorhombic structural phase transition decreases gradually as a function of x . Slightly below T_S , coherent precessions of the muon spin are observed corresponding to static magnetism, possibly reflecting a significant magnetoelastic coupling in the FeAs layers. Short-range order in both the Fe and Pr moments persists for higher levels of x . The static magnetic moments disappear at a concentration coincident with that expected for percolation of the J_1 - J_2 square-lattice model.

DOI: [10.1103/PhysRevB.90.064515](https://doi.org/10.1103/PhysRevB.90.064515)

PACS number(s): 28.20.Cz, 65.40.De, 76.75.+i, 74.20.Mn

I. INTRODUCTION

The precise role of magnetism and its coupling to the lattice is a central problem in the physics of unconventional iron-based superconductors and related materials [1–3]. In general, the undoped parent compounds of the 1111 family iron-pnictide superconductors are tetragonal paramagnets at high temperatures. Upon cooling, they display a tetragonal-orthorhombic structural transition at T_S , followed or accompanied by a spin-density-wave (SDW) transition at T_{SDW} [2,4,5]. Superconductivity can usually be induced by suppressing these transitions and inevitably results when this is done by using dopants that introduce charge carriers. The use of isovalent dopants, for example the substitution of Ru for Fe, allows for investigations of the physics without the complications induced by changing the electron count. In the 122 family compound BaFe_{2-x}Ru_xAs₂ the suppression of the structural and magnetic transitions via Ru substitution indeed results in a superconducting ground state, but at a much larger Ru content than has been observed with nonisovalent dopants [6,7]. Investigations of the 1111 compounds including PrFe_{1-x}Ru_xAsO and LaFe_{1-x}Ru_xAsO also showed that Ru/Fe substitution suppresses the structural and magnetic phase transitions, but in contrast to the 122s, there is no observation of a superconducting ground state for any concentration of Ru [8–11].

Arguably, when Ru is substituted for Fe in the 1111 compounds, the main effect on the magnetism can be understood by considering the substitution as simply equivalent to spin dilution. This is consistent with local density approximation calculations on LaFe_{1-x}Ru_xAsO [12], which illustrates that Ru atoms do not show any tendency to sustain a magnetic moment regardless of their concentration. This is also compatible with previous experimental data on PrFe_{1-x}Ru_xAsO [8]. In this

paper, we present a systematic study of the evolution of the magnetic and structural transitions in the isovalently doped PrFe_{1-x}Ru_xAsO system. The neutron diffraction measurements of Ref. [10] have been extended and complemented by new muon spin relaxation measurements. The previous neutron work [10] showed no evidence for the structural transition in PrFe_{1-x}Ru_xAsO above $x = 0.4$ as determined by Rietveld refinements. The magnetic transition in the FeAs layers was not detected beyond $x = 0.1$. The $x = 0.1$ sample was previously measured using elastic scattering at the HB1A triple axis spectrometer [10], and was not sensitive to ordered moment sizes less than $0.02\mu_B$. The other neutron diffraction measurements had significantly lower sensitivities. The sensitivity of μ SR ($\approx 0.001\mu_B$) is therefore more than an order of magnitude better than the neutron measurements, enabling a more complete determination of the phase diagram. Remarkably, it is observed that all signatures of magnetic order disappear at the percolation concentration of the J_1 - J_2 square-lattice model. We also note that the negative thermal expansion (NTE) reported earlier in PrFe_{1-x}Ru_xAsO [10,13] persists across the entire Ru doping range even for pure PrRuAsO.

This paper is organized as follows: Sample synthesis is described in Sec. II, bulk characterization and neutron diffraction results in Sec. III, and μ SR results in Sec. IV. Discussion and conclusions follow in Secs. V and VI, respectively.

II. SAMPLE SYNTHESIS

Methods reported earlier [8,14] were used to synthesize the samples. PrFe_{1-x}Ru_xAsO samples were made from powders of PrAs, Fe₂O₃, RuO₂, Fe, and Ru. The starting materials were crushed and mixed inside a He glovebox, then pressed into $\frac{1}{2}$ -in. diameter pellets (~ 2 g each) and placed in covered alumina crucibles inside silica tubes. The tube was evacuated, backfilled with ultrahigh-purity Ar, and flame sealed. Each

*yyiu@utk.edu

individual sample was heated at 1200 °C for 12–36 h several times, and was thoroughly ground and pressed into pellets between the heating cycles.

III. BULK CHARACTERIZATION AND NEUTRON DIFFRACTION RESULTS

Heat-capacity and dc magnetic susceptibility measurements were performed using the MPMS SQUID and PPMS system by Quantum Design. The results for $0 \leq x \leq 0.75$ were presented in Ref. [10]. Figure 1(a) shows the reciprocal magnetic susceptibility temperature dependence for $x = 1$, i.e., PrRuAsO, with no indication of superconductivity down to 2 K. The Curie-Weiss law describes the data well down to 14 K. Data points for $T > 50$ K were fitted to the Curie-Weiss law, with the resultant fit intersecting the temperature axis at $T_{CW} = -33(5)$ K with a Curie constant of 1.4(1), close to the expected value of 1.6 for Pr^{3+} . Figure 1(b) shows the field dependence of the magnetization at $T = 2$ K, with no sign of saturation up to 6 T. Figure 1(c) shows the temperature dependence of the heat capacity. The data for $x = 1$ are very similar to the data for all concentrations $x > 0$, with a broad hump observed around 14 K, coinciding with the Néel temperature for Pr ordering in PrFeAsO. This is presumably related to short-range order involving the Pr spins.

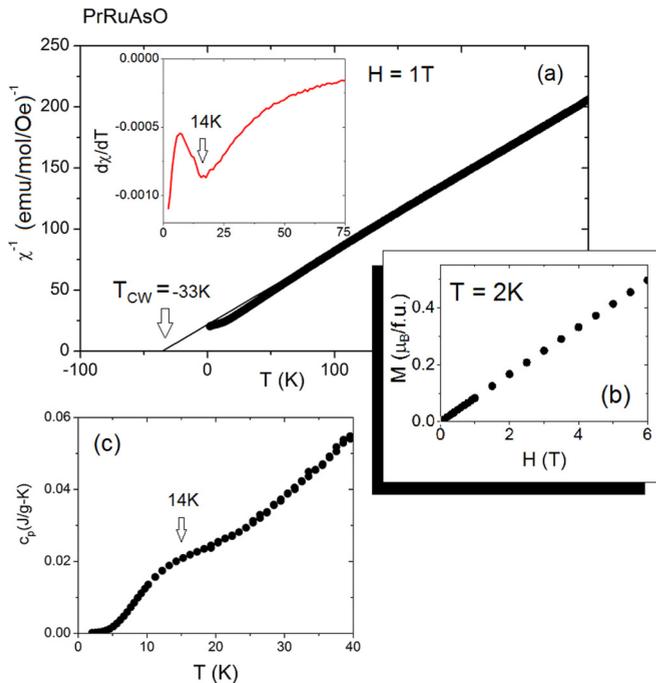


FIG. 1. (Color online) (a) Temperature dependencies of the reciprocal susceptibility for PrRuAsO. The anomaly around 14 K is possibly related to magnetic ordering of the Pr sublattice. The straight line is the Curie-Weiss law fitted to data above 50 K. (a, inset): $d\chi/dT$ vs T , better illustrating the anomaly at 14 K. (b) Field dependence of the magnetic susceptibility at $T = 2$ K, with no sign of moment saturation up to 6 T. (c) Temperature dependence of heat capacity. Similar to that from the $x = 0.1 - 0.75$ samples, the sharp peak in PrRuAsO at $T_{N,\text{Pr}} = 14$ K is suppressed, but a broad hump remains [10].

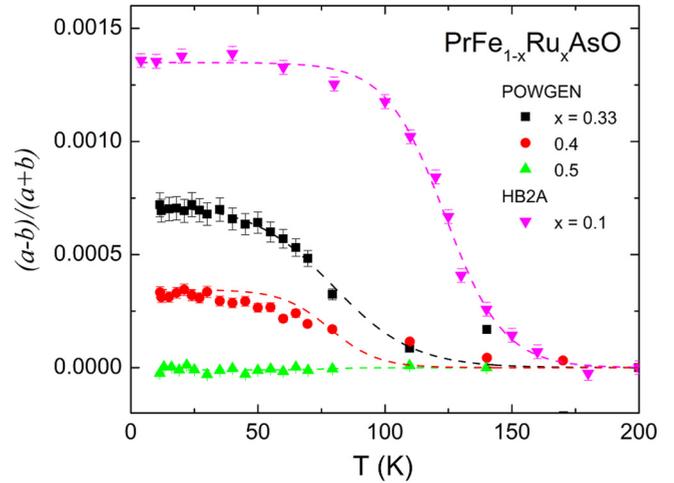


FIG. 2. (Color online) Temperature dependence of the orthorhombicity for $\text{PrRu}_{1-x}\text{Ru}_x\text{AsO}$ as discussed in the text. The lines are guides to the eye.

As discussed in the following, μSR provides evidence for local quasistatic fields below $T \approx 14$ K.

Neutron powder diffraction was performed using POWGEN at the Spallation Neutron Source of Oak Ridge National Laboratory. Rietveld refinement of the data confirmed that PrRuAsO is isostructural to PrFeAsO at room temperature, and remains in the tetragonal $P4/nmm$ structure down to the base temperature of 10 K, similar to other $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ samples with $x \geq 0.33$ [10]. Some of the figures below include data previously reported [10]. In Ref. [10] the neutron diffraction was analyzed via Rietveld refinement, and the transition temperature was determined by whether or not the quality of fit was better for the orthorhombic or tetragonal structure. For $x = 0.4$, the difference in quality of fit was undetectable down to base temperature, and it was concluded that the structure was tetragonal. As described in the next paragraph, here we have reanalyzed that data using a different criterion for identifying the transition.

Figure 2 shows the temperature dependence of the orthorhombicity, defined as $(a - b)/(a + b)$. At high temperature, all of the samples are tetragonal and the orthorhombicity is zero by definition. The orthorhombicity values plotted in Fig. 2 were determined as follows: lattice parameters a and b were extracted by imposing an orthorhombic structure on the Rietveld refinement over the entire temperature range for all samples. For each doping concentration, the fitted value $(a - b)/(a + b)$ determined by the refinement to an orthorhombic structure at $T = 200$ K was subtracted from the corresponding values at other temperatures. This analytical method is useful for detecting structural transitions that are too subtle to be observed via the splitting or broadening of a single nuclear Bragg peak. The data show clear evidence for the structural transition temperature T_S in samples up to $x = 0.4$. (Here, T_S is defined operationally as the temperature at which the orthorhombicity reaches $\frac{1}{2}$ of the asymptotic low-temperature value.) For samples with $x \geq 0.5$, no deviation from zero orthorhombicity can be detected at any temperature.

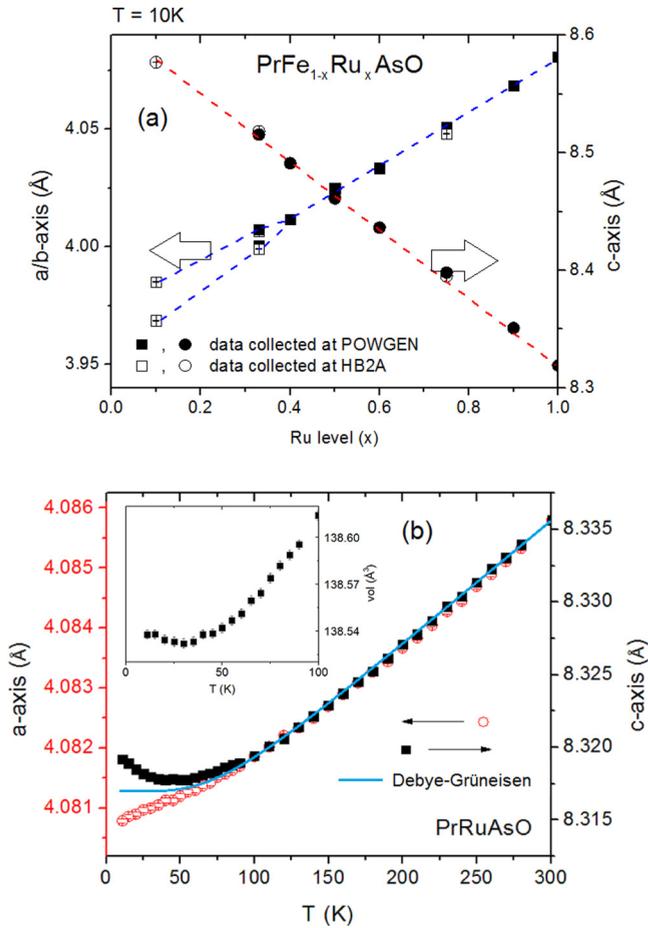


FIG. 3. (Color online) (a) Doping dependence of lattice parameters a , b , and c . Data for $x \neq 1$ are from Ref. [10]. (b) T dependence of lattice parameters a and c for PrRuAsO. The solid (blue) line shows Debye-Grüneisen fit (see Ref. [10]) for $T \geq 100$ K. The inset shows the T dependence of the cell volume. The effect of NTE in the c axis is somewhat compensated by the opposing behavior of the a axis.

Figure 3(a) shows the doping dependence of lattice parameters a , b , and c (including some data previously published in Ref. [10]). As Fe is substituted by Ru, the in-plane (a, b) axis elongates, and the out-of-plane c axis shrinks [8]. The difference of the lattice parameters between $x = 0$ and 1 is of the order of a few percent. Figure 3(b) shows the temperature dependence of a and c for PrRuAsO. As reported previously [10,13], for $x \leq 0.75$, PrFe $_{1-x}$ Ru $_x$ AsO exhibits NTE in the c axis for temperatures below approximately 50 K. The NTE is also observed clearly in stoichiometric PrRuAsO. The magnitude of NTE in the c axis is about 0.02% relative to the minimum at 50 K. The a axis shrinks more than that predicted by the Debye-Grüneisen model, and compensates somewhat for the NTE in the c axis, resulting in a smaller NTE as determined by the unit-cell volume shown in Fig. 3(c). This compensating behavior can be explained by considering that an expansion in the a - b plane forces the unit cell to shorten along c in order to satisfy Fe/Ru-As bonding requirements [8]. The opposite signs of the x dependence of the a - b and c lattice parameters can similarly be understood. The in-plane expansion as a function of x has been attributed

to the substitution of larger Ru atoms for Fe atoms, which stretches along the a - b plane [8].

IV. μ SR

Zero-field (ZF) and longitudinal-field (LF) μ SR experiments were performed on the GPS spectrometer at the Laboratory for Muon Spin Spectroscopy of Paul Scherrer Institut. Here, the findings are presented in two parts, one for the SDW ordering involving FeAs layers, and the other for the magnetic ordering of the Pr moment.

A. SDW ordering

The following methods were used to interpret the data. For the ZF data, the time dependence of the spin-polarization function for a positive, 100% spin-polarized muon in a magnetic sample can be described as

$$\frac{A_{ZF}(t)}{A_0} = (1 - V_m)e^{-\frac{\sigma_i^2 t^2}{2}} + \sum_{i=1}^N f_i [w_i^\perp F_i(t)e^{-\frac{\sigma_i^2 t^2}{2}} + w_i^\parallel e^{-\lambda_i t}], \quad (1)$$

where A_{ZF} is the asymmetry of the muon decay and A_0 is the initial muon asymmetry (i.e., $t = 0$). V_m represents the fraction of muons probing a static local field \mathbf{B}_i , i.e., the sample's magnetic volume fraction. The index i represents each of N crystallographically inequivalent muon stopping sites, and each stopping site is characterized by a stopping probability f_i , with $\sum_{i=1}^N f_i = V_m$. The two terms in the square brackets reflect the orientation of the internal field with respect to the initial muon spin S_μ direction: transverse for $\mathbf{B}_i \perp S_\mu$ and longitudinal for $\mathbf{B}_i \parallel S_\mu$. For powder samples, the ratio of the two terms is related and normalized by $w_i^\perp = 2/3$ and $w_i^\parallel = 1/3$.

The longitudinal component (\parallel) can be described by a Lorentzian decay function with relaxation rate λ . For the transverse component (\perp), $F_i(t)$ represents the time dependence, and σ_i is the depolarization rate which reflects the second moment of the field distribution $\Delta B_i \equiv (\overline{B_i^2} - \overline{B_i}^2)^{1/2} = \sigma_i/\gamma_\mu$, where $\gamma_\mu/2\pi = 136$ MHz/T is the muon gyromagnetic ratio. When the muon goes through a local field B_i , for example inside a long-range-ordered sample, the muon asymmetry displays Larmor oscillations described with $F_i = \cos(\gamma_\mu B_i t)$, with B_i proportional to the mean magnetic order parameter $\langle S(T) \rangle$. In case of a short-range-ordered sample, the width of the field distribution at the muon site broadens and as a result, the transverse muon fraction yields to a fast decay rate ($\sigma_i \gtrsim 1/\gamma_\mu B_i$), with overdamped oscillations and $F_i = 1$.

For the undoped parent PrFeAsO, the ZF- μ SR time spectra are well fitted with $N = 2$ and occupancy $f_1 \approx 75\%$ and $f_2 \approx 25\%$, which reflects the presence of two inequivalent muon sites [15–17]. In the $x = 0.33$ and 0.4 samples, the two frequencies are still detectable, but with f_2 reduced in half. The complementary missed amplitude gives rise to overdamped oscillations and can be easily fitted as a third additional nonoscillating component $i = 3$, with $f_3 \approx f_2$, $F_3 = 1$, and $\sigma_3 \sim 5 \mu\text{s}^{-1}$. This change might be simply due to the increase of disorder by Ru.

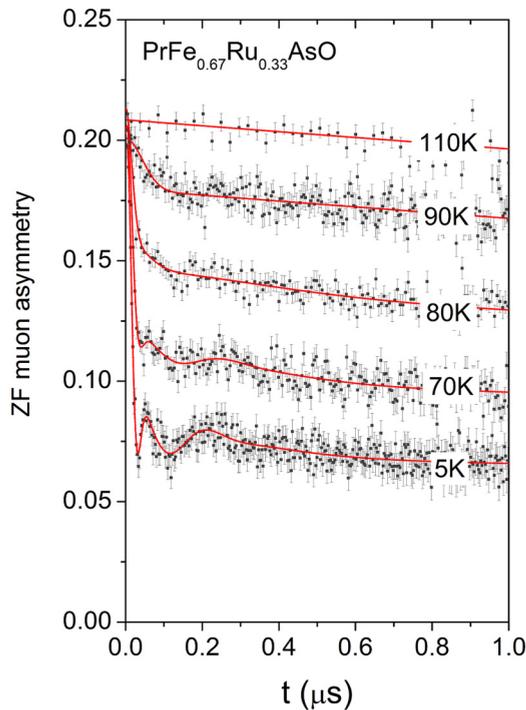


FIG. 4. (Color online) Time dependence of ZF- μ SR asymmetry for $x = 0.33$ between 110 and 5 K, the lines represent the best fit using Eq. (1).

These three components provide a good fit of the time evolution of the ZF muon asymmetry, as seen in Fig. 4, which shows data for $x = 0.33$ at different temperatures, fitted with Eq. (1). At higher temperatures, the oscillations become overdamped and the transverse amplitude ($\propto V_m$) reduces and vanishes at $T \geq 100$ K. Figure 5 displays the low-temperature ZF- μ SR time spectra for all our samples. For $x = 0.5$ and 0.6 , the coherent oscillations are absent and the fit uses only two components but with $F_1 = F_2 = 1$, suggesting that the increase of Ru/Fe substitution induces field inhomogeneity. Accordingly, the presence of the magnetic phase is reflected by the sizable decay rate detected corresponding to $\Delta B_1 \approx 40$ mT and $\Delta B_2 \approx 5$ mT. The same behavior has also been reported in Ru/Fe substituted LaFeAsO [9] at a similar doping level.

Figure 5 shows the components with fast decay rates in samples from $x = 0$ up to 0.6 which are also characterized by the longitudinal fraction $\Sigma_i w_i^{\parallel} = 1/3$, typical of fully magnetic samples. The lack of a fast decay component in the $x = 0.75$ and 1 samples indicates that Fe moments do not order in those samples. However, for T below ≈ 14 K, the fit of the LF muon asymmetry requires two nonoscillating amplitudes with distinct relaxation rates, as shown in Figs. 6(a) and 6(b). This behavior can be attributed to activities in the Pr sublattice around $T_{\text{Pr}} \approx 14$ K, where there are noticeable features in both the susceptibility and specific-heat measurements (Fig. 1 and Ref. [10]). We will discuss this point again later in Sec. IV B.

To summarize, the temperature dependence of the magnetic volume fraction for all samples is shown in Fig. 7. We are able to detect ordering in the FeAs layer up to $x = 0.6$. For the

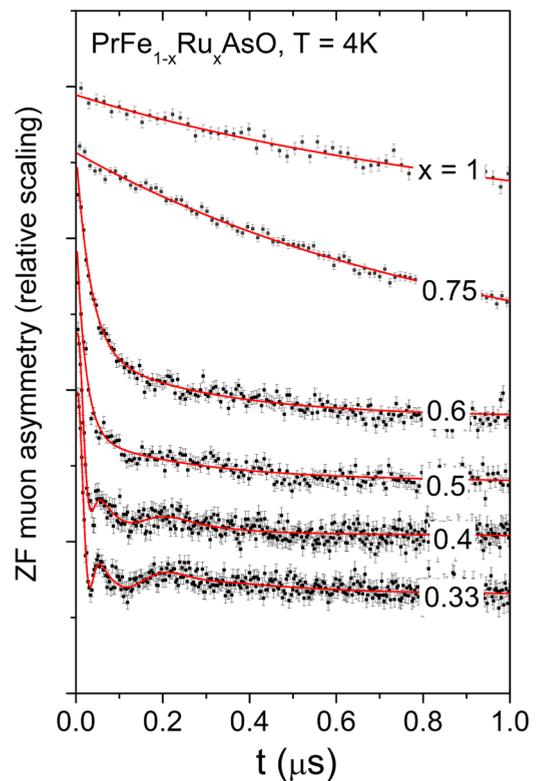


FIG. 5. (Color online) Time dependence of ZF- μ SR asymmetry for $x = 0.33, 0.4, 0.5, 0.6, 0.75$, and 1 at $T = 4$ K. For graphing purposes, each composition is shifted along the vertical axes by an arbitrary constant.

construction of a phase diagram later in this paper, we define T_{SDW} as the temperature at which the magnetic volume fraction is 80%. For $x \leq 0.40$, the magnetic transition temperatures T_{SDW} can be directly determined from the evolution of the mean magnetic order parameter $\langle S(T) \rangle \propto B_i(T)$ as a function of temperature, shown in Fig. 7(b). The magnetic order parameter $\langle S(T) \rangle$ has been successfully fit to the phenomenological function $\langle S(T) \rangle = S(0)[1 - (T/T_{\text{SDW}})^{2.4}]^{0.24}$, which is found to hold generally for REFeAsO (RE: rare earths) compounds [15]. The values of T_{SDW} determined using the two criteria are consistent to within about 2 K.

B. Pr magnetic ordering

Previous neutron diffraction measurements did not detect long-range ordering (LRO) of Pr in samples with $x \geq 0.1$ [10]. However, the μ SR data show that the muon relaxation rate increases below $T \sim 14$ K in PrFe_{0.25}Ru_{0.75}AsO [see Fig. 6(a)], hinting at a possible short-range ordered (SRO) state involving the Pr sublattice. Figure 6(b) shows the LF- μ SR spectra for PrRuAsO. For $x = 0.75$, the muon relaxation function (A_{ZF}) in zero magnetic field consists of two separate components: $A_f e^{-\lambda_f t} + A_s e^{-\lambda_s t}$, where $\lambda_f = 1.4 \mu\text{s}^{-1}$ represents the fast decay rate and $\lambda_s = 0.25 \mu\text{s}^{-1}$ represents the slower one.

This empirical fitting function mimics the trend expected for a quasistatic Kubo-Toyabe relaxation [18] with a Lorentzian distribution of internal fields having half width at half maximum (HWHM) $\Delta B = \lambda_f / \gamma_\mu \sim 2$ mT and

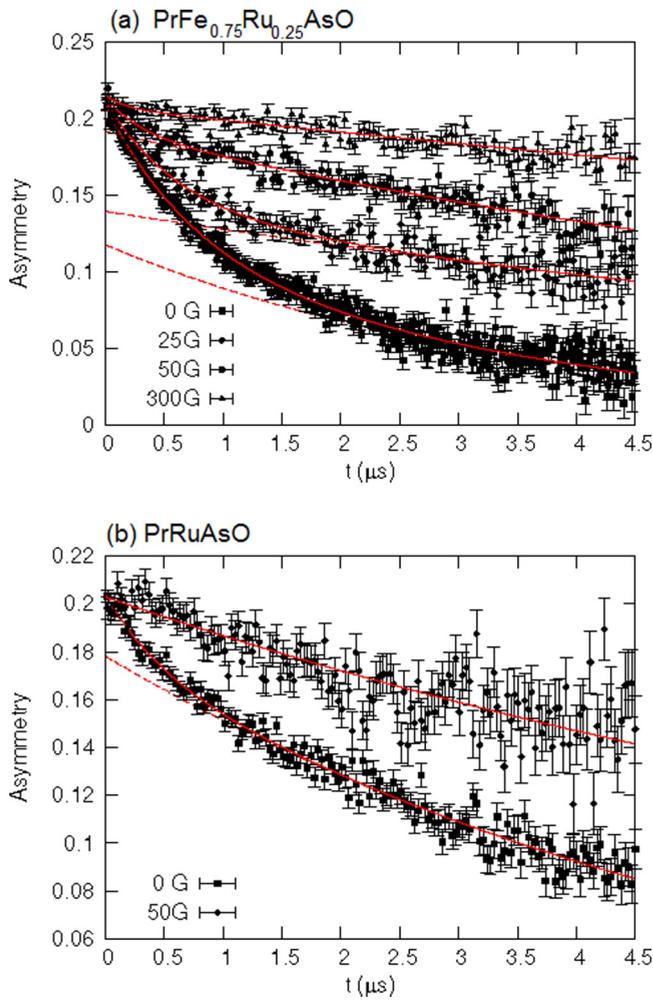


FIG. 6. (Color online) LF- μ SR time spectra for (a) $\text{PrFe}_{0.25}\text{Ru}_{0.75}\text{AsO}$ and (b) PrRuAsO , for different external fields $H \parallel S_{\mu}$. The lines are fits to the two nonoscillating amplitudes with distinct relaxation rates.

characterized by a slow dynamics with correlation time $\tau \sim 1/\lambda_s$. Notably, the HWHM of the $x = 0.75$ sample is nearly 20 times lower than for the $x = 0.6$ sample. In the static case ($\tau \rightarrow \infty$) $A_f = 2A_s$, but A_s is expected to grow as dynamics sets in.

The onset of longitudinal fields decreases the fast decay rate and increases the slow decay rate in both samples. For $x = 0.75$, a field of $H = 300$ G completely suppresses the faster (static) component of the muon relaxation and only leaves the slower dynamical component. This suggests that the ordering is quasistatic. The observed values of ΔB are consistent with the dipolar field from Pr moments ($\sim 3.6\mu_B$). Figure 6(b) shows the same for $x = 1$. In this case, a longitudinal field $H = 50$ G completely suppresses the faster (static) component of the zero-field relaxation and the residual dynamics is a little bit faster. The difference between the $x = 0.75$ and 1 amplitude weights, field dependencies, and decay rates of the faster component might arise from the fact that in the $x = 0.75$ material an extra contribution from Fe fluctuations, indirectly driven by the Pr fluctuations, is possible. It should be noticed that such fluctuations are absent in the $\text{LaFe}_{1-x}\text{Ru}_x\text{AsO}$ for $x > 0.6$ where no Pr is present [9].

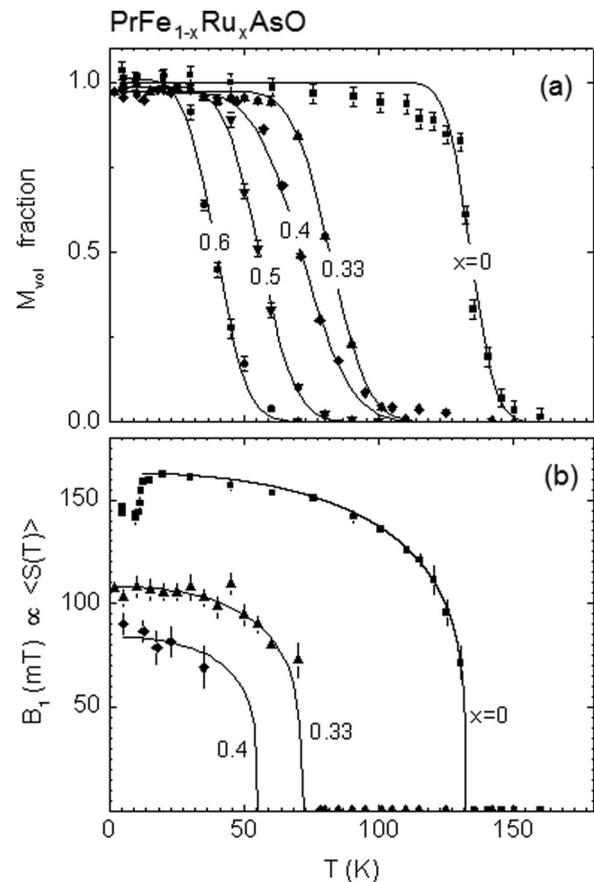


FIG. 7. (a) Magnetic volume fraction as a function of temperature for $x = 0.33, 0.4, 0.5,$ and 0.6 , with the main contribution from SDW ordering. The lines are guides for the eye fits. (b) Temperature evolution of the internal field B_1 proportional to the mean magnetic order parameter $\langle S \rangle$. The lines are the best fit to a phenomenological mean-field-like function as described in the text.

V. DISCUSSION

Figure 8(a) displays the T versus x phase diagram for $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ as determined by neutron diffraction and μ SR, with some additional points determined from anomalies detected in heat capacity and resistivity measurements. Using the orthorhombicity criterion described above, the tetragonal-to-orthorhombic structural transition is detected by neutron scattering for x up to 0.4 . Long-range magnetic order as detected by neutron diffraction is observed only for $x \leq 0.1$. Conversely, from the μ SR data one detects signs of static moments in the FeAs layers to approximately $x = 0.6$, and evidence for Pr moments up to $x = 1$. To reconcile these observations, it must be noted that the neutron measurements of magnetic Bragg peaks are sensitive to spatially dependent long-range order. Conversely, muons provide a sensitive probe of local magnetic fields, and therefore may detect local fields associated with static short-range order, i.e., with magnetic moments that fluctuate slowly (correlation times less than $1 \mu\text{s}$) and with a short magnetic coherence length (even less than 10 lattice spacings) [19]. Such SRO does not contribute to the magnetic Bragg peaks detected via neutron diffraction.

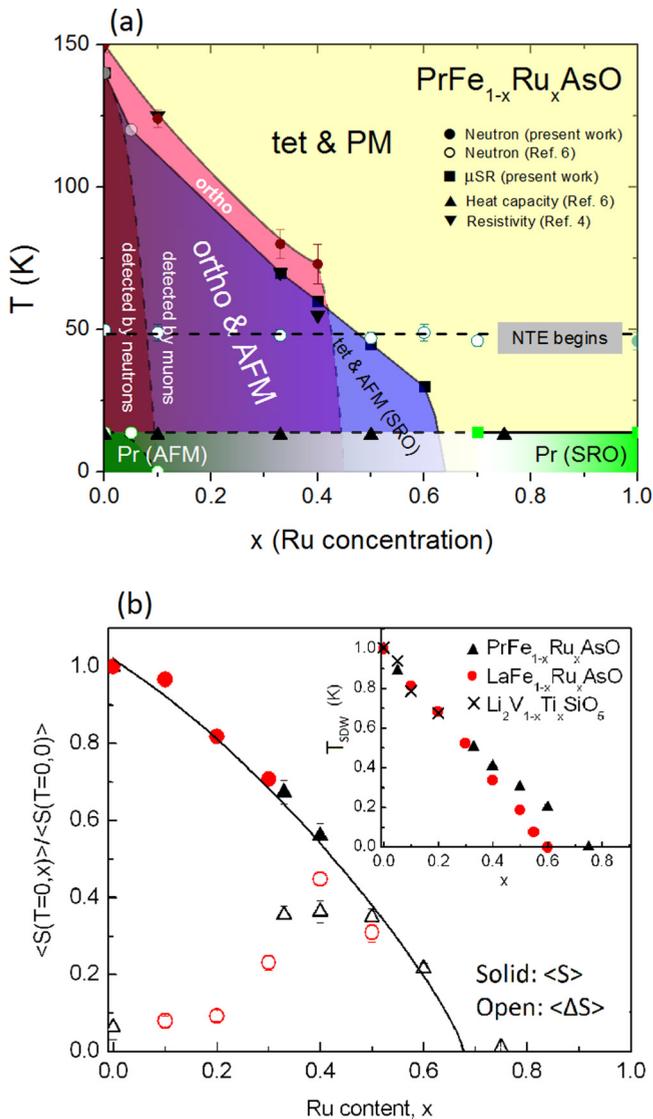


FIG. 8. (Color online) (a) A phase diagram for $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ constructed using data presented in this paper and also data from Ref. [10]. tet: tetragonal; ortho: orthorhombic; AFM: antiferromagnetic; PM: paramagnetic; SRO: short-range order; NTE: negative thermal expansion. The location of the structural transition is defined by the orthorhombicity analysis discussed in the text. (b) The doping dependence of the staggered magnetization at zero temperature $S(0, x)$ (solid symbols) and of its distribution width $\Delta S(0, x)$ (open symbols) in $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ (triangles) and $\text{LaFe}_{1-x}\text{Ru}_x\text{AsO}$ (circles, from Ref. [9]). The data are normalized to the value of the undoped member $S(0, 0)$. (b, inset): Doping dependence of magnetic transition temperatures T_{SDW} normalized to the undoped value for $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$, $\text{LaFe}_{1-x}\text{Ru}_x\text{AsO}$, and $\text{Li}_{1/2}\text{V}_{1-x}\text{Ti}_x\text{SiO}_5$.

The muon data for samples with $0.4 \leq x \leq 0.6$ exhibit overdamped oscillations and the μSR asymmetry displays a component with a fast decay rate ($\sigma_1 \sim 50 \mu\text{s}^{-1}$), indicating that the system is still magnetically ordered but the muon spin precessions have become incoherent. Conventionally, this implies that the correlation length of the Fe ordered domains has become shorter than about 10 unit cells [19]. This suggests a transition from LRO to SRO as detected by muons. This

is indicated by a dashed vertical line in Fig. 8(a) around $x = 0.4$, which interestingly coincides with the suppression of the structural transition as detected by neutrons. The fact that the progressive reduction of T_{SDW} is closely accompanied by the reduction of T_S hints at significant magnetoelastic coupling in the FeAs layers.

The persistence of static moments as observed by μSR despite the absence of LRO implied by the neutron measurements may provide a clue to the reason for the failure of superconductivity to appear in $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$.

Notwithstanding the fact that the coexistence of magnetic order and superconductivity is possible in Fe-pnictide compounds, superconductivity almost always emerges in these materials when both the structural and magnetic transitions are suppressed. However, there is evidence that a necessary condition for the emergence of superconductivity is the persistence of magnetic fluctuations. Some indirect evidence for the latter statement is the complete absence of magnetic fluctuations in the collapsed tetragonal phase observed in 122 family materials [20]. One can speculate that mutually uncorrelated but effectively frozen Fe spin clusters might exist in randomly diluted $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ at low temperatures. As a consequence, a static moment might be detected by a local probe such as μSR , and the absence of significant magnetic fluctuations would impede the emergence of a superconducting ground state.

Figure 8(b) shows the evolution of the magnetic order parameter $\langle S(T \rightarrow 0) \rangle$ versus x as determined by μSR . The spin dilution caused by Ru/Fe substitution reduces both the ordering temperature T_{SDW} and the moment size gradually. The complete suppression of the SDW ordering is determined to be around $x = 0.6$ which is similar to the concentration inferred from previous resistivity measurements [8]. Perhaps coincidentally, this is very close to the disruption of superconductivity by Ru/Fe substitution in F-optimally doped 1111 [21–24]. This value may be very significant as discussed in the following.

A proper description of the magnetism in the Fe pnictides must account for the fact that the systems are itinerant, however, despite this many of the main features can be understood in terms of Hamiltonian models related to local spins. The two-dimensional J_1 - J_2 model with Heisenberg nearest-neighbor (J_1) and next-nearest-neighbor (J_2) interactions on a square lattice [25] exhibits a striped phase for $J_2/J_1 \geq 1/2$. Moreover, any nonzero coupling to the lattice results in an Ising-nematic transition associated with a rectangular lattice. It can be argued on the basis of symmetry that spin-driven Ising nematic order must be accompanied by both a structural phase transition and orbital order [26], and that nematic order may arise from a correlation-driven electronic instability. In any case, the close association of the orthorhombic structural transition and striped antiferromagnetic order in the iron pnictides inspired many applications of the J_1 - J_2 model to explain the underlying physics [27–32]. Caution must be exercised in applying the J_1 - J_2 model to iron-pnictide systems. Inelastic neutron scattering experiments [33–36] and first-principles calculations [37] found that fitting observed magnetic excitations using the J_1 - J_2 Hamiltonian led to parameters that were physically incompatible with the known ordering scenarios and incapable of giving an acceptable explanation of the response functions.

Since then, there has been much work [33,38–40] showing that a minimal effective model must also include a biquadratic exchange term $K(S_1 \cdot S_2)^2$ and a small interplane coupling J_c .

The biquadratic exchange term must exist in the system and also accounts at least partially for the expected effects of itinerancy. With this Hamiltonian, the observed magnetic excitations can be explained with physically reasonable fitted parameters. Within the context of this expanded model, the scenario for magnetic and structural order remain the same as that expected for the J_1 - J_2 , with some minor renormalizations of the parameters [38].

As the moment size is reduced, the significance of the biquadratic term is also diminished and one expects that the J_1 - J_2 model can provide an even better description of the system. In this context, it is very interesting to consider the vanishing of detectable magnetic order near $x = 0.6$. In the simplest scenario for magnetic dilution, magnetic order is expected if the concentration of magnetic ions (here $1 - x$) is greater than or equal to the percolation concentration of the lattice. When the interactions are of the same magnitude, the percolation concentration of the J_1 - J_2 model should be essentially the same as the square lattice with nearest-neighbor and next-nearest-neighbor connectivity. This model leads to a percolation concentration for magnetic ions almost exactly at the value $1 - x = 0.4$ [41]. The fact that this coincides with the disappearance of static magnetism in $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ is a strong indicator that the core physics of the J_1 - J_2 model is at play. We note that the J_1 only model exhibits percolation at $1 - x = 0.59$ [41]. The inset of Fig. 8(b) compares the doping dependence of T_{SDW} in $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ to two other systems that also cited the J_1 - J_2 model for magnetoelastic coupling, namely, $\text{LaFe}_{1-x}\text{Ru}_x\text{AsO}$ [9] and $\text{Li}_2\text{V}_{1-x}\text{Ti}_x\text{SiO}_5$ [42], the latter being an archetype of the $S = 1/2$ J_1 - J_2 square-lattice model. The close association of the structural transition with the magnetic order is also explained naturally by the Ising-nematic scenario predicted for localized spins in the J_1 - J_2 model. If one takes into account for the presence of a magnetoelastic coupling in the system, the structural transition is closely linked to the occurrence of a spin nematic phase at T_S which anticipates the breaking of the rotational symmetry that is associated with the magnetic transition at T_{SDW} .

As discussed earlier, μSR shows that SRO of the Pr moments in $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ persists up to $x = 1$. This is consistent with the anomalies observed in the susceptibility and specific-heat measurements around $T_{\text{Pr}} \sim 14$ K (see Fig. 1 for the PrRuAsO data). The ZF- μSR results indicate a moderately fast depolarization rate in the muon asymmetry around the same temperature. This implies the presence of a broad field distribution generated by a noncollinear arrangement of the Pr moments. LF- μSR spectra shown in Fig. 6 suggest that the magnetic phase is mainly quasistatic. Notably, the NTE seen in the c axis also persists over the entire range of Ru concentrations. Although T_{N}^{Pr} and T_{NTE} are markedly different, the continuous presence of both throughout the entire doping

range leads one to speculate that there is a relation between the ordering of the Pr sublattice and the NTE, and if the latter is driven by magnetoelastic coupling [13], the Pr moments are relevant. Indeed, as shown in Fig. 8(b), the doping dependence of the quantities T_{SDW} and $\langle S(0) \rangle$ in $\text{LaFe}_{1-x}\text{Ru}_x\text{AsO}$ is similar to that seen in $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$, yet the NTE effect has not been observed in $\text{LaFe}_{1-x}\text{Ru}_x\text{AsO}$ [11].

VI. CONCLUSION

In summary, we have combined neutron powder diffraction and muon spin relaxation data for the $\text{PrFe}_{1-x}\text{Ru}_x\text{AsO}$ series, completing the study up to $x = 1$. The substitution of diamagnetic Ru for magnetic Fe generates a spin dilution process which gradually suppresses the ordering in the FeAs layers, in which evidence for static moments persists until around $x = 0.6$, the magnetic percolation threshold expected under a localized J_1 - J_2 model [9,41]. The gradual suppression of the magnetic phase is closely followed by the reduction of the structural tetragonal-orthorhombic phase transition temperature. The lattice distortion and the magnetic ordering are found to be strongly coupled, as predicted for pnictides by many theoretical works [27–32]. The persistence of static moments and possible suppression of magnetic fluctuations may be related to the absence of superconductivity in the system.

In addition, we found that both the magnetic ordering of the Pr sublattice and the negative thermal expansion of the c -axis phenomena persist up to $x = 1$. We speculate that the abnormal thermal expansion behavior can be linked to the magnetoelastic coupling within the Pr sublattice, which survives despite of the disruption of the ordering of Fe moments.

ACKNOWLEDGMENTS

The research reported here utilized the μSR facilities at the Paul Scherrer Institute, Villigen, Switzerland, and neutron scattering facilities at the Spallation Neutron Source, Oak Ridge National Laboratory (ORNL), which is sponsored by the Scientific User Facilities Division of the Office of Science, Basic Energy Sciences, U. S. Department of Energy (BES DOE). We are grateful to A. Amato and H. Luetkens of the Swiss Muon Source group for technical support. We would like to thank A. A. Aczel and T. J. Williams of ORNL for valuable conversations. A.H. and S.E.N. were supported by the Scientific User Facilities Division of BES DOE. M.A.M. was supported by the Materials Sciences and Engineering Division of BES DOE. S.S. and P.C. acknowledge the financial support of Fondazione Cariplo (Research Grant No. 2011-0266). R.D.R., P.B., P.C., and S.S. acknowledge partial support of PRIN2012 Project No. 2012X3YFZ2. Y.Y. was supported by the BES DOE, through the EPSCoR, Grant No. DE-FG02-08ER46528.

[1] M. D. Lumsden and A. D. Christianson, *J. Phys.: Condens. Matter* **22**, 203203 (2010).

[2] D. C. Johnston, *Adv. Phys.* **59**, 803 (2010).

[3] J. M. Tranquada, G. Xu, and I. A. Zaliznyak, *J. Magn. Magn. Mater.* **350**, 148 (2014).

[4] G. R. Stewart, *Rev. Mod. Phys.* **83**, 1589 (2011).

- [5] D. Johrendt, *J. Mater. Chem.* **21**, 13726 (2011).
- [6] A. Thaler, N. Ni, A. Kracher, J. Q. Yan, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **82**, 014534 (2010).
- [7] S. K. Kim, M. S. Torikachvili, E. Colombier, A. Thaler, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **84**, 134525 (2011).
- [8] M. A. McGuire, D. J. Singh, A. S. Sefat, B. C. Sales, and D. Mandrus, *J. Solid State Chem.* **182**, 2326 (2009).
- [9] P. Bonfà, P. Carretta, S. Sanna, G. Lamura, G. Prando, A. Martinelli, A. Palenzona, M. Tropeano, M. Putti, and R. De Renzi, *Phys. Rev. B* **85**, 054518 (2012).
- [10] Y. Yiu, V. O. Garlea, M. A. McGuire, A. Huq, D. Mandrus, and S. E. Nagler, *Phys. Rev. B* **86**, 054111 (2012).
- [11] A. Martinelli, A. Palenzona, I. Pallecchi, C. Ferdeghini, M. Putti, S. Sanna, C. Curfs, and C. Ritter, *J. Phys.: Condens. Matter* **25**, 395701 (2013).
- [12] M. Tropeano, M. R. Cimeterle, C. Ferdeghini, G. Lamura, A. Martinelli, A. Palenzona, I. Pallecchi, A. Sala, I. Sheikin, F. Bernardini, M. Monni, S. Massidda, and M. Putti, *Phys. Rev. B* **81**, 184504 (2010).
- [13] S. A. J. Kimber, D. N. Argyriou, F. Yokaichiya, K. Habicht, S. Gerischer, T. Hansen, T. Chatterji, R. Klingeler, C. Hess, G. Behr, A. Kondrat, and B. Buchner, *Phys. Rev. B* **78**, 140503 (2008).
- [14] M. A. McGuire, A. F. May, and B. C. Sales, *J. Solid State Chem.* **191**, 71 (2012).
- [15] H. Maeter, H. Luetkens, Y. G. Pashkevich, A. Kwadrin, R. Khasanov, A. Amato, A. A. Gusev, K. V. Lamonova, D. A. Chervinskii, R. Klingeler, C. Hess, G. Behr, B. Büchner, and H.-H. Klauss, *Phys. Rev. B* **80**, 094524 (2009).
- [16] R. D. Renzi, P. Bonf, M. Mazzani, S. Sanna, G. Prando, P. Carretta, R. Khasanov, A. Amato, H. Luetkens, M. Bendele, F. Bernardini, S. Massidda, A. Palenzona, M. Tropeano, and M. Vignolo, *Supercond. Sci. Technol.* **25**, 084009 (2012).
- [17] G. Prando, P. Bonfà, G. Profeta, R. Khasanov, F. Bernardini, M. Mazzani, E. M. Brüning, A. Pal, V. P. S. Awana, H.-J. Grafe, B. Büchner, R. De Renzi, P. Carretta, and S. Sanna, *Phys. Rev. B* **87**, 064401 (2013).
- [18] R. Kubo, *Hyperfine Interact.* **8**, 731 (1981).
- [19] A. Yaouanc and P. Dalmas de Reotier, *Muon Spin Rotation, Relaxation, and Resonance* (Oxford University Press, Oxford, 2011).
- [20] J. H. Soh, G. S. Tucker, D. K. Pratt, D. L. Abernathy, M. B. Stone, S. Ran, S. L. Bud'ko, P. C. Canfield, A. Kreyssig, R. J. McQueeney, and A. I. Goldman, *Phys. Rev. Lett.* **111**, 227002 (2013).
- [21] E. Satomi, S. C. Lee, Y. Kobayashi, and M. Sato, *J. Phys. Soc. Jpn.* **79**, 094702 (2010).
- [22] S. C. Lee, E. Satomi, Y. Kobayashi, and M. Sato, *J. Phys. Soc. Jpn.* **79**, 023702 (2010).
- [23] S. Sanna, P. Carretta, P. Bonfà, G. Prando, G. Allodi, R. De Renzi, T. Shiroka, G. Lamura, A. Martinelli, and M. Putti, *Phys. Rev. Lett.* **107**, 227003 (2011).
- [24] S. Sanna, P. Carretta, R. De Renzi, G. Prando, P. Bonfà, M. Mazzani, G. Lamura, T. Shiroka, Y. Kobayashi, and M. Sato, *Phys. Rev. B* **87**, 134518 (2013).
- [25] P. Chandra, P. Coleman, and A. I. Larkin, *Phys. Rev. Lett.* **64**, 88 (1990).
- [26] R. M. Fernandes, A. V. Chubukov, and J. Schmalian, *Nat. Phys.* **10**, 97 (2014).
- [27] C. Fang, H. Yao, W.-F. Tsai, J.-P. Hu, and S. A. Kivelson, *Phys. Rev. B* **77**, 224509 (2008).
- [28] R. M. Fernandes, L. H. VanBebber, S. Bhattacharya, P. Chandra, V. Keppens, D. Mandrus, M. A. McGuire, B. C. Sales, A. S. Sefat, and J. Schmalian, *Phys. Rev. Lett.* **105**, 157003 (2010).
- [29] E. Abrahams and Q. Si, *J. Phys.: Condens. Matter* **23**, 223201 (2011).
- [30] Q. Si and E. Abrahams, *Phys. Rev. Lett.* **101**, 076401 (2008).
- [31] C. Xu, M. Müller, and S. Sachdev, *Phys. Rev. B* **78**, 020501 (2008).
- [32] R. M. Fernandes, A. V. Chubukov, J. Knolle, I. Eremin, and J. Schmalian, *Phys. Rev. B* **85**, 024534 (2012).
- [33] A. L. Wysocki, K. D. Belashchenko, and V. P. Antropov, *Nat. Phys.* **7**, 485 (2011).
- [34] J. W. Lynn and P. Dai, *Phys. C (Amsterdam)* **469**, 469 (2009).
- [35] J. Zhao, D. T. Adroja, D.-X. Yao, R. Bewley, S. Li, X. F. Wang, G. Wu, X. H. Chen, J. Hu, and P. Dai, *Nat. Phys.* **5**, 555 (2009).
- [36] S. O. Diallo, V. P. Antropov, T. G. Perring, C. Broholm, J. J. Pulikkotil, N. Ni, S. L. Bud'ko, P. C. Canfield, A. Kreyssig, A. I. Goldman, and R. J. McQueeney, *Phys. Rev. Lett.* **102**, 187206 (2009).
- [37] Z. P. Yin, S. Lebegue, M. J. Han, B. P. Neal, S. Y. Savrasov, and W. E. Pickett, *Phys. Rev. Lett.* **101**, 047001 (2008).
- [38] J. Hu, B. Xu, W. Liu, N.-N. Hao, and Y. Wang, *Phys. Rev. B* **85**, 144403 (2012).
- [39] R. Yu, Z. Wang, P. Goswami, A. H. Nevidomskyy, Q. Si, and E. Abrahams, *Phys. Rev. B* **86**, 085148 (2012).
- [40] J. K. Glasbrenner, J. P. Velev, and I. I. Mazin, *Phys. Rev. B* **89**, 064509 (2014).
- [41] K. Malarz and S. Galam, *Phys. Rev. E* **71**, 016125 (2005).
- [42] N. Papinutto, P. Carretta, S. Gonthier, and P. Millet, *Phys. Rev. B* **71**, 174425 (2005).